

**İSTANBUL TECHNICAL UNIVERSITY ★ GRADUATE SCHOOL OF
SCIENCE ENGINEERING AND TECHNOLOGY**

**SYNTHESIS AND CHARACTERIZATION OF POLYSTYRENE – ZINC
PHTHALOCYANINE COMPOSITES**

**M. Sc. THESIS
Yunus Alp SÜTCÜLER**

Polymer Science and Technology

Polymer Science and Technology

Thesis Advisor: Prof.Dr. Ahmet GÜL

JUNE 2016

**İSTANBUL TECHNICAL UNIVERSITY ★ GRADUATE SCHOOL OF
SCIENCE ENGINEERING AND TECHNOLOGY**

**SYNTHESIS AND CHARACTERIZATION OF POLYSTYRENE – ZINC
PHTHALOCYANINE COMPOSITES**

**M. Sc. THESIS
Yunus Alp SÜTCÜLER
(515141026)**

Polymer Science and Technology

Polymer Science and Technology

Thesis Advisor: Prof.Dr. Ahmet GÜL

JUNE 2016

İSTANBUL TEKNİK ÜNİVERSİTESİ ★ FEN BİLİMLERİ ENSTİTÜSÜ

**POLİSTİREN – ÇİNKO FTALOSİYANİN KOMPOZİTLERİNİN SENTEZİ
VE KARAKTERİZASYONU**

**YÜKSEK LİSANS TEZİ
Yunus Alp SÜTCÜLER
(515141026)**

Polimer Bilimi ve Teknolojisi

Polimer Bilimi ve Teknolojisi

Tez Danışmanı: Prof. Dr. Ahmet GÜL

HAZİRAN 2016

To my family,

FOREWORD

First, I would like to thank my supervisor, Professor Ahmet Gül, for his encouragement, guidance, and patience.

I would like to thank my advisor, Altuğ Mert Sevim, for his help and tips about experimental work and support. He is not only a successful academician but also a charitable and gracious person.

I also thank to Barbaros Akkurt and Ilgın Nar for their helps.

I would like to thank to Professor İ.Ersin Serhatlı and Tuba Çakır Çanak for their helps about the experimental work.

Finally, i thank to my mother Gülay Sütçüler, my father İrfan Sütçüler, my brother Akın Sütçüler, my aunt Tuğba Sütçüler and littlest member of our family Arda Sütçüler, for their encouragement and support throughout my education.

June 2016

Yunus Alp SÜTCÜLER

Chemist

TABLE OF CONTENTS

	<u>Page</u>
FOREWORD	vii
TABLE OF CONTENTS	xiii
ABBREVIATIONS	xv
LIST OF SYMBOLS	xvii
LIST OF FIGURES	xix
SUMMARY	xxi
ÖZET	xxiii
1. INTRODUCTION	1
2. THEORETICAL PART	3
2.1 Composites	3
2.1.1 Classification of composites	3
2.1.2 Features of composites.....	4
2.1.3 Naming of composites	5
2.1.4 Polymer composites	6
2.2 General Properties and Applications of Polystyrene	6
2.3 Polymerization Types	8
2.3.1 Condensation polymerization	8
2.3.2 Addition polymerization	9
2.3.2.1 Anionic and cationic polymerization	9
2.3.2.2 Radicalic polymerization.....	11
2.4 Phthalocyanines	12
2.4.1 General information	12
2.4.2 Synthetic methods of phthalocyanines.....	14
2.4.2.1 Metal free phthalocyanines (H ₂ Pc).....	14
2.4.2.2 Metallophthalocyanines (MPc)	16
2.4.2.3 Synthesis of substituted phthalocyanines	17
2.4.2.4 Tetrasubstituted phthalocyanines	18
2.4.2.5 Octasubstituted phthalocyanines	19
2.4.2.6 New methods for synthesis of phthalocyanines	20

2.4.3 Purification of phthalocyanines	20
2.4.4 Characterization of phthalocyanines	21
2.4.4.1 FTIR spectra of phthalocyanines	22
2.4.4.2 ¹ H-NMR spectra of phthalocyanines	22
2.4.4.3 UV-Vis spectra of phthalocyanines	23
2.4.5 Recent developments on phthalocyanines	23
2.5 Click Chemistry	24
2.6 Previous Studies of Phthalocyanine-Polymer Composites	26
3. EXPERIMENTAL WORK	31
3.1 Instruments and Chemicals	31
3.2 Preparation of Polymers	31
3.2.1 Synthesis of PS-Br (1)	31
3.2.2 Synthesis of PS-N ₃ (2)	32
3.3 Synthetic Steps of Non-symmetrical Phthalocyanine Compound	32
3.3.1 Synthesis of 4-nitrophthalimide	32
3.3.2 Synthesis of 4-nitro phthalamide	33
3.3.3 Synthesis of 4-Nitrophthalonitrile	33
3.3.4 Synthesis of 4-(4-tert-butylphenoxy)phthalonitrile (3)	34
3.3.5 Synthesis of 4-((4-ethynylbenzyl)oxy)phthalonitrile (4)	34
3.3.6 Synthesis of 9(10),16(17),23(24)-Tris-(t-butylphenoxy)- {4-ethynylbenzyloxy} phthalocyaninatozinc(II) (5)	35
3.4 Synthesis of PS- Zinc Phthalocyanine Composites via Click Chemistry	36
4. RESULTS AND DISCUSSION	39
4.1 Synthesis	39
4.2 Characterization	40
4.2.1 Characterization of novel phthalonitrile precursor (4)	40
4.2.2 Characterization of the unsymmetrical ZnPc (5)	40
4.2.3 Characterization of azido-polystyrene	41
4.2.4 Characterization of phthalocyanine-terminated polystyrene	41
5. CONCLUSION	47
REFERENCES	49
APPENDIXES	55
CURRICULUM VITAE	72

ABBREVIATIONS

Pc	: Phthalocyanine
PS	: Polystyrene
PS-Br	: Bromo-terminated polystyrene
PS-N₃	: Azido-polystyrene
ZnPc	: Zinc phthalocyanine
PS-ZnPc	: Polystyrene-unsymmetrical phthalocyanine compound
MPc	: Metallophthalocyanine
H₂Pc	: Metal-free phthalocyanine
Li₂Pc	: Lithium phthalocyanine
FT-IR	: Fourier transform infrared
¹H NMR	: Proton nuclear magnetic resonance
PDT	: Photo dynamic therapy
UV-Vis	: Ultraviolet-visible

LIST OF SYMBOLS

A	: Alpha
β	: Beta
k	: Rate constant
ppm	: Parts per million
$^{\circ}\text{C}$: Celsius
M_n	: The number average molecular weight
M_w	: The weight average molecular weight
M_w/M_n	: The molecular weight distribution

LIST OF FIGURES

	<u>Page</u>
Figure 2.1: Classification of composites.....	4
Figure 2.2: Impact properties of some kind of composites.....	5
Figure 2.3: Polyester formation via condensation polymerization.	8
Figure 2.4: Nylon 66 formation via condensation polymerization.	9
Figure 2.5: Epoxy resin synthesis via condensation polymerization.	9
Figure 2.6: Stages of anionic polymerization.	10
Figure 2.7: Stages of cationic polymerization.	11
Figure 2.8: Example of a propagation reaction.....	12
Figure 2.9: An example termination scheme.	12
Figure 2.10: (a) Metal-free phthalocyanine, (b) metallophthalocyanine.	14
Figure 2.11: Precursors that lead to phthalocyanine formation.	15
Figure 2.12: Scheme for the synthesis of non-metallophthalocyanines and starting materials.....	16
Figure 2.13: Scheme for the synthesis of metallophthalocyanines and starting materials.....	17
Figure 2.14: 4-Nitrophthalonitrile synthesis.	18
Figure 2.15: Structural isomers of tetra-substituted phthalocyanines.....	19
Figure 2.16: Non-peripherally Octasubstituted Phthalocyanines' Synthesis (H_2Pc - $onp-C_n$).....	20
Figure 2.17: General scheme some kind of “click” chemistry cycloaddition reactions.	25
Figure 2.18: Huisgen 1,3-dipolar cycloaddition.	26
Figure 2.19: Synthetic scheme of $SiPc[OSi(C_nH_{2n+1})_3]_2$ ($SiPc_n$, $n = 2, 3, 4, 6$) and $SiPc[OSi(iBu)_2C_{18}H_{37}]_2$ ($SiPcB_{18}$).....	27
Figure 2.20: The synthesis of unsymmetrical zinc (II) phthalocyanine.....	28
Figure 2.21: Chemical structure of investigated compounds ($M=Zn, Cu$).	29
Figure 2.22: Molecular structures of the low symmetrically substituted complexes. MCPc = monocarboxy phthalocyanine (complexes 1-3), TPCPc = tetraphenylcarboxyphthalocyanine (6) and ZnPc.	30
Figure 3.1: Polymerization and azidation process of styrene.	32
Figure 3.2: Synthesis of 4-Nitrophthalimide.....	33

Figure 3.3: Synthesis of 4-nitro phthalamide.....	33
Figure 3.4: Synthesis of 4-Nitrophthalonitrile.....	34
Figure 3.5: Synthesis of 4-(4-tert-butylphenoxy)phthalonitrile.....	34
Figure 3.6: Synthesis of 4-((4-ethynylbenzyl)oxy)phthalonitrile.....	35
Figure 3.7: Synthesis of novel zinc(II)phthalocyanine 5.....	36
Figure 3.8: PS- Zinc Phthalocyanine Composites.....	37
Figure 4.1: FTIR spectrum of (a) 4, (b) ZnPc, (c) PS-ZnPc.....	42
Figure 4.2: FTIR spectrum of (a) PS-Br, (b) PS-N ₃ , (c) PS-ZnPc.....	44
Figure 4.3: UV-Vis spectrum of (a) PS-Br, (b) PS-N ₃ , (c) PS-ZnPc.....	45
Figure 4.4: ¹ H-NMR spectrum of ZnPc, PS-Br, PS-N ₃ , PS-ZnPc.....	46
Figure A. 1: ¹ H-NMR spectrum of unsymmetrical ZnPc.....	56
Figure A. 2: ¹ H-NMR spectrum of PS-Br.....	57
Figure A. 3: ¹ H-NMR spectrum of PS-N ₃	58
Figure A. 4: ¹ H-NMR spectrum of PS-ZnPc.....	59
Figure A. 5: ¹ H-NMR spectrum of 4-((4-ethynylbenzyl)oxy)phthalonitrile.....	60
Figure A. 6: ¹³ C-NMR spectrum of 4-((4-ethynylbenzyl)oxy)phthalonitrile.....	61
Figure A. 7: UV-Vis spectrum of PS-Br.....	62
Figure A. 8: UV-Vis spectrum of PS-N ₃	63
Figure A. 9: UV-Vis spectrum of ZnPc.....	64
Figure A. 10: UV-Vis spectrum of PS-ZnPc.....	65
Figure A. 11: FT-IR spectrum of (4).....	66
Figure A. 12: FT-IR spectrum of (3).....	67
Figure A. 13: FT-IR spectrum of PS-Br.....	68
Figure A. 14: FT-IR spectrum of PS-N ₃	69
Figure A. 15: FT-IR spectrum of ZnPc.....	70
Figure A. 16: FT-IR spectrum of PS-ZnPc.....	71

SYNTHESIS AND CHARACTERIZATION OF POLYSTYRENE – ZINC PHTHALOCYANINE COMPOSITES

SUMMARY

Composite is a material consisting of two or more different phases and having bulk characteristics importantly different from those of any of the constituents. Matrix phase is the primary phase having a continuous character. Matrix is usually more ductile and less hard phase. It holds the dispersed phase and shares a load with it. Dispersed (reinforcing) phase is embedded in the matrix in a discontinuous form. This secondary phase is called the dispersed phase. Dispersed phase is generally stronger than the matrix, consequently, it is sometimes called reinforcing phase. Matrix materials are generally polymers, ceramics or metals. The polymer matrices also called resins are by far the most common due to the versatility of their properties such as light weight, easy processing and corrosion resistance. Composite materials are designed and prepared for particular applications with desired properties such as light weight and high performance.

Polystyrene is made from petroleum, a non-sustainable, non-renewable, heavily polluting, and fast-disappearing commodity. CD covers and plastic drinking cups are made out of the polymer polystyrene. This polymer is known to be a clear brittle plastic that is synthesized by a free radical polymerization. Polystyrene is not biodegradable. It takes several decades to hundreds of years for polystyrene to deteriorate in the environment or in a landfill. Polystyrene takes up more spaces in landfills than paper, and will eventually re-enter the environment when water or mechanical forces breach landfills. Polystyrene contains the toxic substances styrene and benzene, suspected carcinogens and neurotoxins that are hazardous to humans.

Phthalocyanines are planar macrocycle molecules related to porphyrins constituted by four isoindole units presenting an 18 π electron aromatic cloud delocalized over an arrangement of alternated carbon and nitrogen atoms. Phthalocyanines have high thermal and chemical stability. Phthalocyanines are conjugated polymers which are gaining much interest due to their special electronic and optical properties that stem from phthalocyanine macrocycle. Conjugation of the macrocycles with polymer chains enhances their processability, provides a means to control the molecular arrangement of the phthalocyanine rings, improves their solubility in common organic solvents. The main problems in the phthalocyanine chemistry are their insolubility in most of the solvents and aggregation tendency in solutions because of the molecular interactions between the macrocyclic rings. Elemental analysis used in the characterization of organic compounds, and FTIR and UV-Vis are also used in the characterization of phthalocyanine. In particular, the position of the Q-band in the visible range is influenced by the substituents and the central metal atom. Therefore, these techniques play an important role in the characterization of phthalocyanines. NMR is a useful technique for soluble phthalocyanine derivatives. However, due to

the orientations of phthalocyanine compounds to strong aggregation in solution and causing enlargement prevent a good spectrum from NMR.

Cu(I)-catalyzed azide-alkyne cycloaddition (CuAAC) click reaction, which was initially postulated as a powerful tool for organic synthesis, has been extensively applied as a successful polymer functionalization technique. The cycloaddition first described by Rolf Huisgen involves an alkyne and an azide undergoing a cycloaddition leading to a triazole cycle. The reaction met the click chemistry concept criteria when its conditions were considerably softened by the use of copper catalysts: a reliable, easy, selective, and high-yielding reaction. In contrast to the uncatalyzed conditions, the use of copper(I) salts ensures of the exclusive formation of the 1,2,3-triazole, with the regioselective formation of the 1,4-regioisomer. The required conditions are indeed exceptionally soft; no high temperature or extreme pH conditions are necessary. The possible solvent range is very wide, even including water. The advantages of non-conventional conditions such as microwave irradiation were recently reported.

This study was undertaken to prepare polystyrene (PS) and asymmetric zinc phthalocyanine, azidation of polystyrene, performing click reaction between azidated polystyrene and asymmetric zinc phthalocyanine. Polystyrene was synthesized by using ATRP method and azidation was done in a step by using sodium nitrate. Azidated polystyrene and asymmetric zinc phthalocyanine were bonded with each other via Huisgen 1,3-dipolar cycloaddition.

Prepared polystyrene- asymmetric zinc phthalocyanine composite was characterized by ¹H-NMR, FTIR, and UV-Vis spectroscopy. The results were taken from FTIR spectroscopy showing that preparing of phthalocyanine and polystyrene, azidation of polystyrene and Huisgen 1,3-dipolar cycloaddition were performed successfully. Also, UV-Vis spectrum demonstrated the purity of produced phthalocyanine and polystyrene. ¹H-NMR spectrum shows that the forming of triazole structure and azido-terminated polystyrene- unsymmetrical zinc phthalocyanine composite.

POLİSTİREN – ÇİNKO FTALOSİYANİN KOMPOZİTLERİNİN SENTEZİ VE KARAKTERİZASYONU

ÖZET

Kompozit malzemeler iki veya daha fazla bileşenden oluşan ve bileşenlerinden farklı özelliklere sahip olan yapılardır. Matris fazı genellikle daha çok esneyebilen ve daha az sertliğe sahip olan sürekli bileşendir. Matris fazı takviye fazını tutar ve yükü onunla paylaşır. Takviye fazı matris fazına tutunur ve matris fazından daha güçlüdür. Takviye fazı kompozit özelliklerini geliştirmek için kullanıldığından bazen güçlendirici faz olarak nitelendirilir. Matris fazı genellikle polimer, seramik ve metallere oluşur. Polimer matrisleri genellikle reçine olarak adlandırılır ve hafiflik, kolay işlenebilirlik, iyi korozyon dayanımı gibi çeşitli özelliklere sahiptir. Kompozit malzemeler özel uygulamalar için istenen özelliklerde tasarlanır ve bu özelliklere uygun bileşenler seçilerek hazırlanır.

Polistiren petrolden üretilir. Sürdürülebilirlik ve yenilenebilirlik açısından uygun olmayan bu ürün ayrıca çevre kirliliğine neden olmaktadır. CD koruyucu kaplar ve plastik bardaklar polistirenden üretilmektedir. Serbest radikal polimerizasyonu ile üretilen bu polimer kırılkan, sert bir yapıya sahiptir ve geri dönüşümü yoktur. Polistirenin doğada parçalanması onlarca, yüzlerce yıl sürer. Atık depolama alanlarındaki polistirenden üretilen malzemelerin miktarı, atık kağıt türevlerinin miktarından fazladır ve bu malzemeler zamanla su ve mekanik kuvvetlerin etkisiyle doğaya karışır. Polistiren türevleri stiren ve benzen gibi sağlığa zararlı, tehlikeli bileşenlere sahiptir, bundan dolayı kanser ve diğer sağlık sorunlarına neden olabilmektedir.

Ftalosiyanimler düzlemsel moleküllerdir ve 18 π elektronuna sahip olup isoindol yapılarından oluşurlar. Ftalosiyanimler yüksek termal ve kimyasal kararlılığa sahip, ana yapısı karbon ve azot elementlerinden oluşan makro yapılardır. Ftalosiyanimler çok özel elektronik ve optik özelliklere sahip olan konjuge makrohalkalardır. Polimer zinciriyle halkalar arasındaki konjugasyon, ftalosiyanim bileşiğinin işlenebilirliğini ve yapısal düzenlemeye olanak sağlayarak organik çözücülerde çözünebilirliğini sağlamıştır. Ftalosiyanimler hakkındaki en büyük problemler ise çözücülerin çoğunda çözünmemeleri ve halkalar arasındaki moleküler etkileşimden dolayı agregasyon eğilimi göstermeleridir. Ftalosiyanimlerin karakterizasyonu için FTIR, UV-Vis ve NMR spektroskopisi teknikleri kullanılabilir. UV-Vis spektrumunda Q bandının görünür bölgedeki yeri merkez atoma ve süstitüentlere doğrudan bağlıdır. Bu nedenle bu teknik ftalosiyanimlerin yapısal incelemesinde önemli rol oynamaktadır. Çözünebilir ftalosiyanimler için ise NMR spektroskopisi de uygun bir analiz tekniğidir. Ancak ftalosiyanimlerdeki yoğun etkileşimler ve agregasyon göz önünde bulundurulduğunda NMR spektrumunun yapı hakkında kesin bilgi vermesi mümkün olmayabilir.

Ftalosiyanın geniş metal-iyon kimyası, hem çok ilginç hem de çok fonksiyonludur. Örneğin, spesifik ftalosiyaninler yarı iletken özellik gösterebildikleri gibi, kimyasal transformasyonların değişiminde de katalitik etki sergilerler. Bunun yanında biyokimyasal sistemlerin aydınlatılması için yapılan model çalışmalarda da irdelenmektedirler. Ftalosiyaninlerin temel kullanım alanlarından birisi de endüstriyel renklendiricilerdir.

Bakır katalizli azid- alkin siklokatılma klik reaksiyonu organik sentezlerde ve polimerlerin işlevselleştirilmesinde çok kullanılan bir yöntemdir. Triazol oluşumu gözlenen azid-alkin katılması ilk olarak Rolf Huisgen tarafından keşfedilmiştir. Bu reaksiyon “klik reaksiyonu” olarak bilinmektedir ve bakır katalizli yapıldığında reaksiyon şartları güvenilir, yüksek verimli, seçici ve kolaydır. Bakır katalizli reaksiyon katalizör kullanmadan yapılan reaksiyona göre 1,2,3-triazol yapısının oluşması bakımından çok daha verimli ve güvenilirdir. Yüksek sıcaklık sıcaklığa ya da pH ayarlama işlemine ihtiyaç duyulmaz. Kullanılabilecek solvent çeşitleri oldukça fazladır. Geleneksel olmayan yöntemin kullanımının avantajlarından biri mikrodalga ışınları yayılmasıdır.

Yaptığımız çalışmada azidlenmiş polistiren ve uç alkil bileşiği içeren asimetrik çinko ftalosiyanın klik reaksiyonu ile birbirine tutturulmuş ve triazol halkasının oluştuğu gözlenmiştir. Polistiren ATRP metodu ile sentezlenmiş ve devamında sodyum nitrat ile reaksiyona sokularak azidleme işlemi yapılmıştır. Asimetrik ftalosiyanın ise merkez atomu çinko olarak sentezlenmiş ve kolon kromatografisi ile saflaştırılmıştır. Azidlenmiş polimer ile asimetrik çinko ftalosiyanın azid-alkin siklokatılma reaksiyonu ile birbirine bağlanmış ve polistiren-ftalosiyanın kompoziti elde edilmiştir.

Çalışmada kullanılan ligandlardan biri ve sentezlenen ftalosiyanın daha önce literatürde bulunmayan, ilk kez sentezlenen bileşiklerdir. Ftalosiyanın agregasyon ve düşük çözünürlük özellikleri göz önüne alınarak sentezlenmiştir. Agregasyonu mümkün olduğunca azaltabilecek ve çözünürlüğün artmasını sağlayacak büyük gruplu ligand tercih edilmiştir. Sentez için kullanılan yöntemde çok sayıda yan ürün oluştuğu için kromatografik yöntemlerle ayırma yapılmış ve deneysel çalışmaların ileri safhalarında kullanılabilecek ürün elde edilmiştir. Ayrıca hedef bileşiğin üretilmesinde klik reaksiyonundan faydalanılacağı için bu reaksiyonda yer alacak bileşikler bu reaksiyona uygun olarak modifiye edilmek zorundadır. Sentezlenen ftalosiyanın bileşiği alkin grubu içerdiği için reaksiyona uygundur. Kullanılan bromo polistiren ise azidlenerek klik reaksiyonu için uygun hale getirilmiştir. Son olarak azidlenmiş polistiren ve asimetrik çinko ftalosiyanın bileşiği klik reaksiyonu kullanılarak birbirine tutturulmuş ve hedeflenen ürün başarıyla sentezlenmiştir. Çeşitli cihazlarla yapılan işlemler incelenmiş ve işlem basamakları kontrol edilerek deneysel çalışmalar tamamlanmıştır.

Hazırlanan polistiren-asimetrik çinko ftalosiyanın kompoziti ¹H-NMR, FTIR ve UV-Vis spektroskopi yöntemleri kullanılarak analiz edilmiştir. FTIR spektrumu incelendiğinde sentezlenen ligandın, asimetrik çinko ftalosiyanınin, polistirenin ve azidlenme işleminin başarıyla yapıldığı görülmüştür. Ayrıca UV-Vis spektrumu incelendiğinde asimetrik çinko ftalosiyanın yapısının başarıyla saf olarak elde edildiği anlaşılmıştır. Tüm bunlara ek olarak ¹H-NMR spektrumları incelendiğinde polistirene ait azidleme reaksiyonunun başarıyla tamamlandığı ve son olarak klik

reaksiyonu ile elde edilen polistiren-asimetrik inko ftalosiyanın kompozitinin hedeflendiđi gibi sentezlendiđi grlmştr.

alıřma kapsamında yapılan spektral analizler, sentezin her ařamasında belirli piklerin varlıđı veya yokluđunu iermesi sebebiyle reaksiyonların mkemmел bir şekilde takip edilmesini sađlamıřtır.

Hazırlanan polistiren-asimetrik inko ftalosiyanın kompoziti, yksek teknoloji uzmanları tarafından ileri arařtırmalar yapılmayı hak etmektedir. İlerleyen zamanda sentezlenen bileřik ile ilgili farklı alıřmalar yapılması tasarlanmaktadır.

1. INTRODUCTION

Polystyrene is made from petroleum, a non-sustainable, non-renewable, heavily polluting, and fast-disappearing commodity. The environmental impacts of polystyrene production in the categories of energy consumption, greenhouse gas effect, and total environmental effect ranks second highest, behind aluminum. Polystyrene is not biodegradable. It takes several decades to hundreds of years for polystyrene to deteriorate in the environment or in a landfill.

The word phthalocyanine is derived from the Greek terms for naphtha (rock oil) and cyanine (dark blue). Professor Linstead of the Imperial College of Science and Technology first used the term "phthalocyanine" in 1933, to describe a class of organic compounds [23]. Phthalocyanines (Pcs) were discovered accidentally. In 1907, Braun and Tcherniac, at the South Metropolitan Gas Company in London, upon examining the properties of a cyanobenzamide that they made from the reaction of phthalamide and acetic anhydride, found a trace amount of a blue substance after heating o-cyanobenzamide, cooling, dissolving in alcohol, and filtration. This substance undoubtedly was phthalocyanine.

The grace and efficiency of the structures and function detected in nature, has long directed scientists' efforts both on understanding how nature functions through observation and apery and on creating novel, synthetic biomaterials combining the optimized by evolution properties of biomolecular structures with that of synthetic components. Taking into account the multifunctional and, most of the times, chemically fragile nature of biological entities, the major challenge into this direction is a chemical one: the need to proceed through bioorthogonal reactions and under the benign reaction conditions that would preserve and respect the multifunctionality and structure of biologically derived components [41].

This study was undertaken to prepare polystyrene (PS) and asymmetric zinc phthalocyanine, azidation of polystyrene, performing click reaction between azidated

polystyrene and asymmetric zinc phthalocyanine. Polystyrene was synthesized by using ATRP method and azidation was done in a step by using sodium azide. Azidated polystyrene and asymmetric zinc phthalocyanine were bonded with each other via Huisgen 1,3-dipolar cycloaddition.

Prepared polystyrene- asymmetric zinc phthalocyanine composite was characterized by ¹H-NMR, FTIR, and UV-Vis spectroscopy. The results were taken from FTIR spectroscopy showing that preparing of phthalocyanine and polystyrene, azidation of polystyrene, and Huisgen 1,3-dipolar cycloaddition were performed successfully. Also, UV-Vis spectrum demonstrated purity of produced phthalocyanine and polystyrene.

2. THEORETICAL PART

2.1 Composites

“Composite” word was firstly used in a broad sense in 1950, and it has been used domestically from about the 1960s. Composite material is a kind of complex multi-component multi-phase system, and it is hard to be defined definitely [2]. Composite molecules are mixtures of materials differing in composition, where the individual constituents carry on their identities. These separate components act together to give the particular mechanical strength or stiffness to the composite. Composite is a material consisted of two or more different phases and having bulk characteristics importantly different from those of any of the constituents. Matrix phase is the primary phase having a continuous character. Matrix is usually more ductile and less hard phase. It holds the dispersed phase and shares a load with it. Dispersed (reinforcing) phase is embedded in the matrix in a discontinuous form. This secondary phase is called the dispersed phase. Dispersed phase is generally stronger than the matrix, consequently, it is sometimes called reinforcing phase [1].

2.1.1 Classification of composites

On the basis of matrix phase, composite materials can be divided into metal matrix composites (MMCs), and polymer matrix composites (PMCs), ceramic matrix composites (CMCs). The separations according to types of reinforcement are particulate composites (composed of particles), laminate composites (composed of laminates), fibrous composites (composed of fibers). Fibrous composites can be further subdivided on the basis of natural or synthetic fibers. Natural surrounding composites are mentioned to as natural composites. They can be subdivided on the basis of matrix, that is, nonbiodegradable matrix and biodegradable matrix. Bio-based composites made from nature or biofiber and biodegradable polymers are mentioned to as green composites. These can be promote subdivided as hybrid composites and textile composites. Hybrid composites comprise of a union of two or more types of fibers (Figure 2.1) [1].

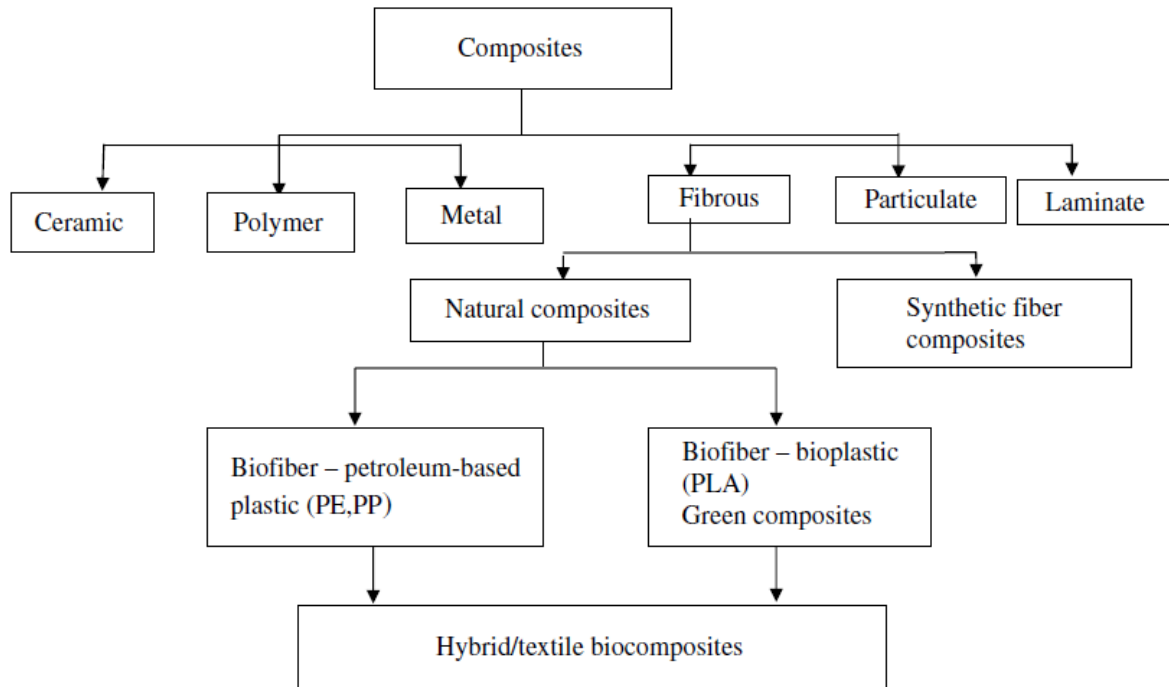


Figure 2.1: Classification of composites.

2.1.2 Features of composites

Composite materials are designed and prepared for particular applications with desired properties such as lightweight and high performance. Composite materials offer some advantages over engineering materials as discussed below.

- Composite materials provide abilities for part integration.
- Composite structures provide in-service monitoring or online process monitoring with the help of embedded sensors [5].
- Composite materials offer a high stiffness [4].
- Composites have a high strength.
- The fatigue strength is much higher for composite materials.

- Composite materials can be designed for superior corrosion resistance to particular hostile environments.
- They provide increased amount of design flexibility.
- Composite materials provide good impact properties (Figure 2.2).
- Noise and vibration properties are better for composites than metals [5].

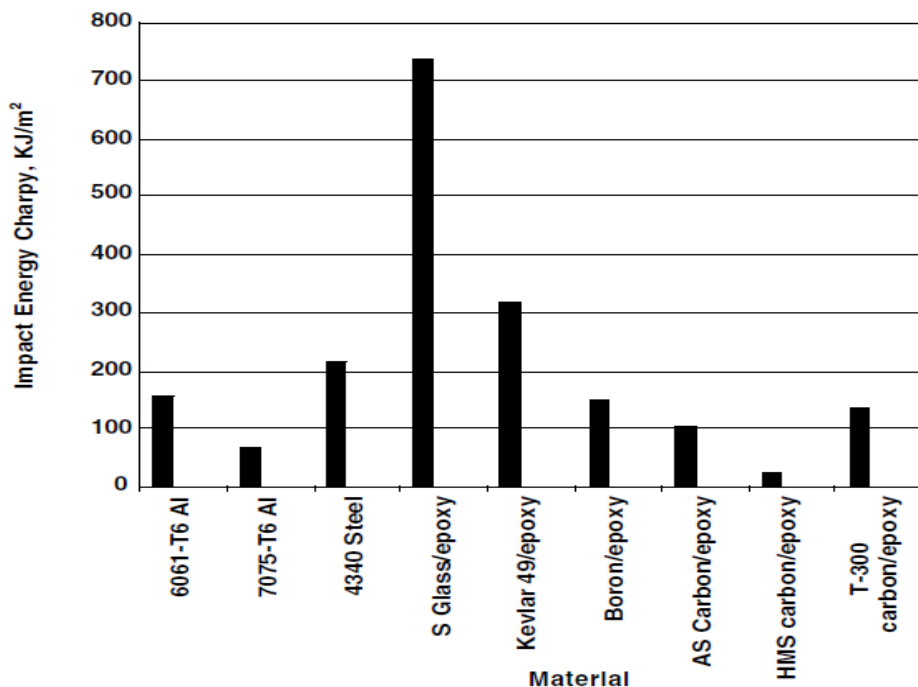


Figure 2.2: Impact properties of some kind of composites.

2.1.3 Naming of composites

Composite materials can be called by reinforcement and the matrix material. According to the type of matrix materials, there are metal matrix composite material, aluminum matrix composites, polymer matrix composite material, and epoxy resin matrix composite material. Polymer matrix composites are generally named by the type of their reinforced fiber, such as glass fiber composite material (commonly known as glass fiber reinforced plastics), carbon fiber composites, and hybrid fiber composites. More particularly, the name of the reinforcement is put the front of the

name of the matrix material, along with “composite material” on the back. For example, composite material with E-GF and epoxy resin can be named “E-glass fiber epoxy composite material”. For convenient writing, it can also be written as abbreviation of the reinforcement and matrix materials, with a “/” separating them, along with “composite material” on the back, and so the former “E-glass fiber epoxy composite material” is briefly called “E-GF/epoxy composite material” (traditionally called epoxy GFRP). Composite material of carbon fiber and metal matrix is called “metal matrix composites”, and can also be written as “carbon/metal composite material”. Carbon fiber reinforced carbon matrix composite material is called “carbon/carbon composite” or “C/C composite material”. The above-mentioned nomenclature can also be addressed using commodities trademark directly, for example, T300/648, M40/5208, S-GF/5245C, Kevlar49/QY8911, HT3/5405 and so on [2].

2.1.4 Polymer composites

Materials have been combined with each other for producing new materials with desired properties. A composite material is created by combining two or more materials to provide discernible improvement of properties. In a composite, substantial volume fraction of high strength, high stiffness reinforcing elements are embedded in a matrix phase.

Matrix materials are generally polymers, ceramics or metals. The polymer matrices also called resins are by far the most common due to the versatility of their properties such as light weight, easy processing and corrosion resistance [13].

2.2 General Properties and Applications of Polystyrene

Polystyrenes have been produced commercially by polymerization in an extruder [14]. Polystyrene is made from petroleum, a non-sustainable, non-renewable, heavily polluting and fast-disappearing commodity. The environmental impacts of polystyrene production in the categories of energy consumption, greenhouse gas effect and total environmental effect ranks second highest, behind aluminum.

Polystyrene is not biodegradable. It takes several decades to hundreds of years for polystyrene to deteriorate in the environment or in a landfill. Polystyrene takes up

more spaces in landfills than paper, and will eventually re-enter the environment when water or mechanical forces breach landfills. Polystyrene contains the toxic substances styrene and benzene, suspected carcinogens and neurotoxins that are hazardous to humans. Polystyrene foam, commonly known by the name "Styrofoam" is formed by adding a blowing agent to polystyrene, a petroleum-based plastic material. Polystyrene foam is light-weight (about 95% air), with good insulation properties, and is used in all types of products from cups that keep beverages hot or cold to materials that protect items during shipping. There are two widely used types of expanded polystyrene: EPS (expanded polystyrene) and XPS (extruded polystyrene). They are made from the same plastic (polystyrene), but the manufacturing processes are different. EPS begins as small plastic "beads" that are expanded and fused together, forming products such as protective packaging for electrical appliances. XPS begins as a continuous mass of molten material, which is then shaped into products such as take-out lunch boxes and trays for fresh cuts of meat at the supermarket. XPS has little recycling ability since it is often contaminated by food, and grease that render it non-recyclable [15].

Styrene, a component of polystyrene, is a known hazardous substance that medical evidence and the US Food and Drug Administration suggests leaches from polystyrene containers into food and drink. Polystyrene food containers leach Styrene when they come into contact with warm food or drink, alcohol, oils and acidic foods causing human contamination and posing a direct health risk to people. It is for this reason that it is not recommended that plastic take-out containers ever be heated in a microwave. Styrene is a suspected carcinogen and neurotoxin which potentially threatens human health. It has been detected in the fat tissue of every man, woman and child tested by the EPA in a 1986 study. Styrene has been found in human tissue samples and human nursing milk samples tested [15].

CD covers and plastic drinking cups are made out of the polymer polystyrene. This polymer is known to be a clear brittle plastic that is synthesized by a free radical polymerization. An initiator, such as benzoyl peroxide, is used to initiate the free radical polymerization of styrene. Once the radical initiator initiates the polymerization of styrene, propagation occurs which "builds up" the polymer chain. Once the polymer chain has "grown" and at a desirable length or molecular weight,

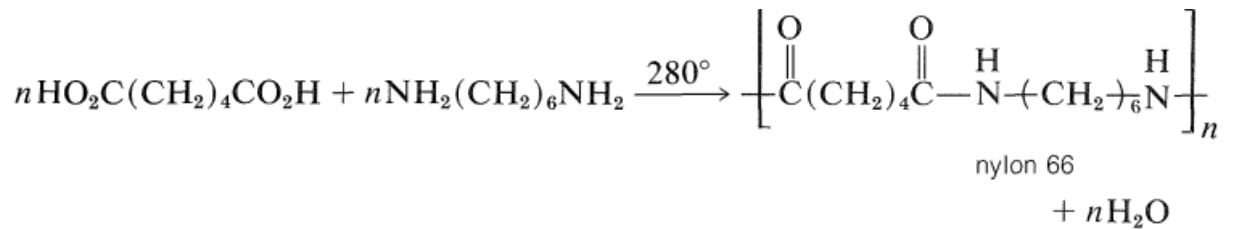


Figure 2.4: Nylon 66 formation via condensation polymerization.

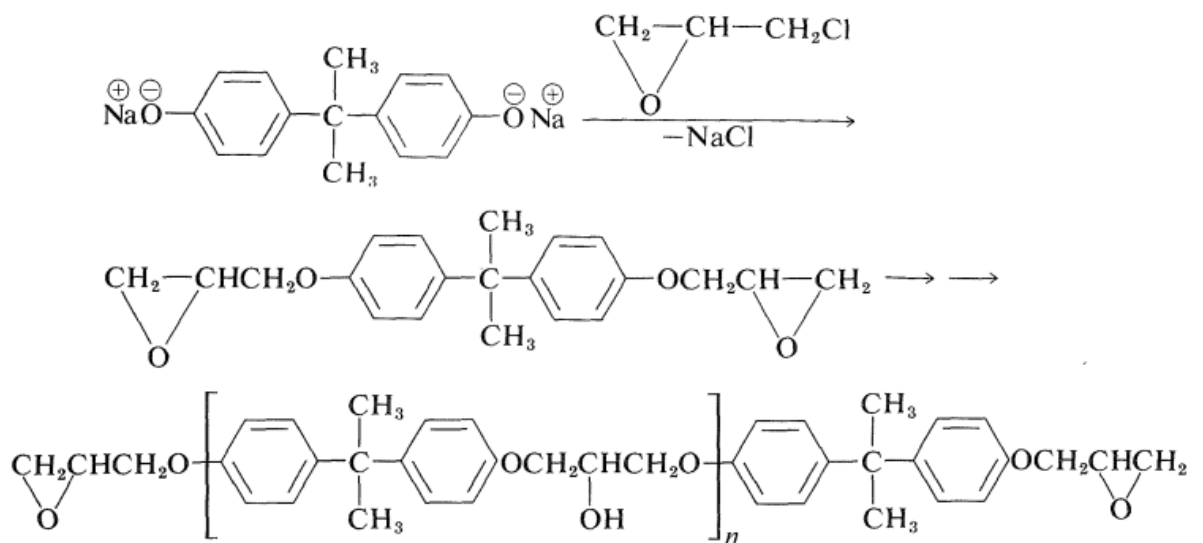


Figure 2.5: Epoxy resin synthesis via condensation polymerization.

2.3.2 Addition polymerization

Addition polymerization have two main parts which are called as radical polymerization and ionic polymerization. Also, ionic polymerization is divided to cationic polymerization and anionic polymerization.

2.3.2.1 Anionic and cationic polymerization

Polystyrene can be synthesized by also anionic and cationic polymerization, but radical polymerization was used for producing polystyrene in this work.

Stages of anionic polymerization can be seen in Figure 2.6.

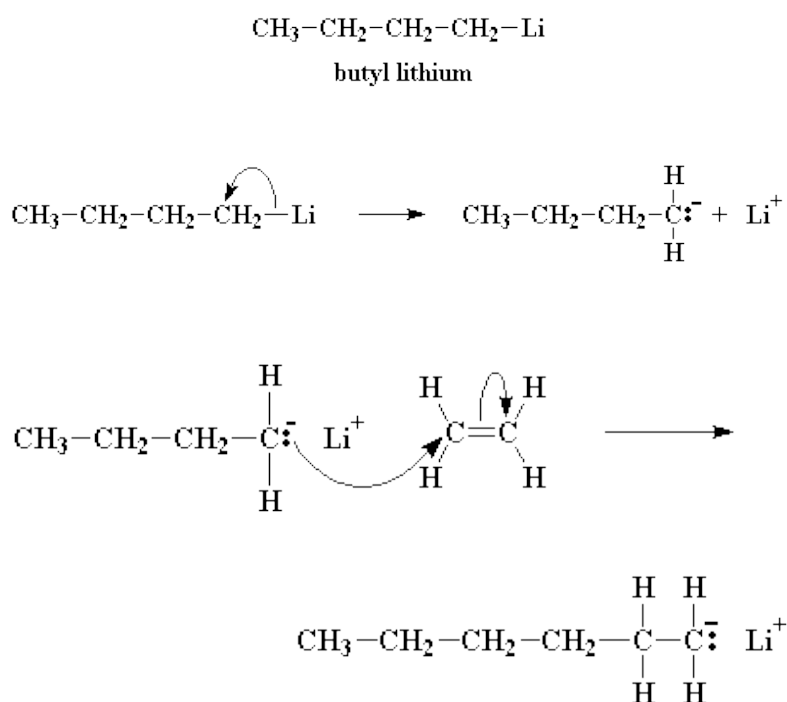


Figure 2.6: Stages of anionic polymerization.

If moisture and oxygen are rigorously excluded, the anionic groups are stable indefinitely, and if more monomer is added, polymerization will continue. Hence the name "living polymer," in contrast to a radical-induced polymerization, which only can be restarted with fresh monomer and fresh initiator, and even then not by growth on the ends of the existing chains [70].

Stages of cationic polymerization can be showed in the following figure (Figure 2.7).

Termination generally occurs via unimolecular rearrangement with the counterion. In this process, an anionic fragment of the counterion combines with the propagating chain end. This not only inactivates the growing chain, but it also terminates the kinetic chain by reducing the concentration of the initiator-coinitiator complex [20].

Initiation and propagation:

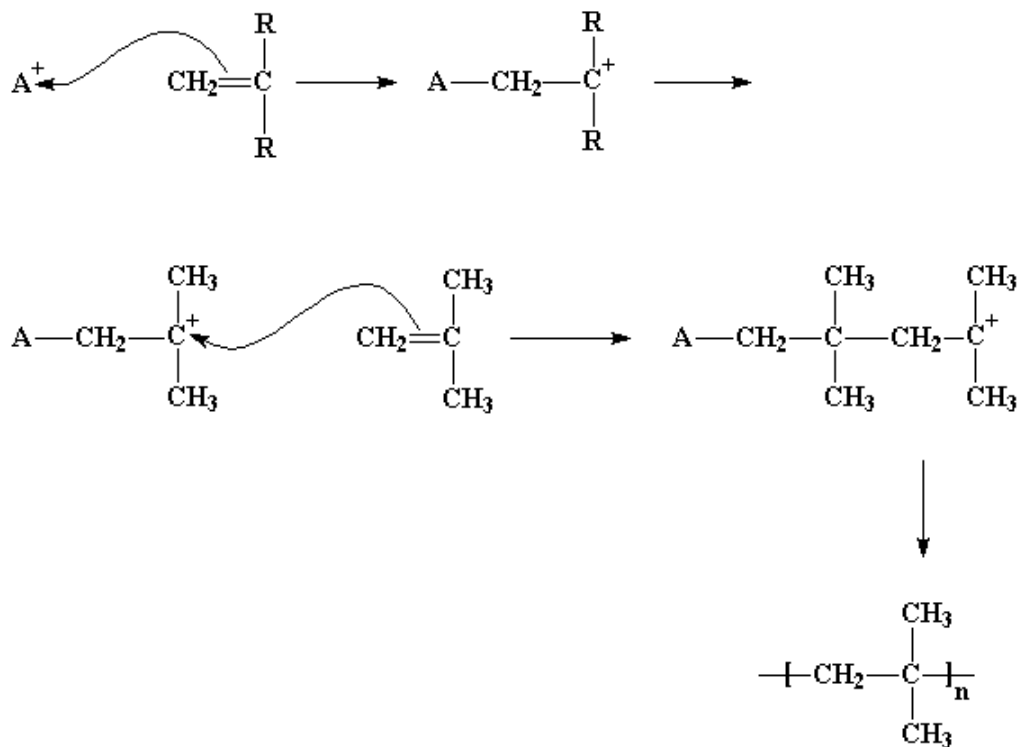


Figure 2.7: Stages of cationic polymerization.

2.3.2.2 Radicalic polymerization

Radicalic polymerization needs an initiator and proceeds by adding one repeating unit at a time [18].

Initiation: Radical polymerizations are different because an initiation step is required to start the polymer chain growth [19]. Initiation can be carried out by adding a small amount of a chemical that decomposes smoothly to form free radicals. Initiators can be monofunctional and make the same free radical. In contrast, initiators can be multifunctional and make different radicals. Multifunctional initiators incorporate more than one labile group.

Propagation: The propagation progression occurs between a monomer and a radical.

An example for a propagation reaction can be shown in Figure 2.8,

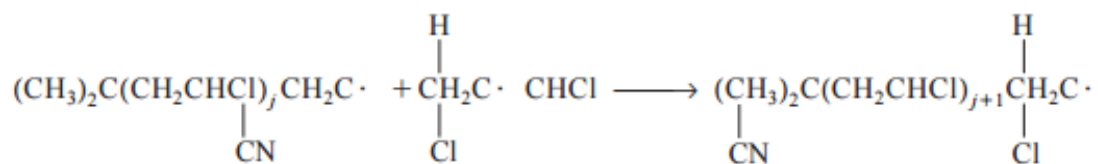


Figure 2.8: Example of a propagation reaction.

The particular reaction rates (k_p) are assumed to be indistinguishable for the addition of each monomer to the growing chain. This is generally a superb assumption once two or more monomers have been added to R_1 and for low conversions of monomer. The particular reaction rate k_i is frequently taken to be equal to k_p .

Termination: For termination, dead polymers can be obtained by two mechanisms.

1. Addition (coupling) of two growing polymers,
2. Termination by disproportionation.

An example can be seen in Figure 2.9.

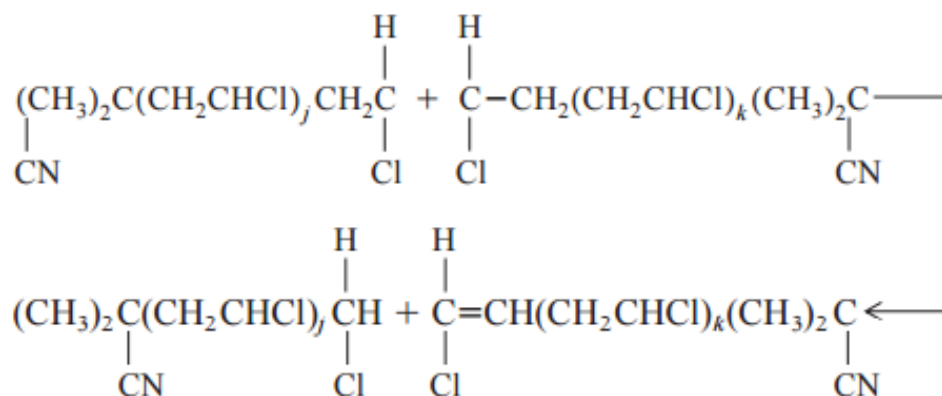


Figure 2.9: An example termination scheme.

2.4 Phthalocyanines

2.4.1 General information

Phthalocyanines (Pcs) were discovered accidentally. In 1907, Braun and Tcherniac, at the South Metropolitan Gas Company in London, upon examining the properties of a cyanobenzamide that they made from the reaction of phthalamide and acetic

anhydride, found a trace amount of a blue substance after heating o-cyanobenzamide, cooling, dissolving in alcohol, and filtration. This substance undoubtedly was phthalocyanine. The word phthalocyanine is derived from the Greek terms for naphtha (rock oil) and cyanine (dark blue). Professor Linstead of the Imperial College of Science and Technology first used the term "phthalocyanine" in 1933, to describe a class of organic compounds [23].

The main problems in the phthalocyanine chemistry are their insolubility in most of the solvents and aggregation tendency in solutions because of the molecular interactions between the macrocyclic rings. These problems limit their usage or causes diminishing of the properties in application steps. While the substitutions of some bulky apolar substituents such as long alkyl, alkyloxy or alkylsulfonyl groups improve their solvation in organic solvents, polar substituents such as sulfo, carboxylic acid or quaternized ammonium groups provide their solubility in aqueous media [28]. Phthalocyanines are divided to two main categories which are metal-free phthalocyanine and metallophthalocyanine. An example about structure of typical phthalocyanine compounds can be seen in Figure 2.10.

Thus, phthalocyanines are thermally and chemically stable: they can be heated up to 500 °C under high vacuum without decomposition and remain unaltered when exposed to the action of non-oxidative acids or bases. Phthalocyanines are planar macrocycles related to porphyrins constituted by four isoindole units presenting an 18 π -electron aromatic cloud delocalized over an arrangement of alternated carbon and nitrogen atoms. A great number of unique properties arise from this electronic delocalization, which makes these compounds applicable in different fields of materials science [22].

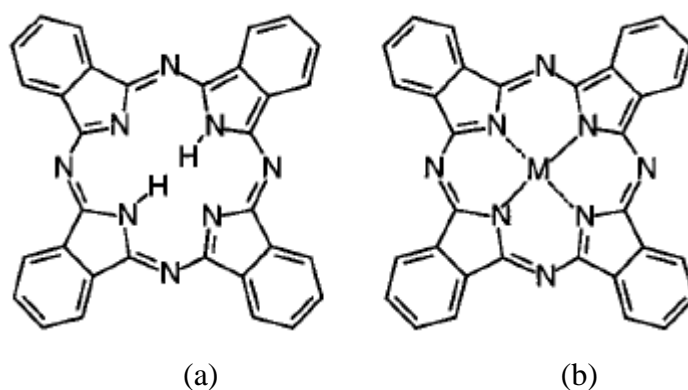


Figure 2.10: (a) Metal-free phthalocyanine, (b) metallophthalocyanine.


Phthalocyanines have been used in a wide range of different applications: chemical sensors [29], photodynamic therapy [30], electrochromic materials [31], liquid crystal displays [32], organic light emitting diodes (OLEDs) [33], nonlinear optical properties [34], organic solar cells [35], chemical catalysts [36], photodynamic activity [37], electronic and optoelectronic properties [38], and adsorption behavior [39].

2.4.2 Synthetic methods of phthalocyanines


In the synthesis of phthalocyanines, as starting materials, phthalic acid (1), phthalonitrile (2), phthalic anhydride (3), phthalimide (4), diiminoisoindoline (5), o-cyanobenzamide (6) are used.

2.4.2.1 Metal-free phthalocyanines (H_2Pc)


It is possible to synthesize non-metallophthalocyanines (H_2Pc) by the technique of cyclotetramerization of lots of phthalonitriles. Some precursors can be seen in Figure 2.11. Synthesis of metal-free phthalocyanines can be seen in Figure 2.12.




Phthalic acid (1)




Phthalonitrile (2)




Phthalic anhydride (3)



Phthalimide (4)



Diiminoisoindoline (5)



o-cyanobenzamide (6)

Figure 2.11: Precursors that lead to phthalocyanine formation.

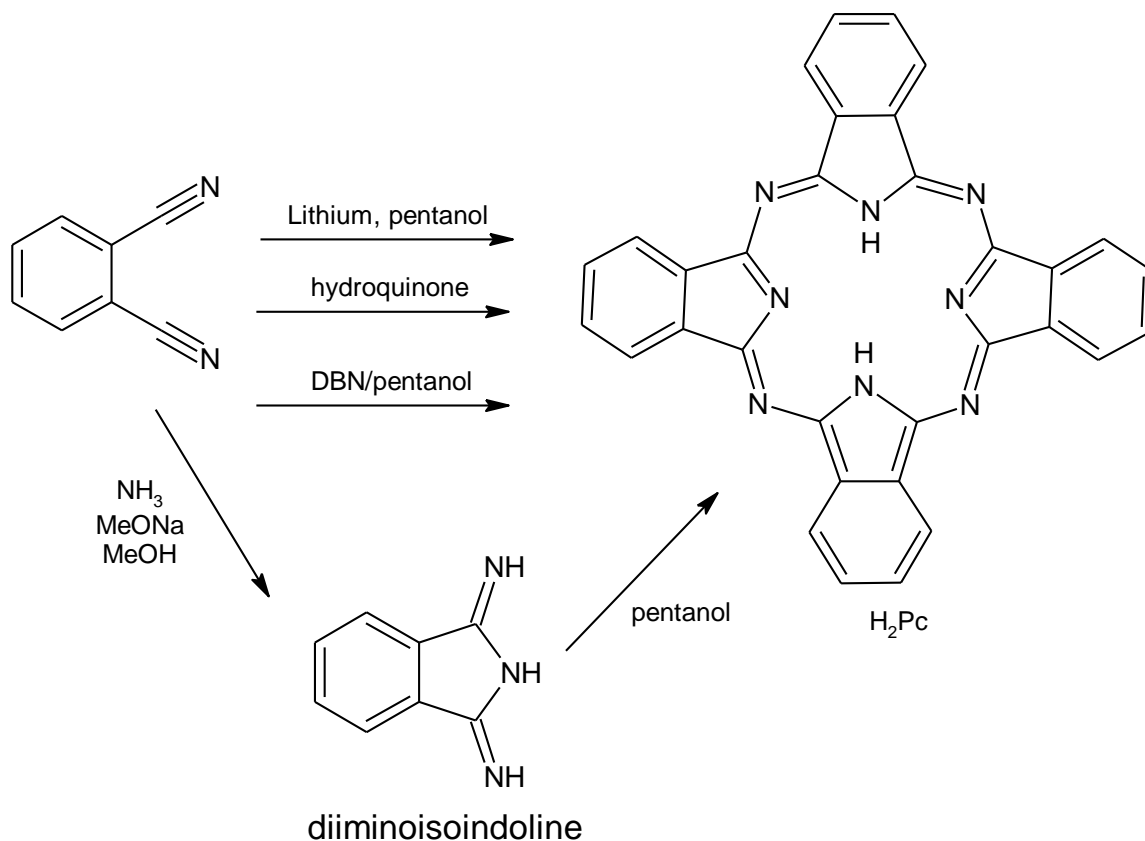


Figure 2.12: Scheme for the synthesis of non-metallophthalocyanines and starting materials.

- Reacting lithium in boiling pentanol under reflux and hydrolysis,
- Melting with hydroquinone,
- DBU, boiling in pentanol,
- Under reflux, boiling with ammonia, methanol, sodium methoxide,
- Under reflux, boiling with an alcohol having high boiling point,

2.4.2.2 Metallophthalocyanines (MPc)

In the synthesis of metallophthalocyanines, like non-metallophthalocyanines, there are lots of possible synthetic methods. The common point of all kinds of synthetic methods is that these methods include many steps and these occur at high temperatures (Figure 2.13).

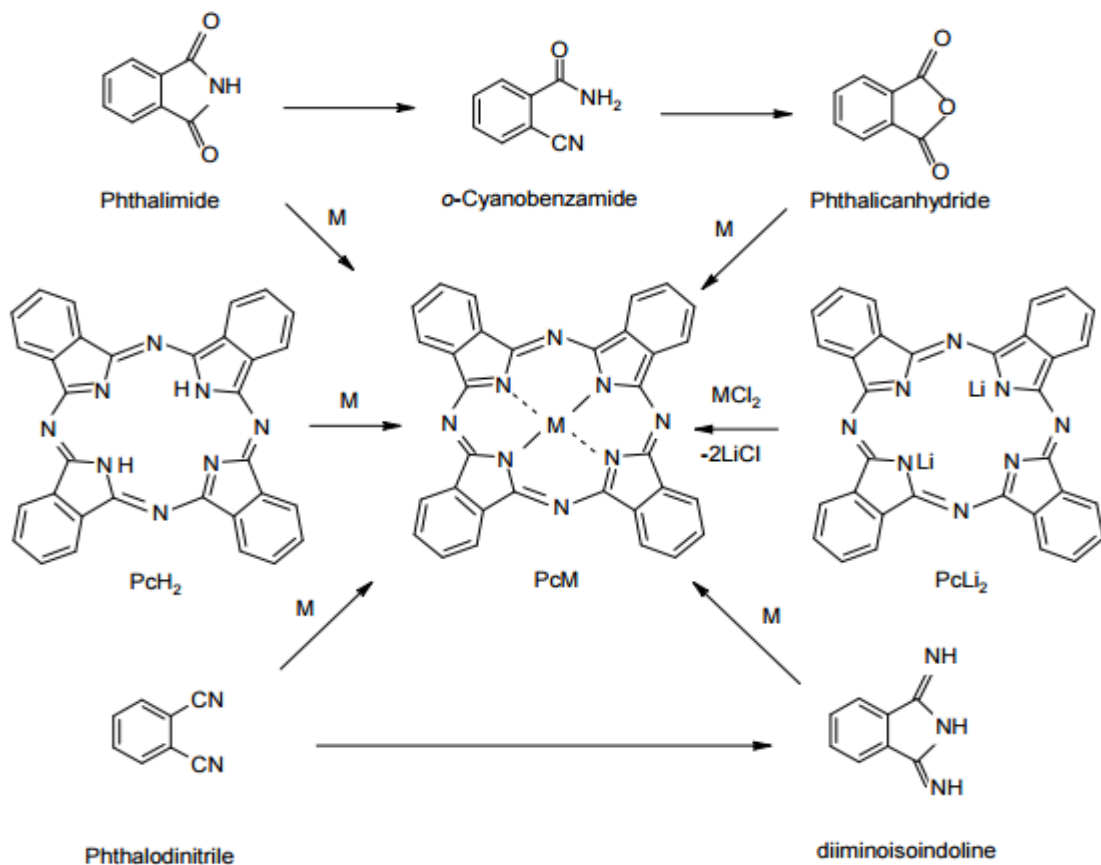


Figure 2.13: Scheme for the synthesis of metallophthalocyanines and starting materials.

Boiling phthalimide or phthalic anhydride structures in solvents having high boiling points and urea and metal salts with the catalysis of molybdate.

- Boiling of diiminoisoindoline or phthalonitrile in DMF, pentanol, hexanol with metal salts
- Boiling Li₂Pc in ethanol
- Adding metal to non-metallophthalocyanines

2.4.2.3 Synthesis of substituted phthalocyanines

Substituted phthalocyanines can be obtained with phthalonitrile derivative. Substituted phthalocyanines are prepared by substitution of the phthalocyanine ring. Consequently, tetra or octa substituents can be obtained.

2.4.2.4 Tetrasubstituted phthalocyanines

Phthalocyanines that have most researches on them are tetra-substituted complexes. The reason of this case is their high solubilities in many organic solvents because of their tetrasubstituent contents. These complexes are used in physical, chemical, biological and electrochemical areas.

Tetra-substituted phthalocyanines are divided into peripheral and non-peripheral, according to the position of the substituents of the macrocyclic structures.

In the synthesis of tetra-substituted phthalocyanine in the peripheral location, most used method is the following three steps synthesis of 4-nitrophthalonitrile compound that was prepared from phthalimide and that the base-catalyzed nucleophilic substitution reaction of the compound is modified [61]. Synthesis of 4-nitrophthalonitrile can be seen in Figure 2.14. 4-nitrophthalonitrile can react with various nucleophiles in a strong polar solvent such as DMSO or DMF. Acidic protons in nucleophiles are cut off with a base such as Na_2CO_3 or K_2CO_3 . Nucleophiles attack to the ring and nitro group is removed in the form of sodium nitrite [62,63].

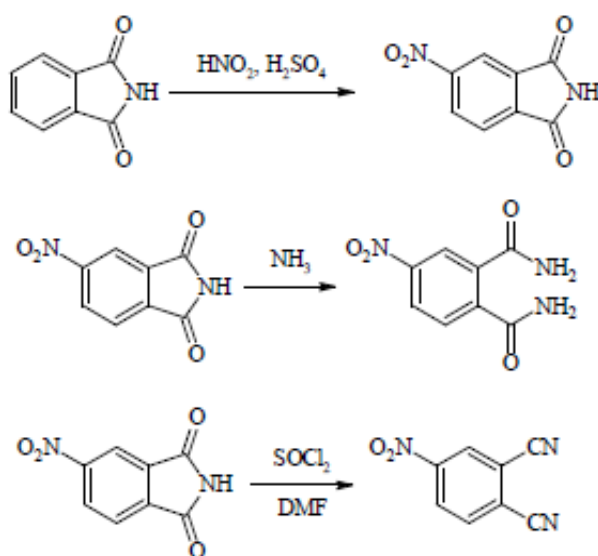


Figure 2.14: 4-Nitrophthalonitrile synthesis.

In the synthesis tetra-substituted phthalocyanines, as a result cyclotetramerization of a monosubstituted starting material, four isomers mixtures in symmetry of D_{2h} ,

$C_{4h}C_{2v}$ and C_s are obtained statistically in ratio of 4: 2: 1: 1 conformational isomers (Figure 2.15).

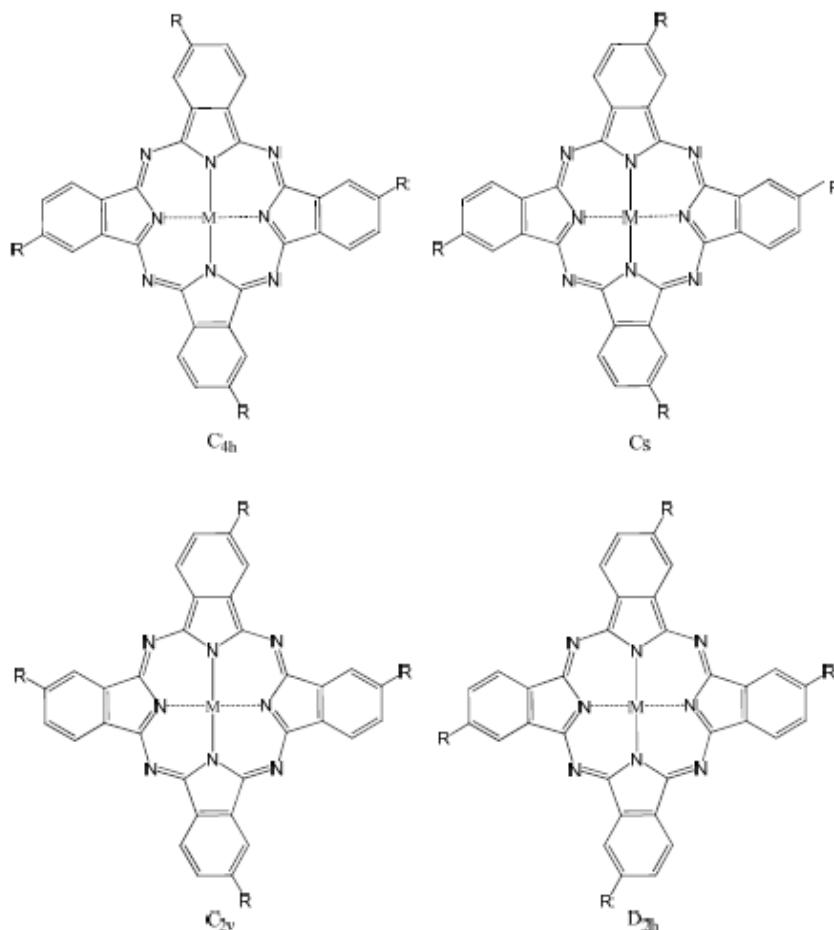


Figure 2.15: Structural isomers of tetra-substituted phthalocyanines.

2.4.2.5 Octasubstituted phthalocyanines

By using 4,5-disubstituted phthalonitrile, mostly more larger than pentyl ($-C_5H_{11}$), peripheral octa substituted phthalocyanines with one isomer can be synthesized. The resulting structures are structures that show liquid crystal property and, soluble in organic solvents. Phthalocyanines containing eight substituents in peripheral positions are obtained with two methods. In the first method, the *o*-xylene compound is brominated to yield 4,5-dibromo-*o*-xylene are obtained, with the result that of bromination with *N*-bromosuccinimide is synthesized 1,2-bromomethyl-4,5-dibromobenzene. Primary alkyl groups are substituted reacting with suitable nucleophiles, and then bromo groups bonded to benzene rings are converted to nitro groups by Rosenmund-Von Braun synthesis [64].

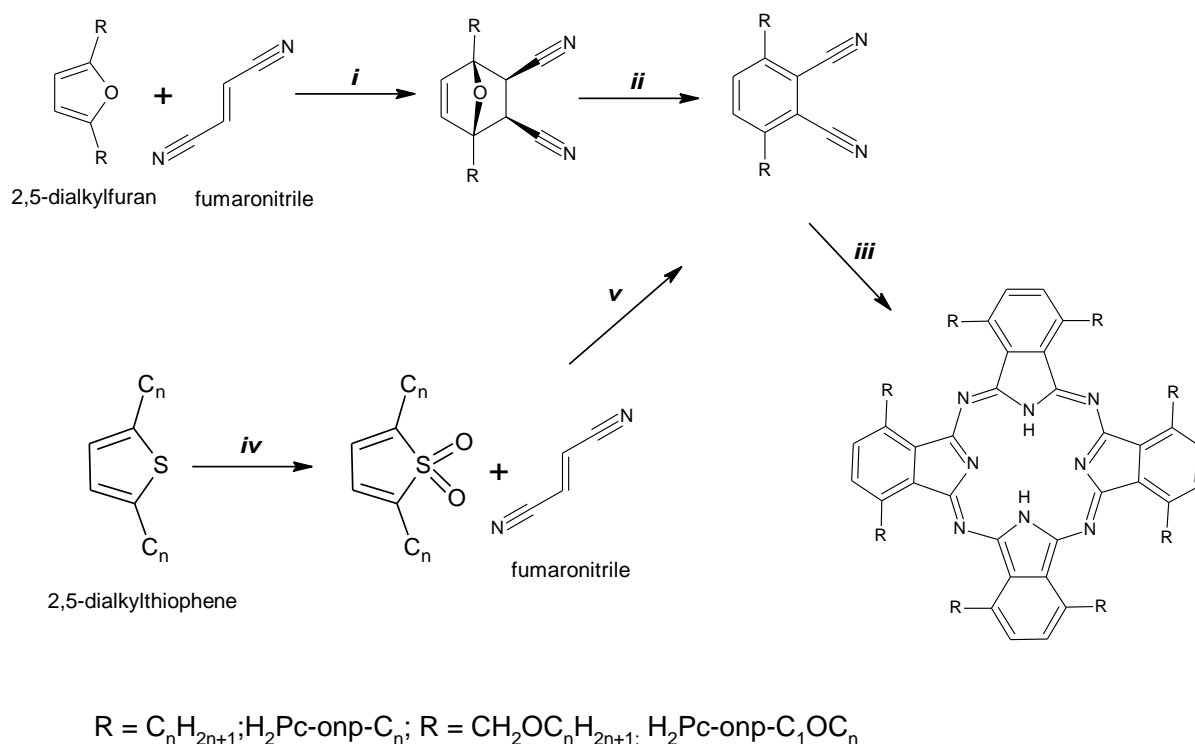


Figure 2.16: Non-peripherally Octasubstituted Phthalocyanines' Synthesis ($H_2Pc-omp-C_n$).

For the synthesis of non-peripheral octa-alkyl-substituted phthalocyanines that have liquid crystallinity ($MPC-omp-C_n$), Cook and his group developed two new methods. 3,6-dialkyl phthalonitrile required for the synthesis are synthesized from the appropriate 2,5-dialkyl furan or thiophene. Appropriate dinitrile derivatives are synthesized as the result of Diels Alder ring addition reaction between fumaronitrile and five heteroring (Figure 2.16).

2.4.2.6 New methods for synthesis of phthalocyanines

Studies in order to improve the synthesis of phthalocyanine compounds are increasing recently. By using these improved methods, it is intended to create more economical, quicker, easier, and more efficient reactions. At the first of these methods is the synthesis of phthalocyanine using microwave energy.

2.4.3 Purification of phthalocyanines

Phthalocyanines (Pcs) have been synthesized with nearly all metals of the periodic table. The metal-free phthalocyanines (H_2Pc) are normally formed as a one-pot multiple-step reaction from derivatives of phthalic acid, phthalic anhydride,

phthalimide, or phthalonitrile usually by fusion or in a high boiling solvent such α -chloronaphthalene [53]. When the reaction is carried out in presence of metal salt, the metal phthalocyanines PcM are formed. Insoluble (unsubstituted) phthalocyanines can be mainly purified by sublimation at high temperature at 450°C under vacuum, by dissolution in concentrated acids followed by precipitation in water, or by extensive extraction with organic solvents. However, soluble (substituted) phthalocyanines can be purified by recrystallization from organic solvents or by chromatography on alumina or silica gel. Wagner and co-workers reported the technical details of a simple train sublimation (carrier gas) system for purification of MPcs and studied the effect of sublimation on the physical properties of MPcs [54].

The other techniques for purification of phthalocyanines are;

- GPC (Gel Permeation Chromatography)
- HPLC (High Performance Liquid Chromatography)
- Column Chromatography using aluminium oxide and silica gel
- Sublimation
- For phthalocyanines with low solubility, purification by washing in various solvents; for phthalocyanines with high solubility, purification by washing in different organic solvents are applied.

2.4.4 Characterization of phthalocyanines

Elemental analysis used in the characterization of organic compounds, and FTIR and UV-Vis are also used in the characterization of phthalocyanine. In particular, the position of the Q-band in the visible range is influenced by the substituents and the central metal atom. Therefore, these techniques play an important role in the characterization of phthalocyanines.

NMR is a useful technique for soluble phthalocyanine derivatives. However, due to the orientations of phthalocyanine compounds to strong aggregation in solution and causing enlargement prevent a good spectrum from NMR.

Recent developments related to the mass spectrometer facilitate the characterization of phthalocyanines. In particular, fast atom bombardment (FAB) and matrix-assisted

laser desorption ionization (MALDI) have begun to constitute an important part in the characterization of high molecular mass phthalocyanines.

2.4.4.1 FTIR spectra of phthalocyanines

The main difference between metal-free phthalocyanines with metallophthalocyanines is that the N-H stretching vibrational band is seen near 3298 cm^{-1} .

In both metal-free phthalocyanines and metallophthalocyanines, the characteristic band due to C-H stretching of the aromatic ring is around $3000\text{-}3050\text{ cm}^{-1}$, C-C stretching vibration band is around $1450\text{-}1600\text{ cm}^{-1}$ and outside the plane of C-H bending band is observed between $750\text{-}800\text{ cm}^{-1}$.

2.4.4.2 $^1\text{H-NMR}$ spectra of phthalocyanines

In unsubstituted phthalocyanine, protons at the peripheral and non-peripheral positions give a signal of equal intensity. Octasubstituted phthalocyanines are formed from a single isomer, tetrasubstituted phthalocyanines are located as a mixture of isomers. Therefore, tetra-substituted phthalocyanines' spectrum signals stand out wider than the octa-substituted phthalocyanines. Because of substituents added to the ring and ligands in the axial position, $^1\text{H-NMR}$ spectrum of metallophthalocyanines becomes more complicated. Magnetic field signals can shift to low field or high field according to the nature and position of substituents. Generally, the electron donating groups when sliding signals to lower field, electron withdrawing groups shift to strong field. Also, phthalocyanines having electron donating non-peripheral substituents generally shift to lower fields comparing with their derivatives peripherally substituted comprising the same groups [57].

The metal-free phthalocyanine in the $^1\text{H-NMR}$ spectrum, as a proof of the aromatic structure of the phthalocyanine ring, because of diamagnetic anisotropy, the chemical shift of the NH proton in the ring stands out as the wide and broad peak in strong fields [58].

2.4.4.3 UV-Vis spectra of phthalocyanines

Chemical and electronic properties of phthalocyanine are coming from the 18 π -electron system. Generally, UV-Vis spectrum of phthalocyanines signal at 650-720 nm Q band; B, less intensity between 300-400 nm (SORET) called as the characteristic band peaks [59]. Severe Q band ground state (HOMO) and the excited state (LUMO) is due to the π - π^* transitions between energy levels. B (SORET), the band between the orbital a_2 or b_2 and orbital e_g , is caused by the transitions. In metal-free phthalocyanine spectra, there is a splitting in the Q band.

2.4.5 Recent developments on phthalocyanines

In chemical synthesis, the term “selectivity” refers to the discrimination displayed by a reagent, when it reacts with two different reactants or functional groups. Highly selective reactions proceed with minimal reliance on protecting groups and contribute to both atom and step economy. Biological and synthetic systems operate somewhat differently when it comes to impose selectivity in chemical transformations. In nature, the biological catalysts, more particularly porphyrins such as cytochromes, are responsible for catalyzing oxidation-reduction processes and electron transfer reactions on which all forms of life are dependent. These enzymes are tailored towards a specific substrate and work with high levels of stereo-, regio-, and chemo-selectivity. However, high price, stability, and bulk availability issues limit their practical utility [55].

Phthalocyanines (Pcs) have structural similarity with porphyrins and are very stable π -conjugated macrocyclic compounds that can form complexes with almost all metals and offer a high architectural flexibility in structure. Due to their greater stability than porphyrins, metal phthalocyanines (MPcs) attract great attention for their applications as catalysts for selective organic transformations including oxidation-reduction processes and electron transfer reactions [56].

Although several catalyzed synthetic methodologies are being developed, controlling reaction selectivity still stands as one of the major challenges in organic synthesis. In this regard, these recent advances clearly evidenced the promising future of MPcs in catalyzing the challenging organic transformations in which high selectivity is required. Currently, visible light absorbing photocatalysts are emerging as powerful

tools in synthetic organic chemistry in which their electron/energy transfer potential is being utilized for sensitization of organic molecules. In this regard, MPC photosensitizers, which strongly absorb in the visible region and have long triplet lifetime, have great potential to be developed for efficient photocatalytic reactions [60].

2.5 Click Chemistry

The grace and efficiency of the structures and function detected in nature, has long directed scientists' efforts both on understanding how nature functions through observation and apery and on creating novel, synthetic biomaterials combining the optimized by evolution properties of biomolecular structures with that of synthetic components. Taking into account the multifunctional and, most of the times, chemically fragile nature of biological entities, the major challenge into this direction is a chemical one: the need to proceed through bioorthogonal reactions and under the benign reaction conditions that would preserve and respect the multifunctionality and structure of biologically derived components [41].

Different click reactions applied in different field of science and yielded extremely reliable process for the synthesis of building block and compound libraries. The various reactions is classified below [44]. Some examples about click reactions can be seen in Figure 2.17.

1. Cycloaddition reaction [45] and Diels Alder reaction [46].
2. Nucleophilic substitution reaction particularly rings opening reaction of strained heterocyclic electrophiles [47].
3. Carbonyl chemistry of the non-aldol type.
4. Addition to carbon-carbon multiple bonds specifically oxidation reaction, epoxidation [48]; hydroxylation; dihydroxylation [49]; aziridination [50].
5. Thiol-ene click reactions [51].
6. Azide-Phosphine reaction [52].

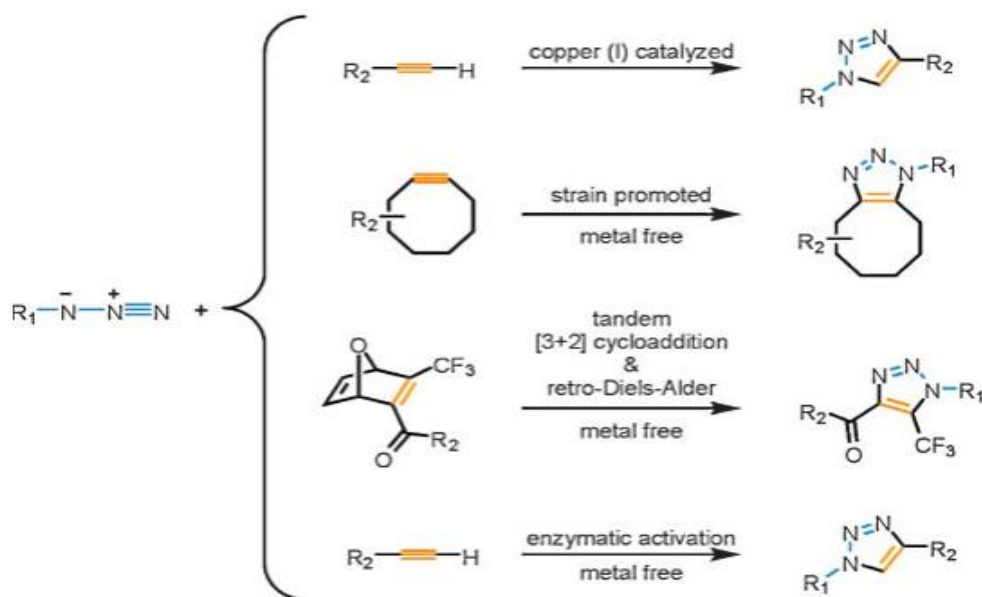


Figure 2.17: General scheme some kind of “click” chemistry cycloaddition reactions.

Following nature’s lead, we strive to produce substances by joining small units together with heteroatom links. The aim is to develop an expanding set of powerful, selective, and modular block that work dependably in both small and large scale applications. We have called the foundation of this approach click chemistry, and have determined a set of rigorous criteria that a process must meet to be useful in this context. The reaction must be modular, wide in scope, give very high yields, produce only harmless byproducts that can be removed by nonchromatographic methods, and be stereospecific. The needed process properties include simple reaction conditions (ideally, the process should be insensitive to oxygen and water), readily available starting materials and reagents, the use of no solvent or a solvent that is benign (such as water) or easily removed, and simple product isolation. Purification required must be by nonchromatographic methods, such as crystallization or distillation, and the product must be stable under physiological conditions [42].

Of the reactions that have been identified as fulfilling the rigorous needs of “click” chemistry, the Huisgen 1,3-dipolar cycloaddition of alkynes (1) and azides (2) to create triazoles (3) was, from the beginning, considered to be the ideal “click” reaction (Figure 2.18). Azide and alkyne functionalities are readily introduced, and

have a high forbearance for the presence of other functional groups as well as high kinetic stability. The cycloaddition in its original form as defined by Huisgen generally needs raised temperatures and generates a mixture of the 1,4 and 1,5-disubstituted regioisomers (3) and (4) [43].

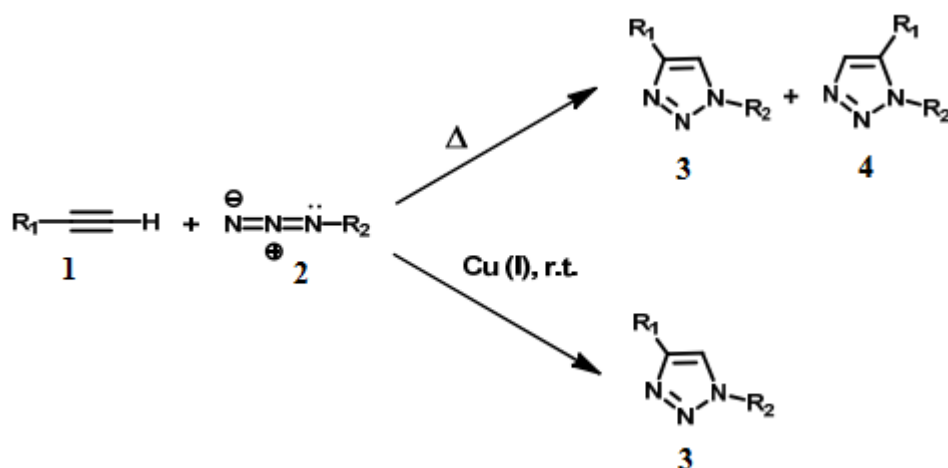


Figure 2.18: Huisgen 1,3-dipolar cycloaddition.

2.6 Previous Studies of Phthalocyanine-Polymer Composites

Ohkita and co-workers (2013) investigated the light-harvesting efficiency of P3HT:PCBM solar cells can be improved by incorporating near-IR dye molecules such as silicon phthalocyanine derivatives with bulky axial groups (SiPc). In order to study the size effect of the axial groups on the dye sensitization in P3HT:PCBM solar cells, they synthesized five SiPc derivatives with different axial groups: SiPc[OSi(C_nH_{2n+1})₃]₂ (SiPc_n, n = 2, 3, 4, 6) and SiPc[OSi(iBu)₂C₁₈H₃₇]₂ (SiPcB₁₈). The power conversion efficiency (PCE) increased in the order of n = 2–4, reached the maximum at around n = 4 and 6, and then decreased for SiPcB₁₈ with the longest axial groups [65]. As a result, the PCE was improved to 4.2%, which is larger by 10% than that of P3HT:PCBM control cells without dye molecules. They therefore conclude that the butyl or hexyl chain in the axial ligand is the most appropriate for the dye sensitization in P3HT:PCBM solar cells (Figure 2.19).

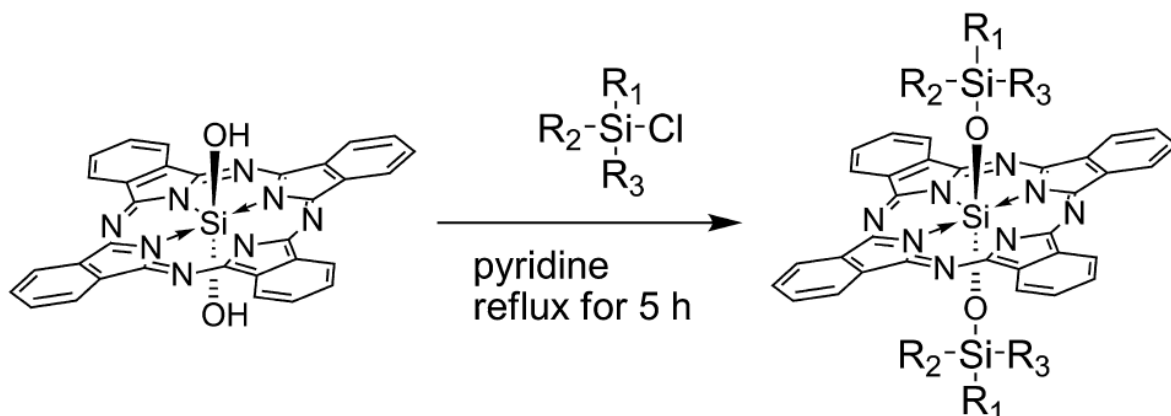


Figure 2.19: Synthetic scheme of $\text{SiPc}[\text{OSi}(\text{C}_n\text{H}_{2n+1})_3]_2$ (SiPc_n , $n = 2, 3, 4, 6$) and $\text{SiPc}[\text{OSi}(\text{iBu})_2\text{C}_{18}\text{H}_{37}]_2$ (SiPcB_{18}).

Mert and co-workers (2014) synthesized unsymmetrically terminal alkynyl substituted zinc (II) phthalocyanine (ZnPc) through an efficient statistical condensation reaction with the unprotected phthalonitrile (2) is reported for the first time [66]. Isolated ZnPc bearing one terminal alkynyl group is a good precursor for Cu(I)-catalyzed azidealkyne 1,3-dipolar cycloaddition (CuAAC) reaction which is classified under the term “click chemistry”. This was approved by the successful click reaction between ZnPc and azide end-functional well-defined polymers obtained by atom transfer radical polymerization (ATRP), and consecutive azidation of corresponding bromo end-functional polymers. The click-reaction efficiencies for the formation of Pc-end functional poly(tert-butyl acrylate) (PtBA), and polystyrene (PS) have been found to be 75, 93% respectively (Figure 2.20). Functionalization of ZnPc with PS increased the chemical stability of the complex but decreased the electrochemical reversibility during redox reactions. *In situ* electrochromic measurements of the complexes allowed the quantification of color coordinates of the each electrogenerated anionic and cationic redox species.

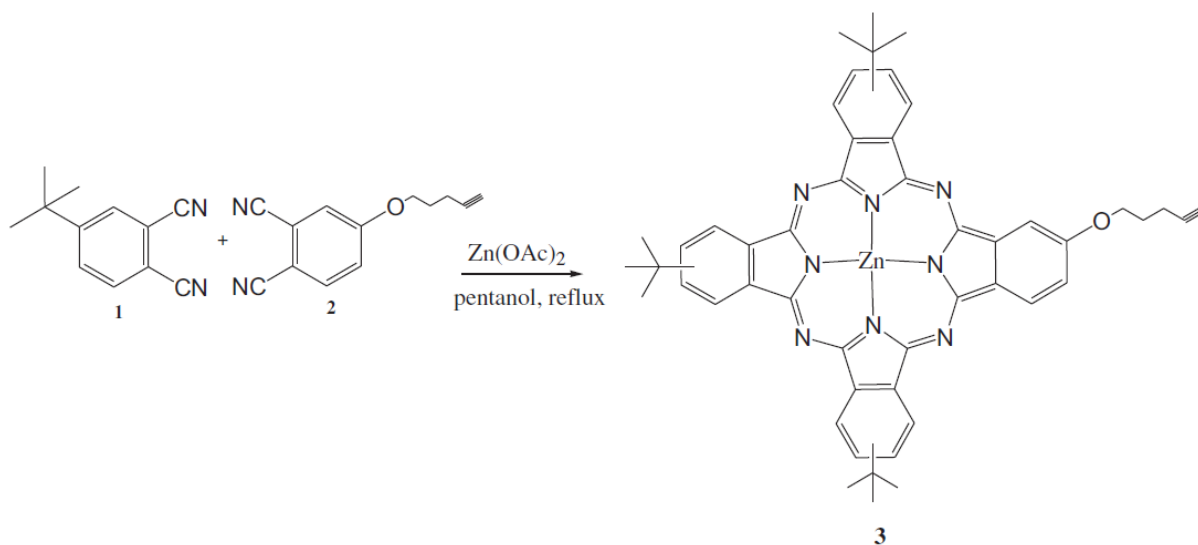


Figure 2.20: The synthesis of unsymmetrical zinc (II) phthalocyanine.

Bekaroğlu and his collaborators (2011) investigated the non-linear absorption and optical limiting properties of two trimeric metallo-phthalocyanines, namely 2,4,6-tris[2-oxa-9,10,16,17,23,24-hexa(hexylthio) phthalocyaninato M(II)]-s-triazine (M=Zn for ZnPc and Cu for CuPc) doped polyvinyl chloride (PVC) thin film in the nanosecond regime by using the open-aperture Z-scan technique [67]. The measurements were performed using 4 ns pulses generated from a frequency-doubled Nd:YAG laser at 532 nm wavelength. OL parameters of the ratio of the excited state to ground state absorption cross-sections κ , the effective nonlinear absorption coefficient β_{eff} , the linear absorption coefficient α_0 and the saturation density or energy density F_{sat} values were determined. The results show that MPC/PVC composite displays much larger nonlinear absorption coefficient and lower saturable fluence for optical limiting when compared to the same Pc molecules in solution. The results indicated that both compounds exhibited good OL performances. ZnPc shows slightly better OL parameters than that of CuPc (Figure 2.21).

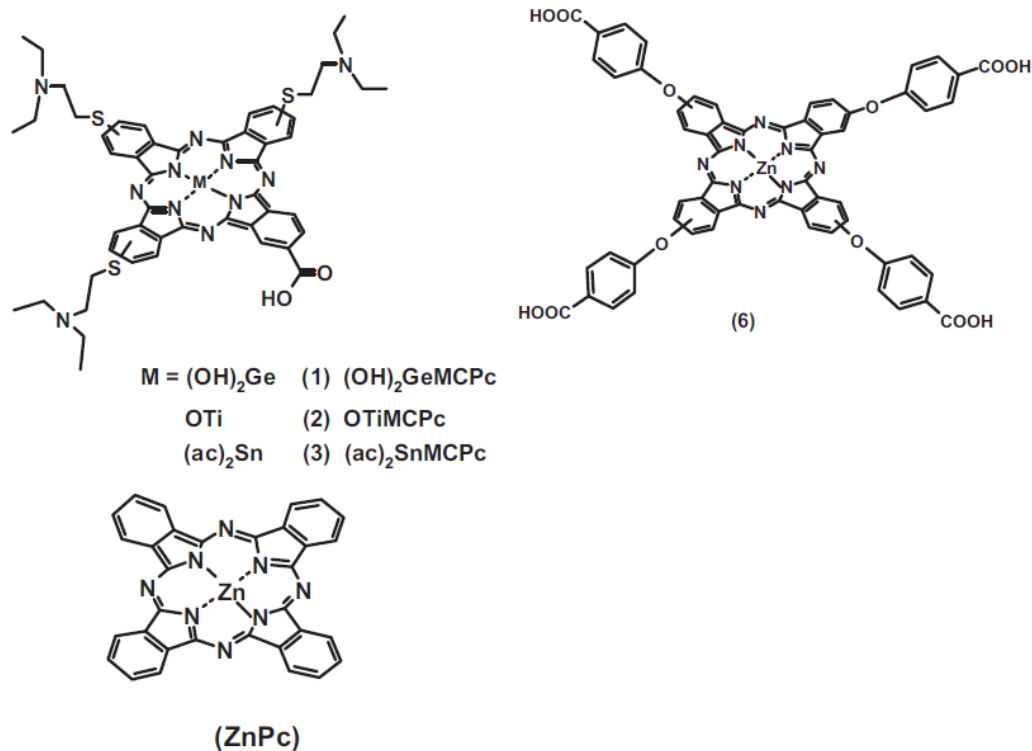


Figure 2.22: Molecular structures of the low symmetrically substituted complexes. MCPc = monocarboxy phthalocyanine (complexes 1-3), TPCPc = tetraphenylcarboxyphthalocyanine (6) and ZnPc.

Pochtennyi and co-workers (2014) investigated the electrical conductivity and adsorption–resistive response to nitrogen dioxide of composite films containing copper phthalocyanine nanoparticles dispersed into the polystyrene matrix [69]. The results are analyzed using the two level model of hopping conductivity. The contributions to the conductivity from intrinsic and impurity localization centers are singled out, and the concentrations of the localization centers in copper phthalocyanines free of impurities as well as the electron localization radii in impurity and intrinsic states are determined.

3. EXPERIMENTAL WORK

3.1 Instruments and Chemicals

- Instruments:

Perkin-Elmer Spectrum One FT-IR Spectrometer, Scinco UV-Vis

Spectrophotometer, Bruker-Spectrospin Inova 500 Mhz $^1\text{H-NMR}$ Spectroscopy.

- Chemicals:

Copper(I)bromide (Cu(I)Br), chloroform (CHCl_3), styrene (C_8H_8), methanol (CH_3OH), tetrahydrofuran ($\text{C}_4\text{H}_8\text{O}$), N,N-dimethylformamide ($\text{C}_3\text{H}_7\text{NO}$), sodium azide (NaN_3), sodium sulfate (Na_2SO_4), dichloromethane (CH_2Cl_2), potassium carbonate (K_2CO_3), ethanol ($\text{C}_2\text{H}_6\text{O}$), n-pentanol ($\text{C}_5\text{H}_{12}\text{O}$), n-hexane (C_6H_{14}), calcium chloride (CaCl_2), zinc acetate ($\text{Zn}(\text{CH}_3\text{COO})_2$), nitric acid (HNO_3),

1,8-diazabicyclo[5.4.0]undec-7-ene ($\text{C}_9\text{H}_{16}\text{N}_2$), 1-phenylethyl bromide ($\text{C}_8\text{H}_9\text{Br}$), 4-ethynylbenzyl alcohol ($\text{C}_9\text{H}_8\text{O}$), dimethylaminoethanol (DMAE) ($\text{C}_4\text{H}_{11}\text{NO}$), N,N,N',N'',N''pentamethyldiethylenetriamine ($\text{C}_9\text{H}_{23}\text{N}_3$).

3.2 Preparation of Polymers

3.2.1 Synthesis of PS-Br (1)

Cu(I)Br (0.125 g, 0.87 mmol), and PMDETA (0.4 mL, 3 mmol) were added to a 25 mL round bottom flask. The contents of the flask were degassed by flowing nitrogen through the flask for 15 min. Previously distilled styrene (5 mL, 0.04 mol) and 1-phenylethyl bromide (0.16 g, 0.87 mmol) were degassed separately and added to the flask. The solution was stirred at 110 °C for 1.5 h under N_2 . The mixture was dissolved in chloroform and run through a neutral alumina column to remove the copper complex and then concentrated by rotary evaporation. The polymer was precipitated into excess methanol (3x) and filtered. The polymer was dried at 40 °C under vacuum [66]. $M_n = 10000$, $^1\text{H-NMR}$ (500 MHz, CDCl_3) δ (ppm): 6.41 -7.25 (m, Ar-H, 5H), 3.65 (br, 1H, CH(Ph)-Br end group of PS), 1.30-2.10 (m, $-\text{CH}_2-\text{CH(Ph)-}$ 2H).

3.2.2 Synthesis of PS-N₃ (2)

PS-Br (2 g, 0.80 mmol) was dissolved in DMF (15 mL) and NaN₃ (0.52 g, 8.0 mmol) was added to the flask. After stirring overnight at room temperature, it was filtered and evaporated to remove the DMF. CH₂Cl₂ (100 mL) was added, and the reaction mixture was washed three times with distilled water. The organic layer was dried with anhydrous Na₂SO₄, and the solvent was removed in vacuum. The polymerization mixture was diluted with THF and precipitated in methanol (Figure 3.1). The recovered polymer PS-N₃ was dried in vacuum oven at 40 °C for 24 h [66]. Yield: 92 %. ¹H-NMR (500 MHz, CDCl₃) δ (ppm): 6.41 -7.25 (m, Ar-H, 5H), 3.41 (br, 1H, CH(Ph)-N₃ end group of PS), 1.25-1.80 (m, -CH₂-CH(Ph)- 2H). FTIR ν (cm⁻¹): 3060-3025 (Ar-H), 2918-2849 (CH, aliphatic), 2011 (-N₃), 1601,1492,1451 (C=C), 1067,1028,906,840,754,695.

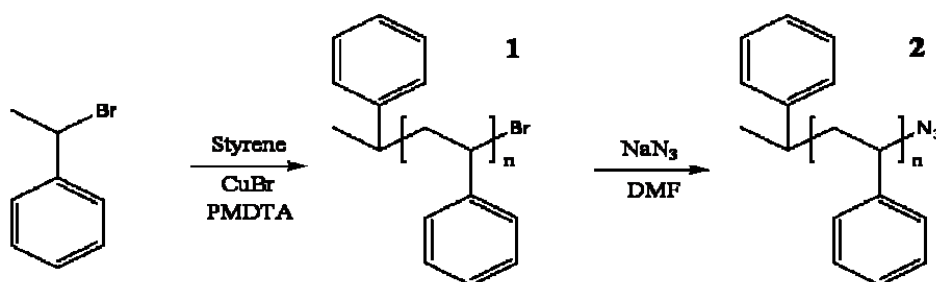


Figure 3.1: Polymerization and azidation process of styrene.

3.3 Synthetic Steps of Non-symmetrical Phthalocyanine Compound

3.3.1 Synthesis of 4-nitrophthalimide

40 g of phthalimide is added in to the mixture of 200 mL of sulfuric acid and 50 mL of nitric acid cooled in an ice-bath, as portions and stirred within 1-1,5 hours also it is provided to keep internal temperature at 10-15°C. After stirring for 30 min. in the ice-bath, the internal temperature is risen to 35°C. By the way, yellow particles are dissolved. Through an hour, the mixture is stirred at this temperature and cooled to 0°C, then poured into nearly 1 kg of ice water. 4-nitro phthalimide (5-nitro-1H-isoindole-1,3(2H)-dione) with yellow color is precipitated and filtered. Until removing acidity of the solution, it is washed with distilled water and crystallized

from 900 mL ethanol (Figure 3.2). Bright yellow crystals are filtered, washed with cold ethanol, then dried in the vacuum oven at 80-90°C [72]. Yield: 31 g (77 %), M.P. 195°C.

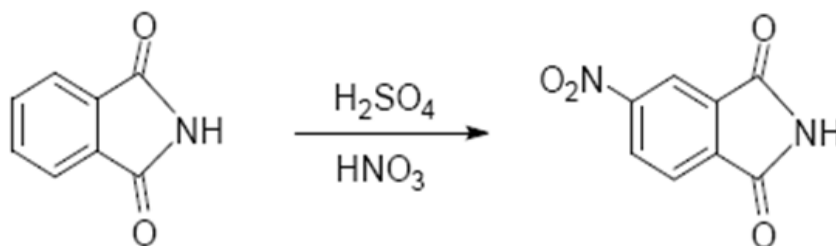


Figure 3.2: Synthesis of 4-Nitrophthalimide.

3.3.2 Synthesis of 4-nitro phthalamide

30 g of 4-nitro phthalimide is stirred in 168 mL of 32% ammonia solution at room temperature. After this, the solution is filtered, washed with cold diluted water and THF. During the reaction the color of 4-nitro phthalimide is yellow, it converts to white with the formation of 4-nitrobenzene-1,2-dicarboximide. This color change shows that the reaction occurred [72]. Yield: 24 g (73 %), M.P. 197°C, C₈H₇N₃O₄ (Figure 3.3).

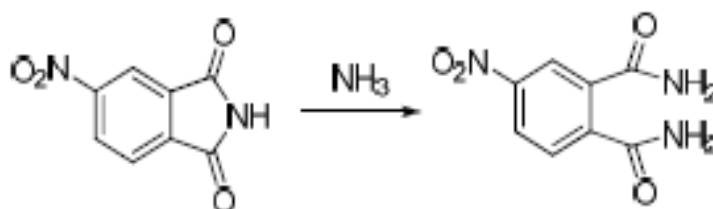


Figure 3.3: Synthesis of 4-nitro phthalamide.

3.3.3 Synthesis of 4-Nitrophthalonitrile

70 mL of dry dimethyl formamide was cooled to 0 °C in an ice bath by bubbling nitrogen gas through a three-necked flask and 7 mL of thionyl chloride was added slowly without exceeding the internal temperature of 5 °C, stopped adding of nitrogen gas and calcium chloride tube was attached to the top of the flask. At the same time the color turned to yellow (Figure 3.4). Then 10 g (48 mmol) of 4-nitro phthalimide was added in portions at 0-5 °C. Stirring in ice bath was continued for 1 hour. The mixture was stirred at room temperature for 2 hours and poured into 500 g of ice-water. White product was filtered, it was washed with water, then with 250 ml

of 5 % sodium bicarbonate solution, again with water and dried in a vacuum oven in 110-120 °C [72]. $C_8H_3N_3O_2$ yield 7.4 g (90 %) M.P. 141°C.

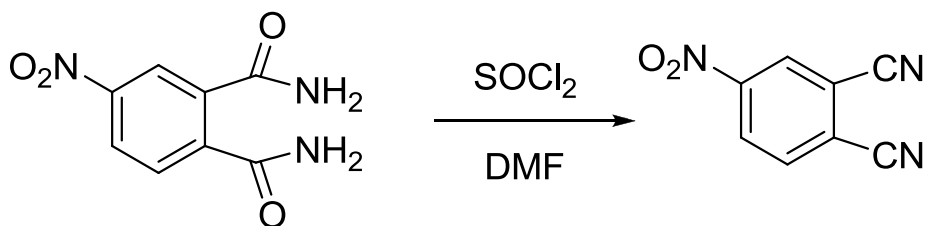


Figure 3.4: Synthesis of 4-Nitrophthalonitrile.

3.3.4 Synthesis of 4-(4-tert-butylphenoxy)phthalonitrile (3)

In an argon atmosphere, 1.59 g (11.48 mmol) of anhydrous K_2CO_3 was added in 0.53 g portions at 1-h intervals to a solution of 1.72 g (11.48 mmol) of 4-tert-butylphenol and 1 g (5.74 mmol) of 4-nitrophthalonitrile in 10 mL of dry N,N-dimethylformamide (DMF). The mixture was stirred for 48 h at room temperature under argon. After 48 h the undissolved salt was filtered, 200 mL of cold water was added, and then the mixture was stirred rapidly. The resulting precipitate was filtered by vacuum and washed with water (Figure 3.5). The crude product was recrystallized from ethanol. White crystals was obtained [73]. Yield: 47%; mp: 114-116 °C. FTIR ν , cm^{-1} : 3226, 3084, 2962, 2903, 2868, 2231, 1668, 1584, 1504, 1480, 1410, 1394, 1279, 1241, 1109, 1179, 1109, 1088, 1019, 953, and 872; 1H -NMR ($CDCl_3$): δ 6.97-7.71 (Ar-H, 7H), 1.35 (s, 9H), and $C_{18}H_{16}N_2O$; MW: 276.34 g/mol.

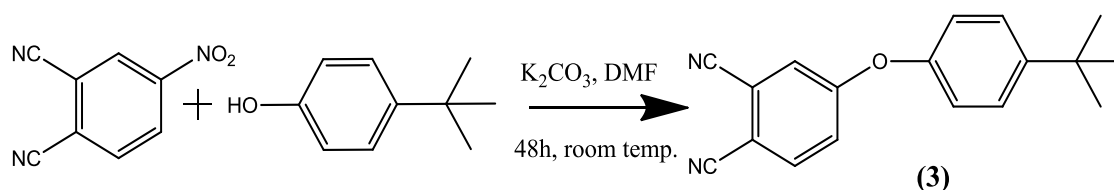


Figure 3.5: Synthesis of 4-(4-tert-butylphenoxy)phthalonitrile.

3.3.5 Synthesis of 4-((4-ethynylbenzyl)oxy)phthalonitrile (4)

0.297 g (2.25 mmol) of 4-ethynylbenzyl alcohol and 4-nitrophthalonitrile 0.389 g (2.25 mmol) were added successively with stirring to dry N,N-dimethylformamide (5 mL). After they were dissolved, anhydrous K_2CO_3 0.56 g (4.05 mmol) was added portion wise for 2h and the mixture was stirred vigorously at 40 °C for 72 h under nitrogen. Then the solution was poured into ice water (200 mL). The solution was

acidified with conc. HCl until precipitation occurred (pH = 1–2). The yellow brownish product was collected by centrifugation and rinsed with ethanol. Finally, the solid was dissolved in a minimum amount of chloroform and then added to n-hexane dropwise (Figure 3.6). The brownish crystals were filtered and dried. Cream colored crystals. Yield: 55%; mp: 132 °C. FTIR ν , cm^{-1} : 3269 (–C≡C–H), 3081 (Ar–H), 2930 (alkyl CH), 2233 (C≡N), 2105 (C≡C), 1260 (C–O–C); $^1\text{H-NMR}$ (500 MHz, CDCl_3) δ (ppm): 7.73 (1H, d, Ar-H), 7.55 (2H, d, Ar-H), 7.37 (2H, d, Ar-H), 7.34 (1H, d, Ar-H), 7.25 (1H, d, Ar-H), 5.17 (2H, s, –O–CH₂), 3.13 (1H, s, –C≡C–H); ^{13}C NMR (500 MHz; CDCl_3), (δ : ppm): 70.47 (O–CH₂), 82.91 (–C≡), 78.23 (≡C–H), 107.86 (aromatic C), 115.09 (C≡N), 115.54 (C≡N), 117.58 (aromatic C), 119.69 (aromatic C), 119.92 (aromatic C), 122.78 (aromatic C), 127.30 (aromatic C), 132.66 (aromatic C), 133.92 (aromatic C), 134.13 (aromatic C), 135.09 (aromatic C), 135.29 (aromatic C), 161.45 (–O–(Aromatic –C=)) and $\text{C}_{17}\text{H}_{10}\text{N}_2\text{O}$; MW: 258.27g/mol.

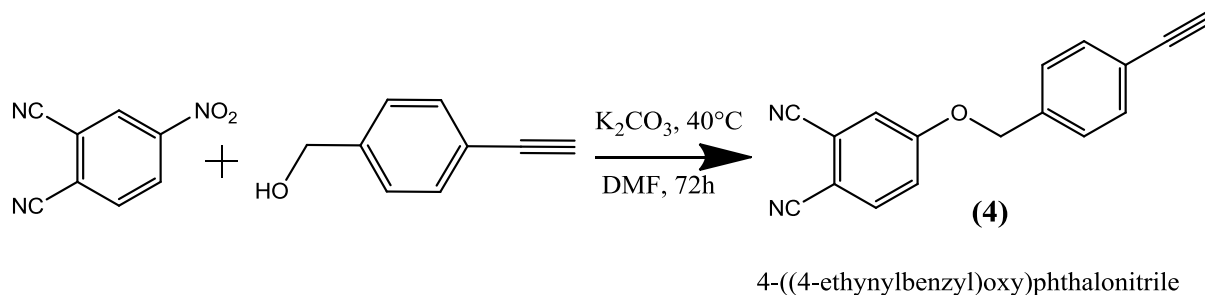


Figure 3.6: Synthesis of 4-((4-ethynylbenzyl)oxy)phthalonitrile.

3.3.6 Synthesis of 9(10),16(17),23(24)-Tris-(t-butylphenoxy)-{4-ethynylbenzyloxy} phthalocyaninatozinc(II) (5)

4 (52 mg, 0.2 mmol), **3** (165 mg, 0.6 mmol), and zinc acetate were added into a solution of DBU (0.5 mL) and pentanol (3 mL). The mixture was stirred under N_2 at 145°C. After 24 hours, the mixture was cooled and the resulting precipitate was collected by centrifugation. The solid was washed with mixture of MeOH and water (1:3) and dried to afford a dark green solid the purification was carried out by column chromatography on silica gel using hexane/ THF (2:1) as the eluent to afford **5** as a green solid (Figure 3.7). Yield: 11%. FTIR ν , cm^{-1} 3285 (–C≡C–H), 3073 (Ar–H), 2956–2866 (alkyl CH), 2105 (C≡C), 1226 (C–O–C). ^1H NMR (500 MHz; CDCl_3 ; Me₄Si: dH, ppm) 7.10–7.91 (28H, b, Ar–H), 5.17 (2H, s, O–CH₂), 3.12

(1H,s, -C≡C-H), 1.40–1.13 (27H, m, -C(CH₃)₃). UV-vis (in THF): 1, nm (log e) 352 (4.71), 675 (5.10)

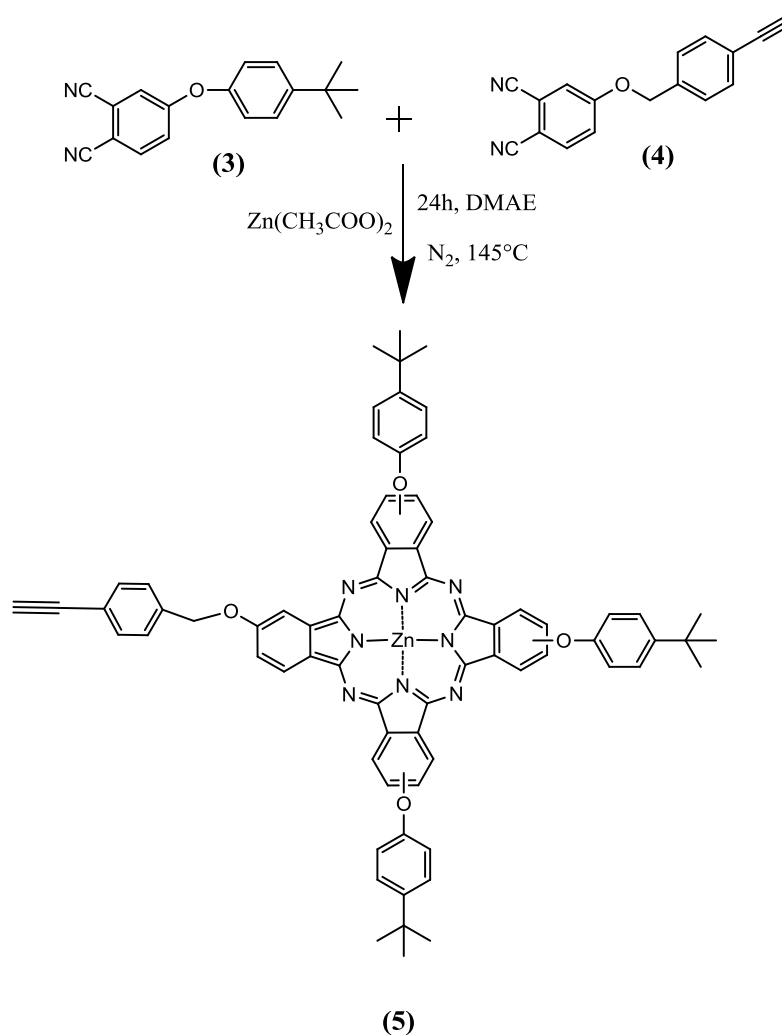


Figure 3.7: Synthesis of novel zinc(II)phthalocyanine **5**.

3.4 Synthesis of PS- Zinc Phthalocyanine Composites via Click Chemistry

Zinc phthalocyanine (0.177 g, 0.0885 mmol), DMF (3 mL) were added to a 25 mL of Schlenk tube and stirred until a homogenous mixture is obtained and then added PMDETA (27.7 mL, 0.1326 mmol), CuBr (0.0190 g, 0.1326 mmol), polystyrene (0.02 g, 0.0221 mmol). The reaction mixture was stirred under nitrogen at 45 °C for 48 h. After the specified time, the polymer was isolated by diluting polymer mixture with tetrahydrofuran (THF) and passing through an alumina column to remove the metal salt. The excess of THF was evaporated under reduced pressure. The resulting polymer was dissolved in THF, precipitated in 10-fold excess of diethyl ether. The

dissolution-precipitation procedure was repeated two times (Figure 3.8). The recovered green product was dried in a vacuum oven at 40°C for 24 h [71]. Yield: 86 %. FTIR ν , cm^{-1} : 3026 (Ar-H), 2930 (alkyl CH), 1260 (C-O-C); $^1\text{H-NMR}$ (500 MHz, CDCl_3) δ (ppm): 8.1 (s, 1H, -N-CH=), 7.7-6.4 (br, Ar-H), 5.2 (s, -O-CH₂), 5.17 (br, 1H, CH(Ph)-triazol-PS), 2.0-0.7 (m, aliphatic protons of Pc and PS).

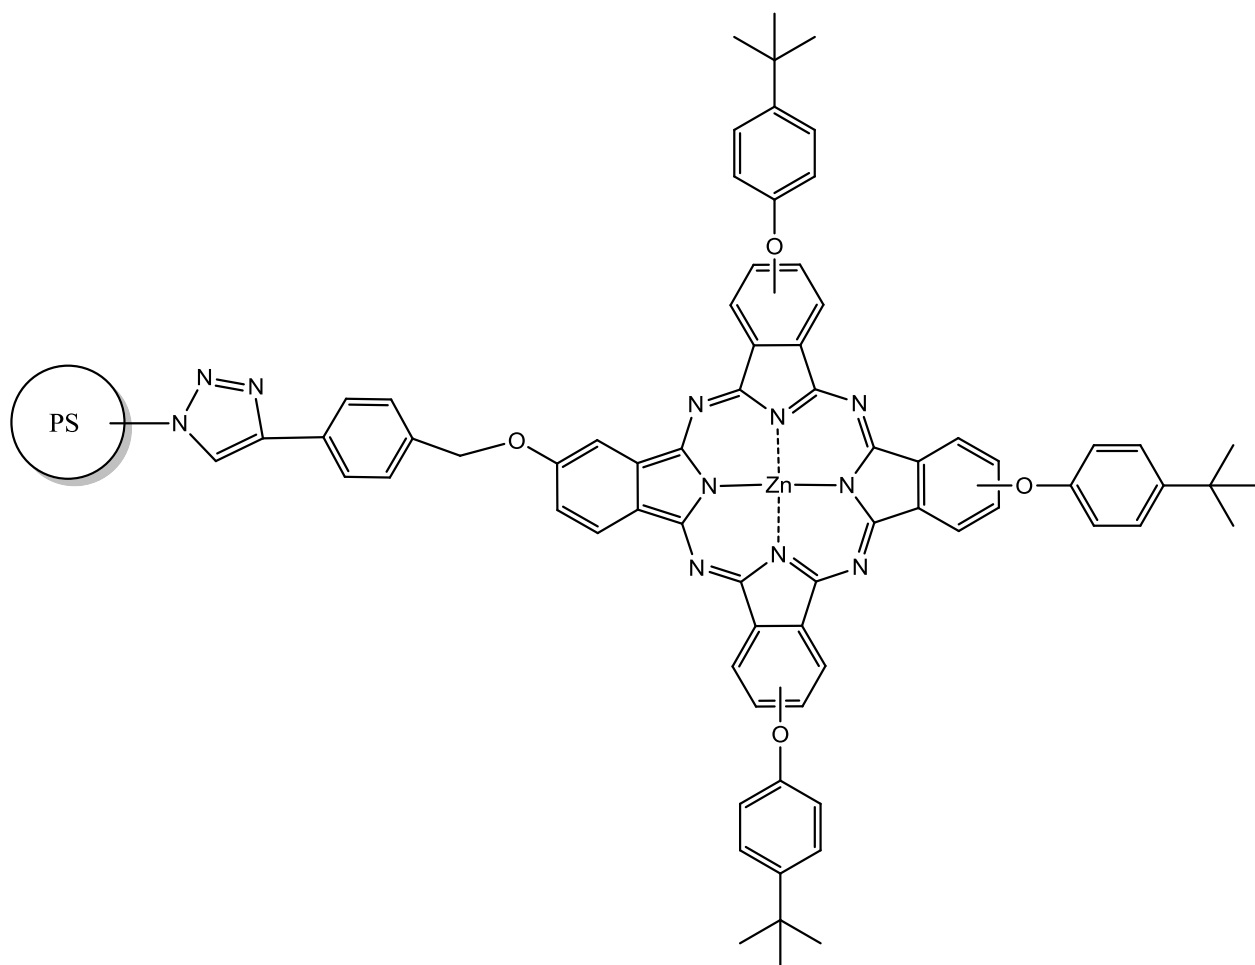


Figure 3.8: PS- Zinc Phthalocyanine Composites.

4. RESULTS AND DISCUSSION

4.1 Synthesis

In chemical synthesis, the term “selectivity” refers to the discrimination displayed by a reagent, when it reacts with two different reactants or functional groups. Highly selective reactions proceed with minimal reliance on protecting groups and contribute to both atom and step economy. Due to their greater stability than porphyrins, metal phthalocyanines (MPcs) attract great attention for their applications as catalysts for selective organic transformations including oxidation-reduction processes and electron transfer reactions [56].

We first synthesized **5** via a method which is mentioned in experimental part and characterized the new product. The direct statistical reaction of **3** and **4** in a ratio of approximately 3:1 gave six products, the desired AAAB could be easily separated by column chromatography as a second fraction. The column chromatography performed by using the solvent mixture of THF:toluene in a ratio of approximately 1:3. The separated fraction of phthalocyanine was washed with excess of cold methanol and dried at room temperature under vacuum. Taking into account that utilization of Pcs in click chemistry requires terminal alkyne functionality and good solubility. Prepared unsymmetrical phthalocyanine have a terminal $-C\equiv C-H$ group. This is important for the future of our process.

On the other hand bromo-end functional polystyrene was synthesized by ATRP method. Prepared polystyrene was azidated by the reaction with sodium azide and DMF. After this reaction PS-N₃ was obtained by precipitation with THF and methanol in a ratio of 1:10. The product was dried under vacuum at 40 °C.

The last step of our work was click reaction between alkyne-end unsymmetrical phthalocyanine and azidated polystyrene. PS-N₃ chains were reacted with the ZnPc in DMF with CuBr/PMDETA as catalyst to produce zinc phthalocyanine-terminated

polymers. After the synthesis process, characterization of ZnPc, bromo-end functional polystyrene and Pc-PS composite were done.

4.2 Characterization

4.2.1 Characterization of novel phthalonitrile precursor (4)

The characterization of the new compound synthesized in this study was performed with FTIR, $^1\text{H-NMR}$, $^{13}\text{C-NMR}$, and similar methods. The relevant FTIR and NMR spectra were given in Appendixes Figure A.5 and Figure A.11. When the FTIR spectrum of the compound is investigated, the CH stretching vibration of characteristic ethynyl group ($-\text{C}\equiv\text{CH}$) was observed at 3269 cm^{-1} and $\text{C}\equiv\text{C}$ stretching vibration peak was seen at 2105 cm^{-1} . Again, the aromatic and alkyl C-H stretching vibrations were observed at 3081 and 2930 cm^{-1} , respectively. As a last remark, since we have observed the $\text{C}\equiv\text{N}$ stretching vibration peak at 2233 cm^{-1} and etheric oxygen bridge in C-O-C moiety in the phthalonitrile compound at 1260 cm^{-1} , this compound was successfully synthesized by means of FTIR data.

Again, the ^1H and ^{13}C NMR spectral data are in perfect harmony with the expected values for the phthalonitrile **4**, so the compound was successfully synthesized. When the $^1\text{H-NMR}$ spectrum of the compound is examined, the group of seven aromatic protons of the structure were observed between $\delta 7.74 - 5.24$ ppm; two protons of the O- CH_2 group appeared at $\delta 5.17$ and, the $\text{C}\equiv\text{C-H}$ proton was found at $\delta 3.13$ ppm. The ^{13}C NMR of the compound revealed that all protons of the 17 C group were at their expected positions. The most characteristic peaks of the compound were the $\text{C}\equiv\text{N}$ peak at $\delta 115.09 - 115.54$ ppm, the O- CH_2 peak at $\delta 70.47$ ppm, the $-\text{C}\equiv$ peak at $\delta 82.91$ ppm, the $\equiv\text{C-H}$ peak at $\delta 78.23$ ppm and $-\text{C}\equiv$ carbon at $\delta 82.91$ ppm. Lastly, the remaining aromatic carbon peaks were observed between $\delta 135.29 - 107.86$ ppm range.

4.2.2 Characterization of the unsymmetrical ZnPc (5)

The unsymmetrical ZnPc was characterized by using $^1\text{H-NMR}$, FTIR and UV-Vis spectroscopy. Infra-red spectrum further showed the presence of terminal alkynyl group bands around 3285 cm^{-1} , 2105 cm^{-1} and tert-butyl groups bands around 1393 cm^{-1} , 1361 cm^{-1} and 1336 cm^{-1} . The $^1\text{H-NMR}$ spectrum of ZnPc showed

characteristic signals for the aromatic Pc ring protons between δ 7.10 and δ 7.91 ppm corresponding to the required number of Pc protons. Moreover the $^1\text{H-NMR}$ spectrum showed the signals at δ 5.17 ppm specific to $\text{CH}_2\text{-O}$ protons, δ 3.12 for $\text{C}\equiv\text{C-H}$ proton and δ 1.13-1.40 for $\text{C-(CH}_3)_3$ protons. The UV-Vis spectra of the studied zinc phthalocyanine **5** in THF was given in Appendixes Figure A.9. The $\pi\text{-}\pi^*$ transitions for the B and Q-band absorption were observed at 352 and 675 nm, respectively.

4.2.3 Characterization of azido-polystyrene (2)

The FT-IR spectra of azidoterminated polystyrene (PS-N_3) exhibits the expected characteristic signal at 2011 cm^{-1} due to the N_3 stretching vibration, hence confirming the presence of azido groups. In the $^1\text{H-NMR}$ spectra, for PS-N_3 , a signal at 3.65 ppm, assigned to CH-Br , disappeared, and a new peak appeared at 3.41 ppm, indicating CH linked to the azide end group.

4.2.4 Characterization of phthalocyanine-terminated polystyrene

At the final step of the study, we prepared the targeted PS-ZnPc composites by the standard copper-catalyzed click reaction by using the azido-terminated polystyrene and terminal alkynyl substituted zinc phthalocyanine we obtained earlier. Every phase of this process was monitored with spectroscopic techniques in a detailed manner. In this context, firstly we understood that the targeted composite was formed by examining the FTIR spectra. The following spectra show the FTIR of each step.

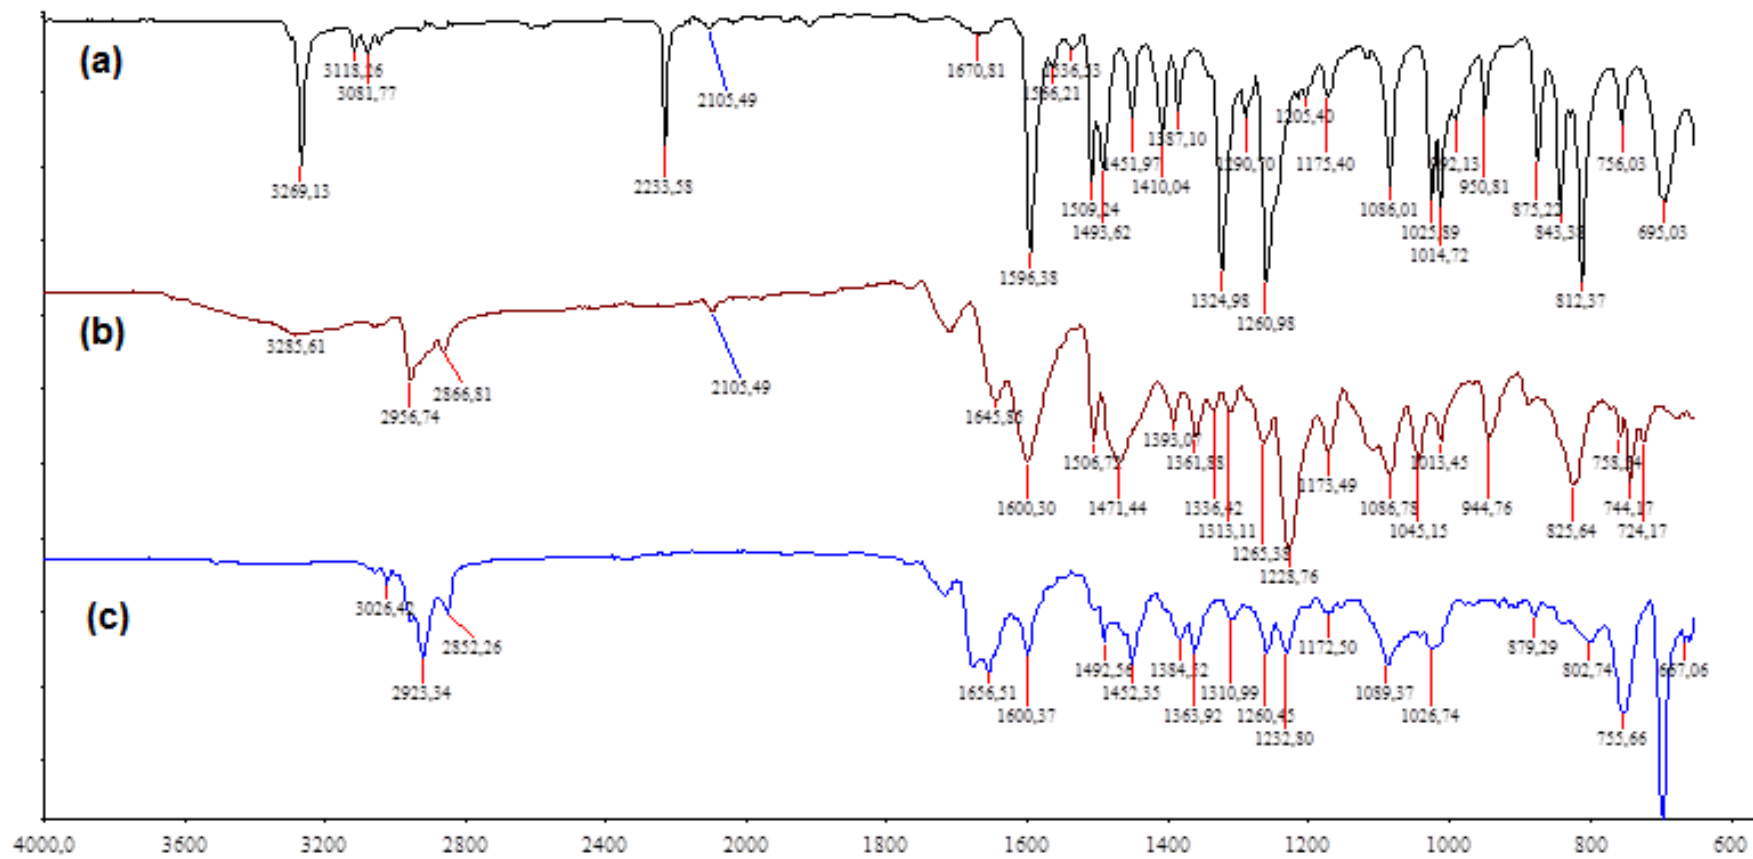


Figure 4.1: FTIR spectrum of (a) 4, (b) ZnPc, (c) PS-ZnPc

In Figure 4.1, it was apparently shown that the click reaction occurred over the ZnPc substrate. Since we monitored the C≡C-H peak, which is characteristic for monosubstituted **4** compound as we took it as a model for click reaction, the reaction was seen to proceed successfully. C≡C and C-H stretching vibrations of the FTIR spectrum of ZnPc compound were seen at 3269 and 2105 cm⁻¹, respectively, and this obviously proves that the Pc obtained has an ethynyl moiety. After click reaction, the FTIR can be seen in Figure 4.1 (c) and it proves the formation of triazol ring by opening of the triple bond after 1,3-dipolar cycloaddition, as evident in the absence of the peaks 3269 and 2105 cm⁻¹.

The process of click reaction was also monitored over the polymer structure.

The successful azidation was observed with a N₃-based stretching peak at 2011 cm⁻¹, visible in the spectrum of PS-N₃ but not PS-Br. Additionally, the characteristic peak of the azide group can be monitored to see the click reaction coming true. The absence of 2011 cm⁻¹ FTIR peak in PS-N₃ in the spectrum of click product is another proof for successful transformation (Figure 4.2).

UV-Vis spectra are useful to differentiate between azide-containing polystyrene and the click product. When the UV-Vis spectrum of the click product was examined, the Q and B bands of the phthalocyanine macrocycle were observed at 675 and 352 nm, respectively. In addition to the previous observation, the peak at 362 nm is the proof of successful azidation of the PS-Br structure, with the special band of azidation. The composite's UV-Vis spectrum shows that this peak at 362 nm disappears completely after cyclization. These UV-Vis data can be used as proof for obtaining the desired final structure as expected (Figure 4.3).

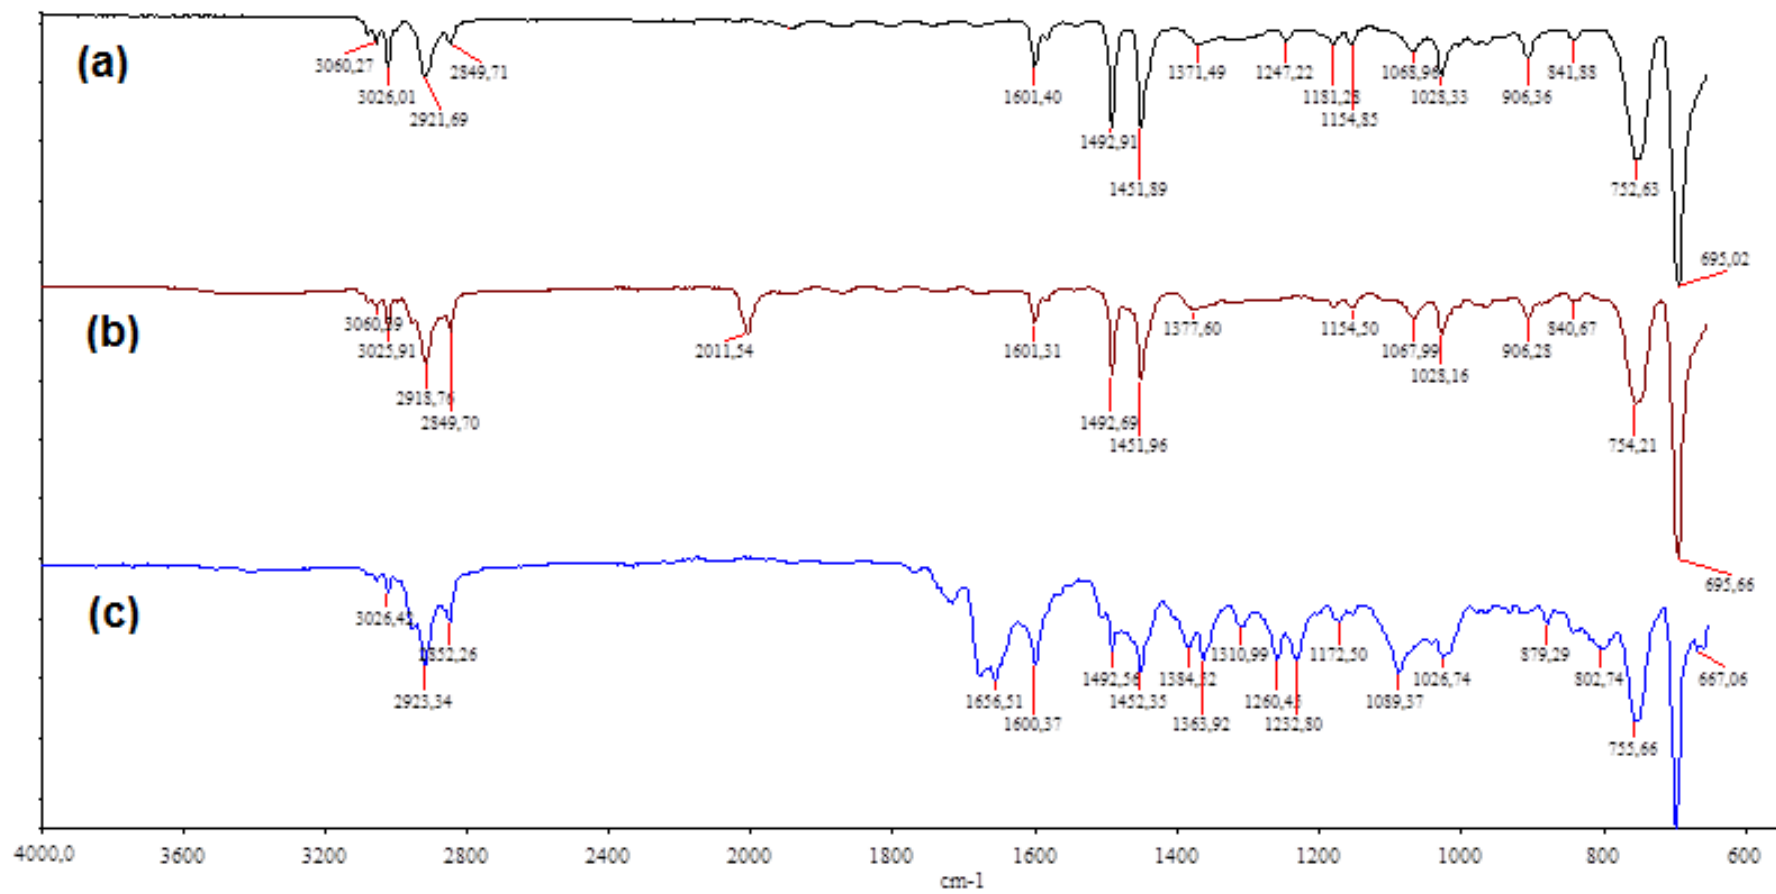


Figure 4.2: FTIR spectrum of (a) PS-Br, (b) PS-N₃, (c) PS-ZnPc.

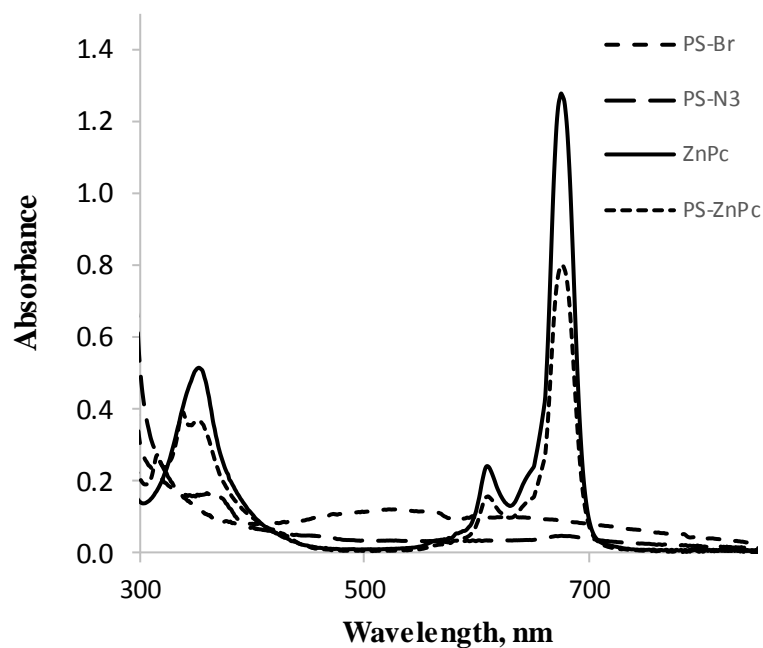


Figure 4.3: UV-Vis spectrum of (a) PS-Br, (b) PS-N₃, (c) PS-ZnPc.

In addition to these analyses, ¹H-NMR spectrum was examined to see the steps of click procedure and the results. PS-Br and PS-N₃ spectra were examined and the CH-Br peak at δ 3.65 ppm shifted to δ 3.41 after azidation. Lastly, the ¹H-NMR spectrum of the final compound had the above-mentioned peak at δ 5.17 ppm. The peak at δ 5.20 ppm is due to the -O-CH₂ group of the zinc phthalocyanine. The ¹H-NMR spectrum of the click product showed a triazole peak at δ 8.1 ppm. The peaks between δ 6.5 – 7.8 ppm are both due to the aromatic benzene ring protons of the phthalocyanine and polymeric backbone.

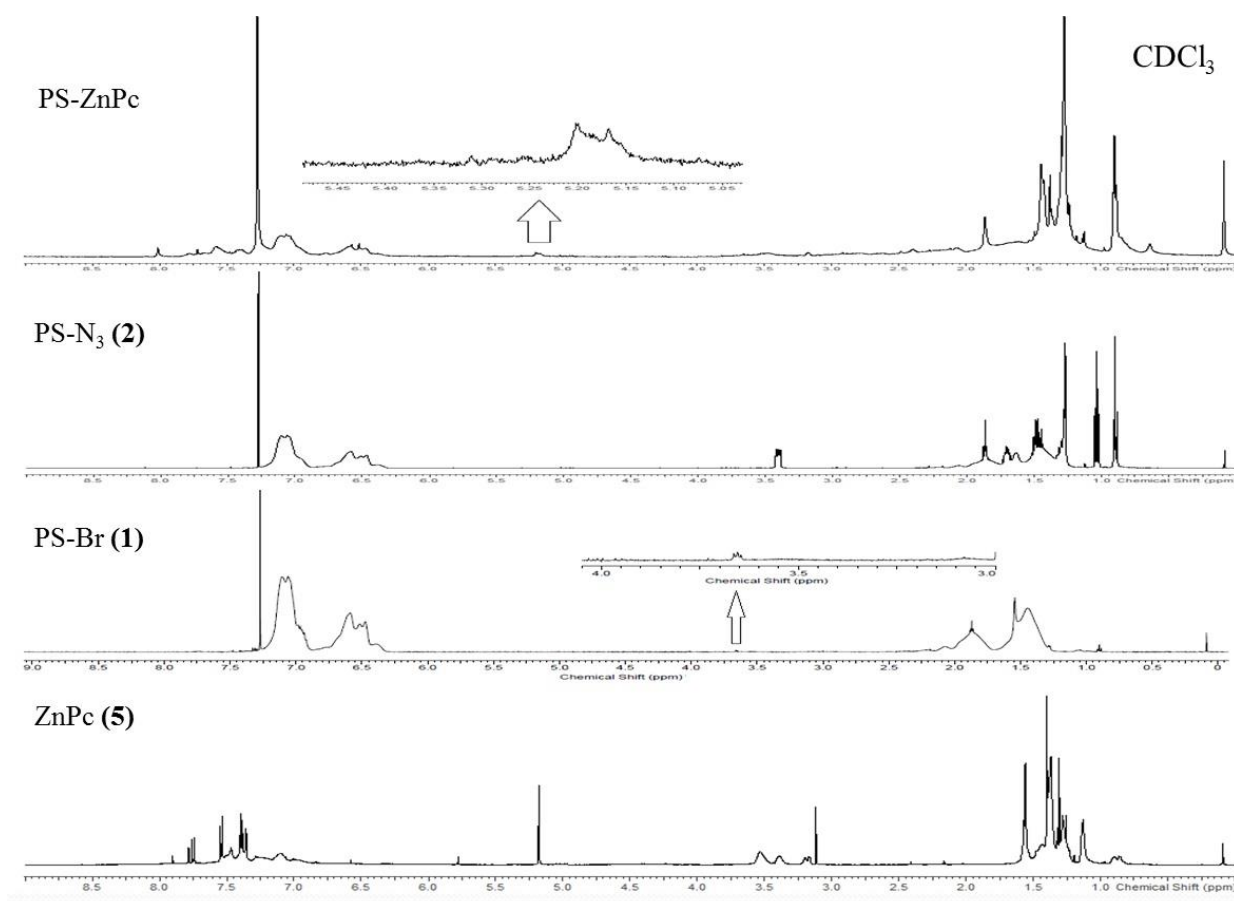


Figure 4.4: ^1H -NMR spectrum of ZnPc, PS-Br, PS- N_3 , PS-ZnPc.

A consideration of the above data shows that the $-\text{CH-Br}$ peak at δ 3.65 for PS-Br converts to δ 3.41 ppm for the $-\text{CH-N}_3$ moiety. Moreover, the shifting of δ 3.41 ppm signal to δ 5.17 ppm after click reaction is indicative of a change of the chemical environment of the PS proton, which is caused by the triazole ring after click reaction (Figure 4.4). The newly formed peak at δ 8.1 ppm around the aromatic region is due to the triazole ring. All of these ^1H -NMR data show us that every phase of the synthesis provided us with the expected molecules.

5. CONCLUSION

Phthalocyanines are important materials finding applications in many fields from photocatalytic events to photodynamic therapy. A frequently encountered problem in phthalocyanine based materials is aggregation of planar molecules which prohibit number of photochemical events. In the present work by combining phthalocyanine with a polystyrene backbone a solution to above cited problems have been proposed. Therefore, we can say that various applications of synthesized polystyrene-unsymmetrical zinc phthalocyanine composites deserve to be investigated by high-tech experts.

REFERENCES

- [1] **Thomas, S., Kuruvilla, J., Malhotra, S. K., Goda, K. and Sreekala.** (2012) M. S., In *Polymer Composites, Volume 1, Macro- and Microcomposites*; Wiley-Vch, 78-81.
- [2] **Wang, R.-M., et al.** (2011). 1 - Introduction to polymer matrix composites. *Polymer Matrix Composites and Technology*, Woodhead Publishing: 1-548.
- [3] **Rothon, R.** (2003). *Particulate-filled Polymer Composites*, Rapra Technology.
- [4] **Srinivasulu, N. V., et al.** (2012). "Mechanical properties of polymer composite materials." *International Journal of Research in Engineering and Technology* **1**(1): 78-81.
- [5] **Mazumdar, S.** (2001). *Composites Manufacturing: Materials, Product, and Process Engineering*, CRC Press.
- [6] **Luo, J.** (2003). "Characterization and modeling of mechanical behavior of polymer/clay nanocomposites." *Composites Science and Technology* **63**(11): 1607-1616.
- [7] **Wang, Y.** (2003). "2-D nano-scale finite element analysis of a polymer field." *Composites Science and Technology* **63**(11): 1581-1590.
- [8] **Harris, B. and I. o. Materials** (1999). *Engineering Composite Materials*, IOM.
- [9] **Ghosh, P.** (2001). *Polymer Science and Technology: Plastics, Rubbers, Blends and Composites*, Tata McGraw-Hill.
- [10] **Hollaway, L. and B. P. Federation** (1994). *Handbook of Polymer Composites for Engineers*, Taylor & Francis.
- [11] **Wang, R. M., et al.** (2011). *Polymer Matrix Composites and Technology*, Elsevier Science.
- [12] **Jenkins, A. D.** (2013). *Polymer Science: A Materials Science Handbook*, Elsevier Science.
- [13] **Özden G.,** (2004), "Synthesis and Characterization of Polystyrene Clay Nanocomposites", *Master Thesis*, Middle East Technical University Graduate School of Natural and Applied Sciences, Ankara

- [14] **Fink, J. K.** (2013). *Reactive Polymers Fundamentals and Applications: A Concise Guide to Industrial Polymers*, Elsevier Science.
- [15] **Biron, M.** (2007). *Thermoplastics and Thermoplastic Composites: Technical Information for Plastics Users*, Elsevier Science.
- [16] **Wünsch, J. R.** (2000). *Polystyrene: Synthesis, Production and Applications*, Rapra Technology Limited.
- [17] **Bevington J. C.** (1961). "Radical Polymerization," Academic Press, New York.
- [18] **Akay, M.** (2013). *Introduction to Polymer Science and Technology*, Bookboon.
- [19] **Kiu J. J. and Choi K. Y.** (1988). "The dynamic behavior of continuous stirred bed reactors for the solid catalyzed gas phase polymerization of propylene" *Chem. Eng. Sci.*, **43**(10): 65.
- [20] **Ebewele, R. O.** (2000). *Polymer Science and Technology*, CRC Press.
- [21] **Kroschwitz, J. I.** (2004). *Encyclopedia of polymer science and technology*, J. Wiley & sons.
- [22] **Nalwa, H. S.** (2001). *Supramolecular Photosensitive and Electroactive Materials*, Elsevier Science.
- [23] **Nalwa, H. S.** (2001). *Handbook of Surfaces and Interfaces of Materials*, Five-Volume Set, Elsevier Science.
- [24] **Kadish, K., et al.** (2012). *The Porphyrin Handbook: Phthalocyanines: Synthesis*, Elsevier Science.
- [25] **Kadish, K., et al.** (2012). *The Porphyrin Handbook: Phthalocyanines: Properties and Materials*, Elsevier Science.
- [26] **Mantareva, V., et al.** (2016). "Lutetium(III) acetate phthalocyanines for photodynamic therapy applications: Synthesis and photophysical properties." *Photodiagnosis Photodyn Ther.* **14**: 98-103
- [27] **Koyun, Ö., et al.** (2016). "Microwave-assisted synthesis, electrochemistry and spectroelectrochemistry of phthalocyanines bearing tetra terminal-alkynyl functionalities and click approach." *Polyhedron* **113**: 35-49
- [28] **Al-Sohaimi, B. R., et al.** (2016). "Enhancing photophysical and photochemical properties of zinc(II) phthalocyanine dyes by substitution of triptycene moieties." *Journal of Luminescence* **173**: 82-88.
- [29] **Kumar, A., et al.** (2016). "Phthalocyanines based QCM sensors for aromatic hydrocarbons monitoring: Role of metal atoms and substituents on response to toluene." *Sensors and Actuators B: Chemical* **230**: 320-329.

- [30] **Zorlu, Y., et al.** (2010). "Monoglycoconjugated water-soluble phthalocyanines. Design and synthesis of potential selectively targeting PDT photosensitisers." *Tetrahedron Letters* **51**(50): 6615-6618.
- [31] **Basova, T., et al.** (2013). "Electrochromic lutetium phthalocyanine films for in situ detection of NADH." *Optical Materials* **35**(3): 634-637.
- [32] **Lee, W., et al.** (2012). "Synthesis and characterization of solubility enhanced metal-free phthalocyanines for liquid crystal display black matrix of low dielectric constant." *Dyes and Pigments* **92**(3): 942-948.
- [33] **Choi, S. A., et al.** (2016). "Effects of thermal preparation on Copper Phthalocyanine organic light emitting diodes." *Journal of Luminescence* **171**: 149-153.
- [34] **Bankole, O. M. and T. Nyokong** (2016). "Nonlinear optical response of a low symmetry phthalocyanine in the presence of gold nanoparticles when in solution or embedded in poly acrylic acid polymer thin films." *Journal of Photochemistry and Photobiology A: Chemistry* **319-320**: 8-17.
- [35] **Yan, X., et al.** (2015). "Synthesis of an octathienyl-fused phthalocyanine as a donor material for organic solar cells." *Dyes and Pigments* **114**: 124-128.
- [36] **Chao, C.-G. and D. E. Bergbreiter** (2016). "Highly organic phase soluble polyisobutylene-bound cobalt phthalocyanines as recyclable catalysts for nitroarene reduction." *Catalysis Communications* **77**: 89-93.
- [37] **Liu, J. Y., et al.** (2016). "In vitro photodynamic activities of zinc(II) phthalocyanines substituted with pyridine moieties." *Photodiagnosis Photodyn Ther* **13**: 341-343.
- [38] **Gou, H., et al.** (2016). "Electronic and optoelectronic properties of zinc phthalocyanine single-crystal nanobelt transistors." *Organic Electronics* **30**: 158-164.
- [39] **Menzli, S., et al.** (2016). "Adsorption study of copper phthalocyanine on Si(111)($\sqrt{3}\times\sqrt{3}$)R30°Ag surface." *Applied Surface Science* **369**: 43-49.
- [40] **Dinçer, H., et al.** (2015). "Synthesis and photophysical studies of poly(ethylene glycol) conjugated symmetrical and asymmetrical zinc phthalocyanines." *Journal of Molecular Structure* **1102**: 190-196.
- [41] **Le Droumaguet, B. and K. Velonia** (2008). "Click Chemistry: A Powerful Tool to Create Polymer-Based Macromolecular Chimeras." *Macromolecular Rapid Communications* **29**(12-13): 1073-1089.
- [42] **Kolb, H. C., et al.** (2001). "Click Chemistry: Diverse Chemical Function from a Few Good Reactions." *Angewandte Chemie International Edition* **40**(11): 2004-2021.

- [43] **Li, Huiyuan, Rachna Aneja, and Irwin Chaiken.** (2013). "Click Chemistry in Peptide-Based Drug Design." *Molecules (Basel, Switzerland)* **18**: 9797–9817
- [44] **Rostovtsev V.V., Green L.G., Fokin V.V., Sharpless K.B.** (2002) A stepwise Huisgen cycloaddition process: copper(I)-catalyzed regioselective "ligation" of azides and terminal alkynes. *Angew Chem Int Ed Engl* **41**: 2596-2599.
- [45] **Domagalska, J., et al.** (2016). "Conversion of leucomycin-A3 antibiotic into novel triazole analogues via regio- and diastereoselective SN1' substitution with allylic rearrangement and 1,3-dipolar cycloaddition of CuAAC type." *Tetrahedron Letters* **57**(15): 1661-1666.
- [46] **Green, S. K., et al.** (2016). "Diels–Alder cycloaddition of 2-methylfuran and ethylene for renewable toluene." *Applied Catalysis B: Environmental* **180**: 487-496.
- [47] **Waring, M. J., et al.** (2015). "A safe and scalable synthesis of 2-hydroxy-3-alkoxypropionates by epoxide ring opening." *Tetrahedron Letters* **56**(34): 4904-4907.
- [48] **Contreras, C. A., et al.** (2016). "Synthesis of a family of peracid-silica materials and their use as alkene epoxidation reagents." *Microporous and Mesoporous Materials* **225**: 289-295.
- [49] **Kejriwal, A., et al.** (2016). "cis-Dihydroxylation of electron deficient olefins catalysed by an oxo-bridged diiron(III) complex with H₂O₂." *Journal of Molecular Catalysis A: Chemical* **413**: 77-84.
- [50] **Nemoto, T., et al.** (2016). "Formal enantioselective synthesis of allosamizoline using chiral diamine-catalyzed asymmetric aziridination of cyclic enones." *Tetrahedron* **72**(16): 1991-1997.
- [51] **Liu, C., et al.** (2016). "Preparation and properties of phosphorous–nitrogen containing UV-curable polymeric coatings based on thiol–ene click reaction." *Progress in Organic Coatings* **90**: 21-27.
- [52] **Mamat, C., et al.** (2011). "Synthesis, structure determination, and (radio) fluorination of novel functionalized phosphanes suitable for the traceless Staudinger ligation." *Tetrahedron* **67**(25): 4521-4529.
- [53] **Hanack, M. And Heckmann, H., Polley, R.** (1998). Chapter II. (Aromatic and Hetero aromatic Large Rings), P 718-833, in (Methods in Organic Chemistry) Houben Weyl, Volume E9d, 4th edition. Thieme Medical Publishers. New York.
- [54] **Wagner, H. J., Loutfy, Rafik O., Hsiao, Cheng Kuo, J.,** (1982). "Purification and characterization of phthalocyanines". *Mat. Sci.* **17**: 2781- 2791.
- [55] **Kumar N.** (2012). Metal Phthalocyanines Catalyzed Selective Organic Transformations: Recent Developments and Promising Future. *Organic Chem Curr Res* **1**:109.

- [56] **Kumari P, Poonam, Chauhan SMS.** (2009). Efficient cobalt(II) phthalocyanine catalyzed reduction of flavones with sodium borohydride. *Chem Commun (Camb)*. 6397-6399.
- [57] **Tau, P., Nyokong, T.** (2006). Synthesis, electrochemical and photophysical properties of phthalocyaninato oxotitanium(IV) complexes tetrasubstituted at the alpha and beta positions with arylthio groups, *Dalton Transactions*, **37**: 4482-4490.
- [58] **Kalkan, A.** (2003). Yeni bir Ftalosiyenin Porfirazin Hibrit Bilesiğinin Sentezi, Yüksek Lisans Tezi, I.T.U. Fen Bilimleri Enstitüsü, İstanbul.
- [59] **Stillman, M.J., Nyokong T.** (1989) in *Phthalocyanines: Properties and Applications*, eds. C.C. Leznoff and A.B.P. Lever, VCH Publishers, New York, Vol.1.
- [60] **Sharma U, Kumar P, Kumar N, Kumar V, Singh B** (2010) Highly chemo- and regioselective reduction of aromatic nitro compounds catalyzed by recyclable copper (II) as well as cobalt (II) phthalocyanines. *Adv Synth Catal* **352**: 1834- 1840.
- [61] **Young, J. G., Onyebuagu, W.** (1990). Synthesis and characterization of didisubstituted phthalocyanines, *Journal of Organic Chemistry*, **55**, 7, 2155-2159.
- [62] **Kahl, S. B., Li, J.** (1996) Synthesis and Characterization of a Boronated Metallophthalocyanine for Boron Neutron Capture Therapy, *Inorg. Chem.*, **35**, 3878-3880.
- [63] **Filippis, M. P., Dei, D., Roncucci G.** (2000). Synthesis of a new water-soluble octa cationic phthalocyanine derivative for PDT, *Tetrahedron Letters*, **41**: 9143-9147.
- [64] **Weiss, R., Fischer, J.** (2003). *The Porphyrin Handbook*, **15**: 19-26.
- [65] **Xu, H., et al.** (2013). "Dye sensitization of polymer/fullerene solar cells incorporating bulky phthalocyanines." *Electrochimica Acta* **100**: 214-219.
- [66] **Şen, B. N., et al.** (2014). "Synthesis and characterization of terminalalkynyl-substituted unsymmetrical zinc phthalocyanine conjugated with well-defined polymers." *Dyes and Pigments* **100**: 1-10.
- [67] **Özdağ, A., M., et al.** (2011). "Optical limiting properties of trimeric metallo-phthalocyanines/polymer composite films." *Optics & Laser Technology* **43**(6): 992-995.
- [68] **Masilela, N., et al.** (2013). "Photodynamic inactivation of *Staphylococcus aureus* using low symmetrically substituted phthalocyanines supported on a polystyrene polymer fiber." *Dyes and Pigments* **96**(2): 500-508.

[69] **Pochtennyi, A. E., et al.** (2014). "Conductivity of copper phthalocyanine-polystyrene composite films in the presence of adsorbed oxygen." *Technical Physics* **59**(9): 1400-1402.

[70] **Singhal.** (2009). *The Pearson Guide To Organic Chemistry For The Iit Jee*, Pearson Education.

[71] **Dinçer, H., et al.** (2015). "Synthesis and photophysical studies of poly(ethylene glycol) conjugated symmetrical and asymmetrical zinc phthalocyanines." *Journal of Molecular Structure* **1102**: 190-196.

[72] **Young, J., Onyebuagu, W.** (1990). Synthesis and Characterization of Disubstituted Phthalocyanines, *J. Org. Chem.* **55**:2155-2159.

[73] **Altintas O, Yankul B, Hizal G, Tunca U.** (2006). A(3)-type star polymers via click chemistry. *J Polym Sci Part A Polym Chem.* **44**: 6458-65.

APPENDIXES

APPENDIX A: Spectral data of the compounds.

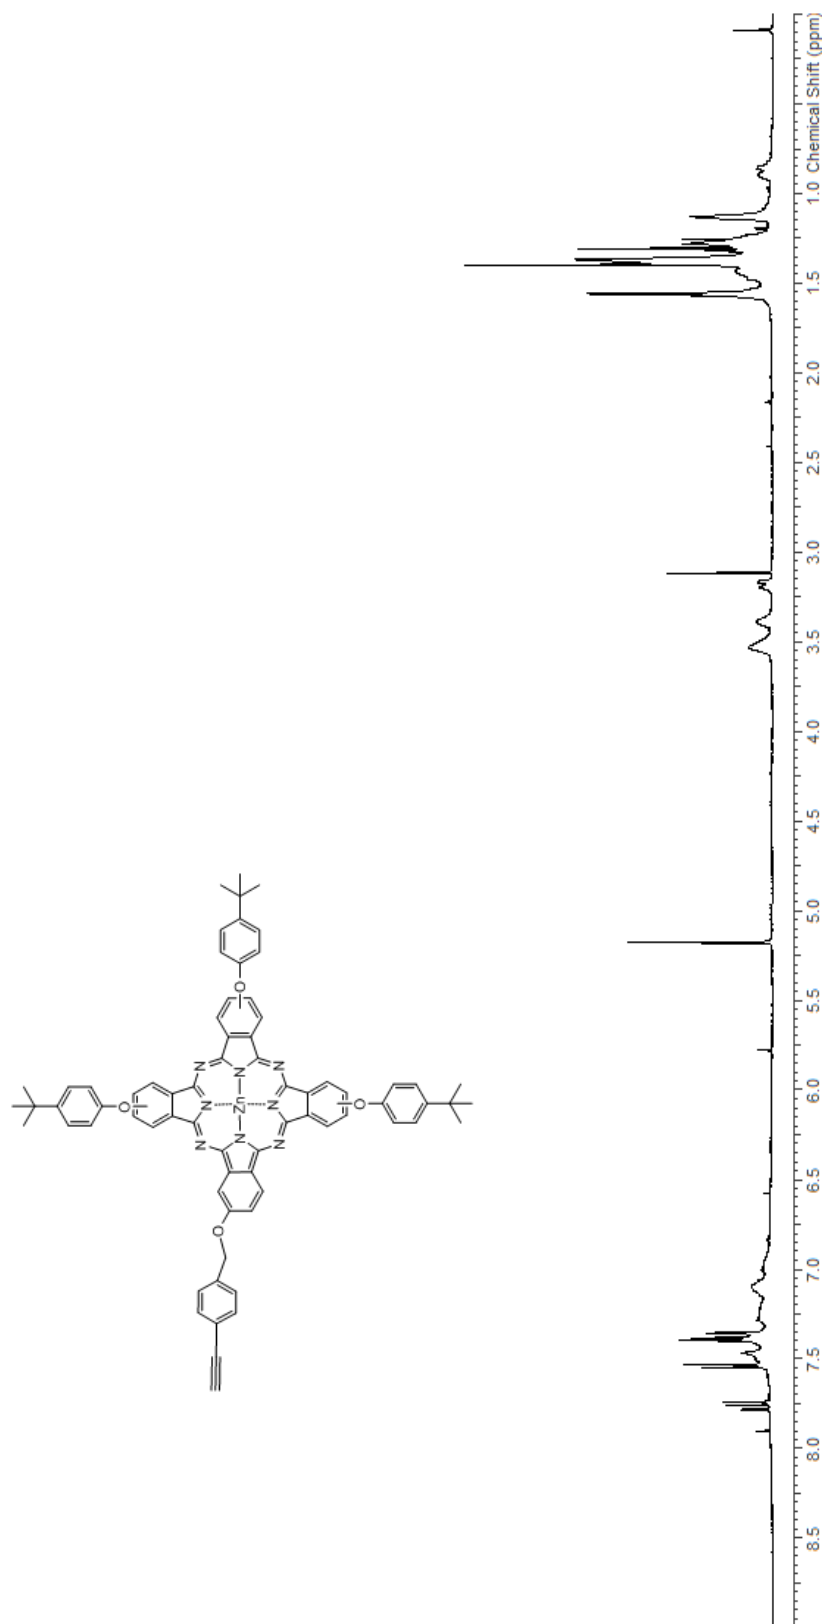


Figure A. 1: ¹H-NMR spectrum of unsymmetrical ZnPc.

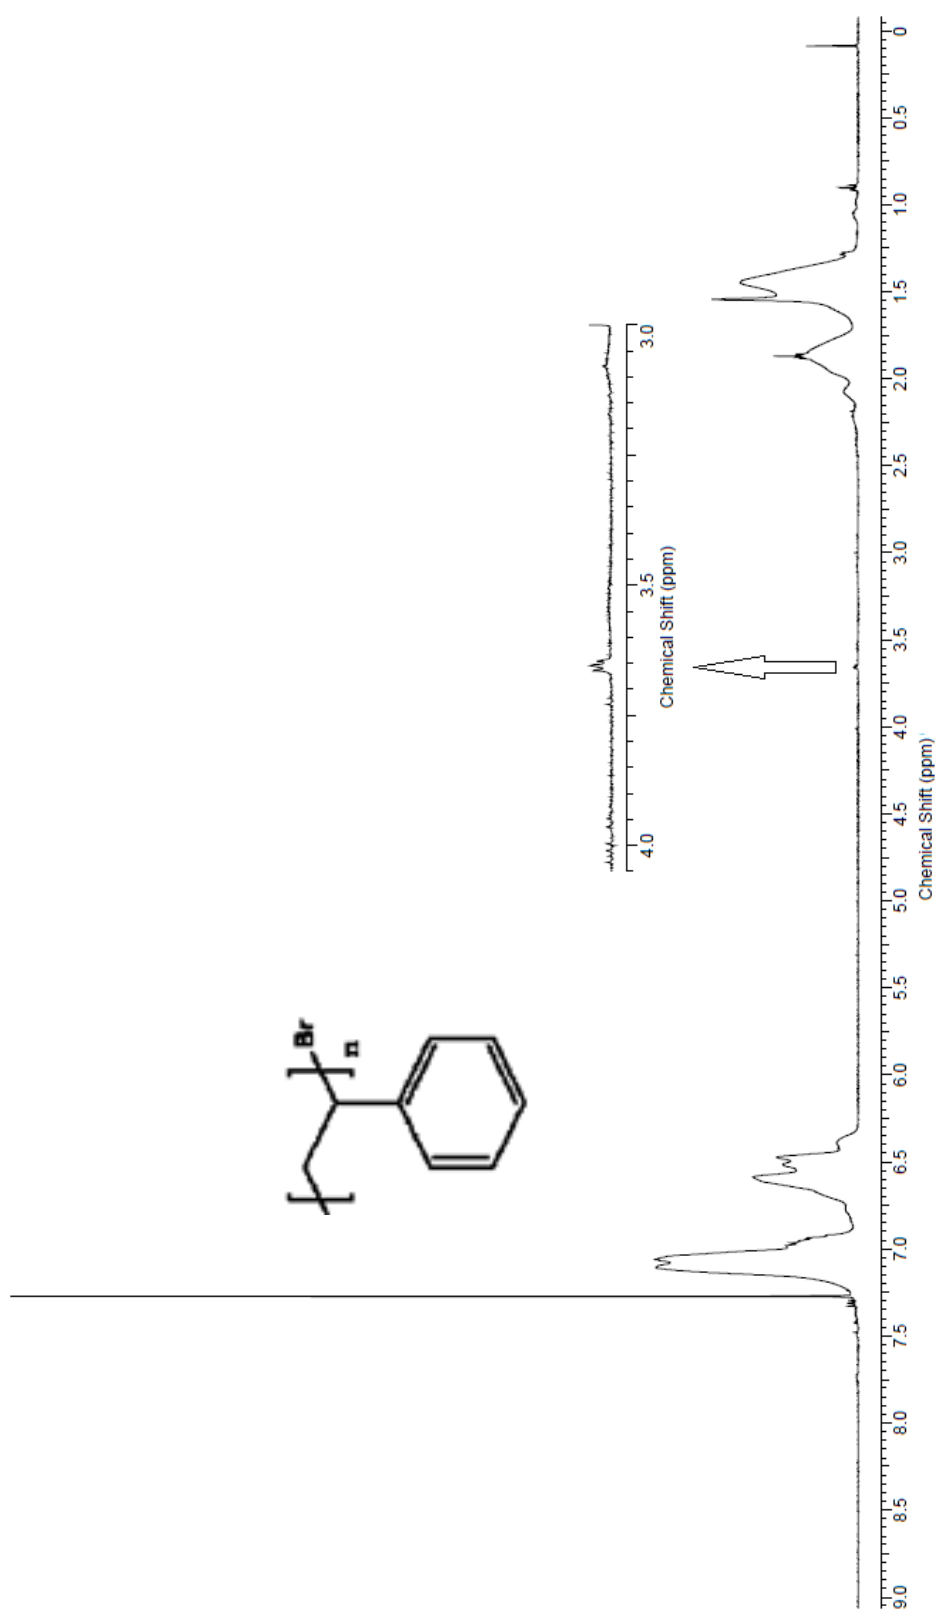


Figure A. 2: $^1\text{H-NMR}$ spectrum of PS-Br.

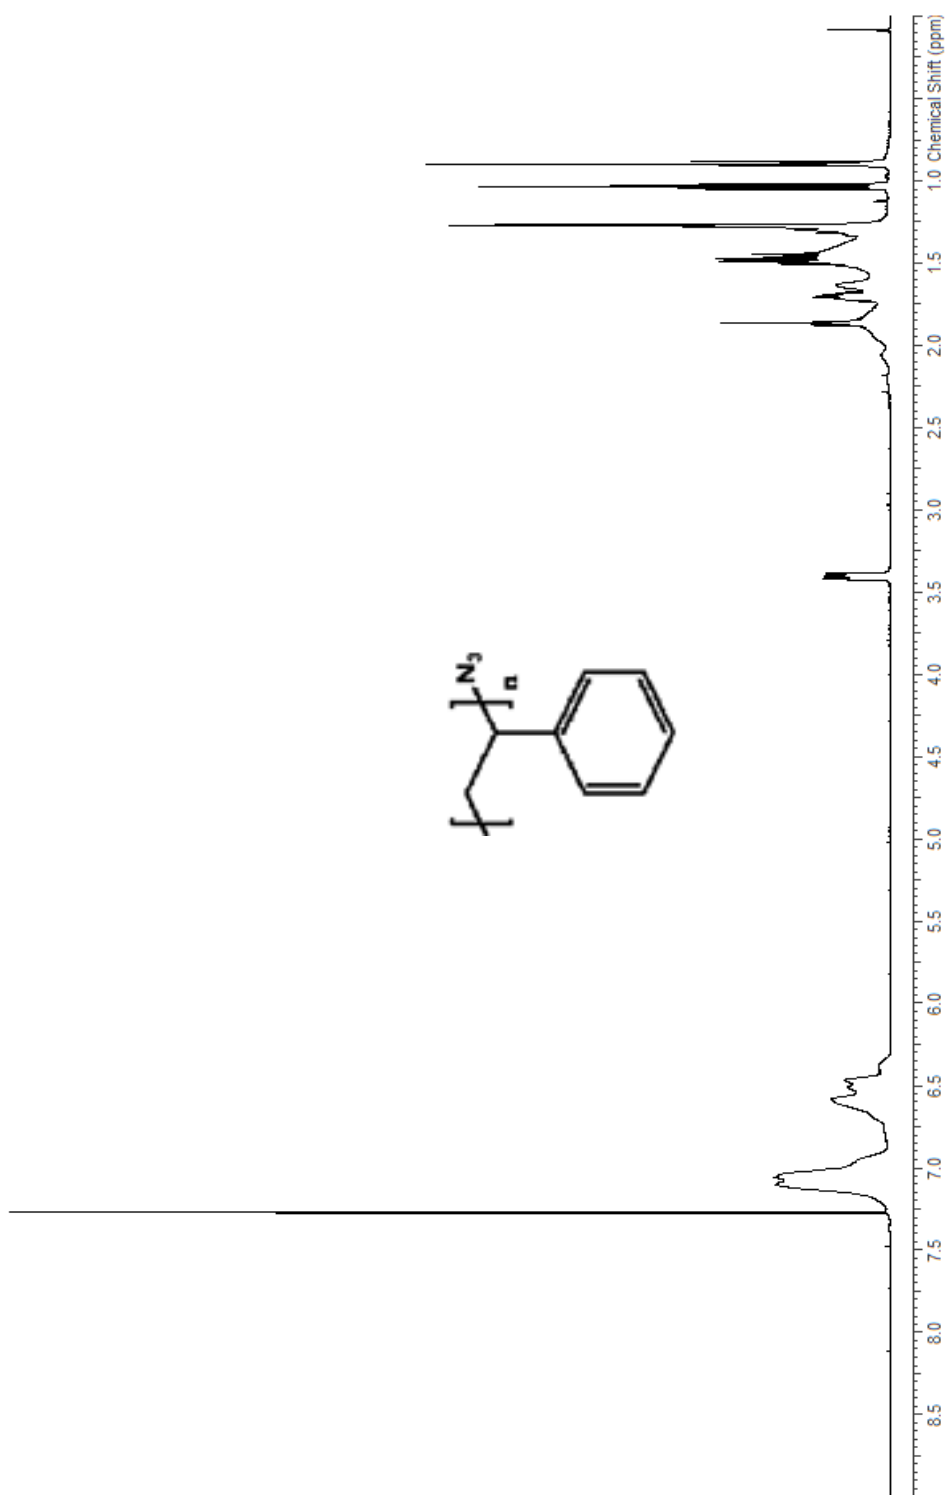


Figure A. 3: $^1\text{H-NMR}$ spectrum of PS- N_3 .

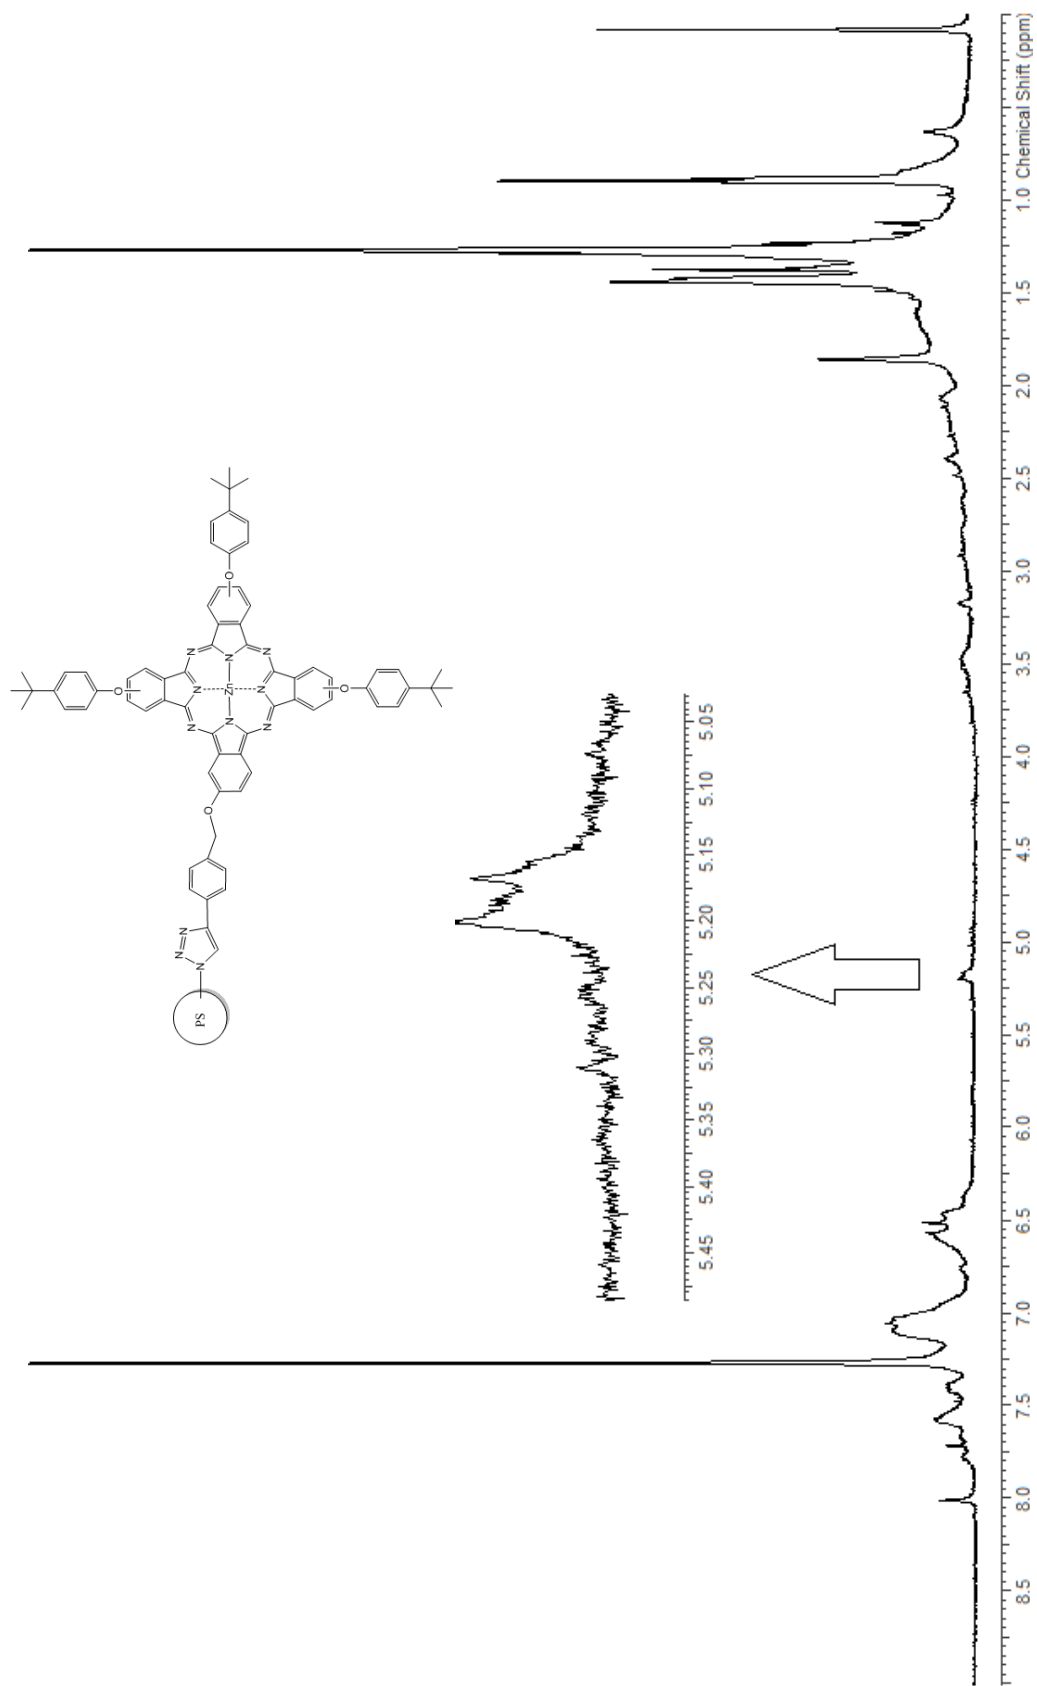


Figure A. 4: $^1\text{H-NMR}$ spectrum of PS-ZnPc.

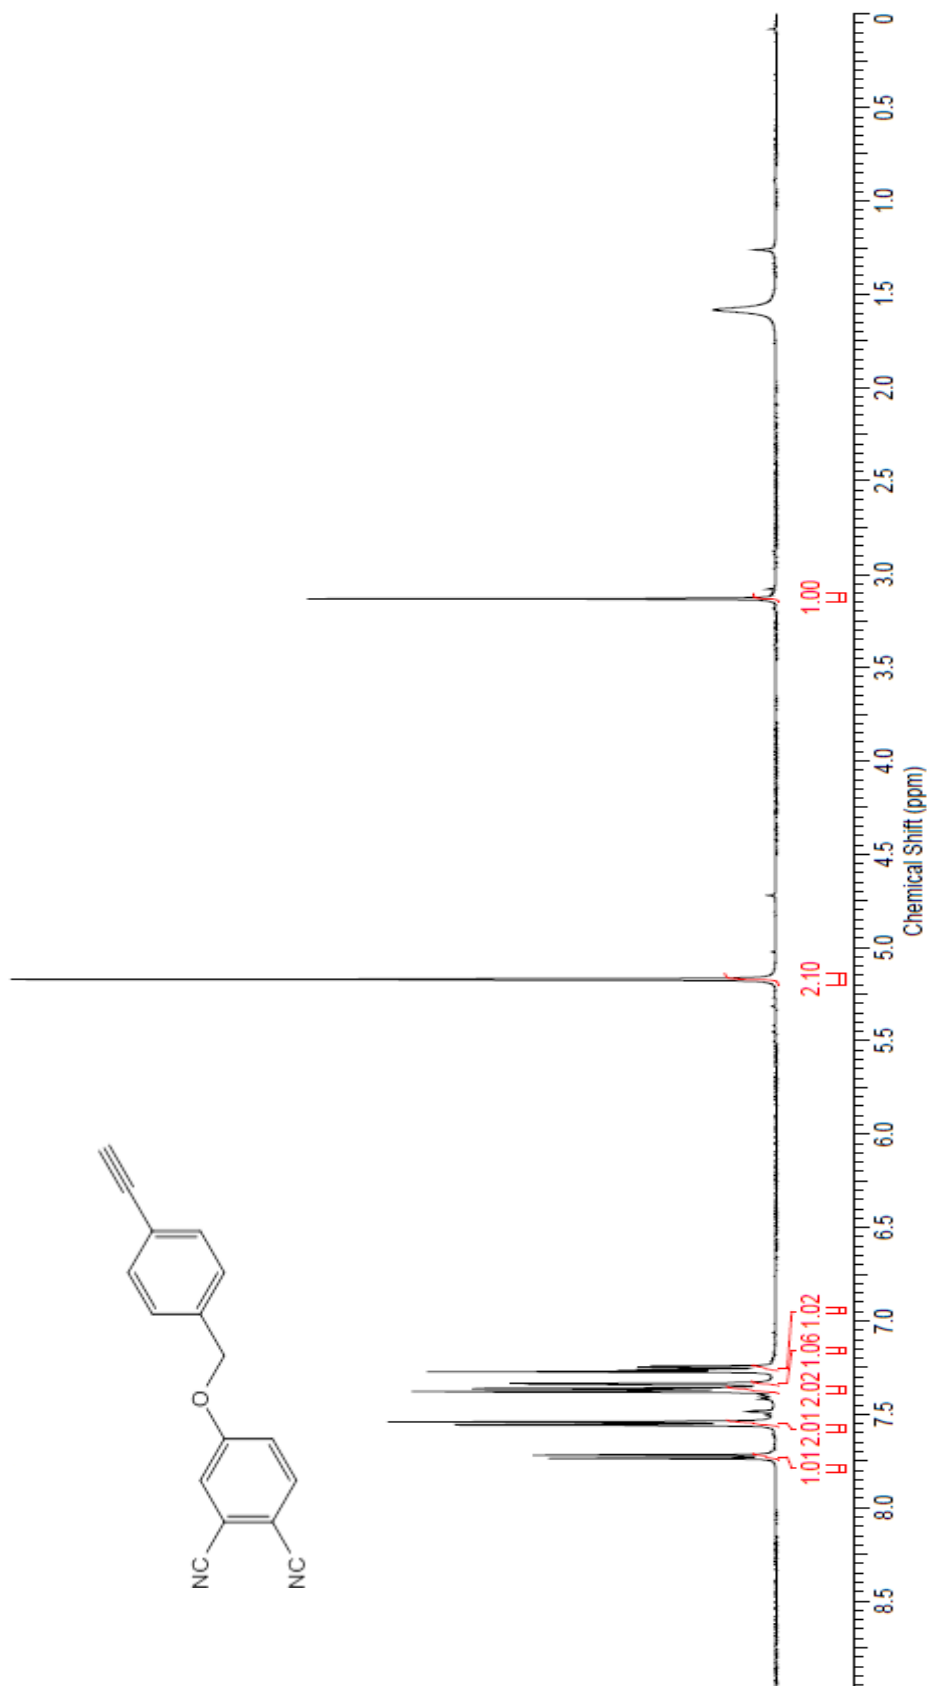


Figure A. 5: $^1\text{H-NMR}$ spectrum of 4-((4-ethynylbenzyl)oxy)phthalonitrile.

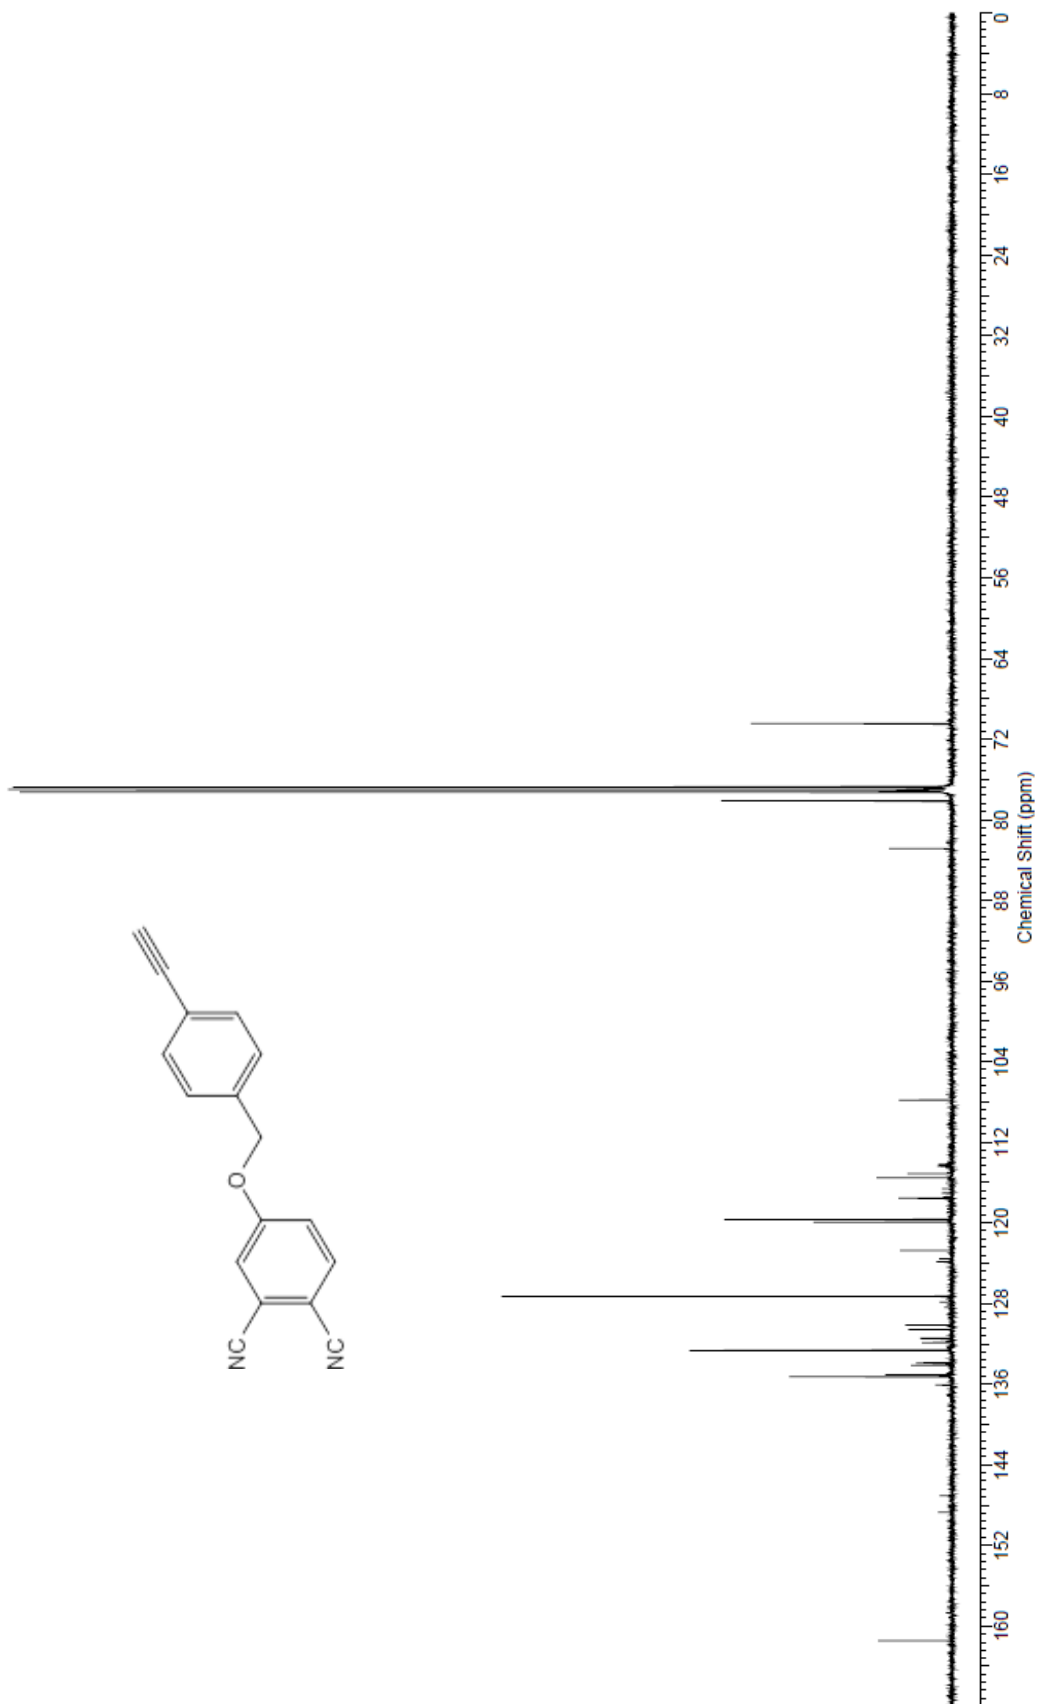


Figure A. 6: ^{13}C -NMR spectrum of 4-((4-ethynylbenzyl)oxy)phthalonitrile.

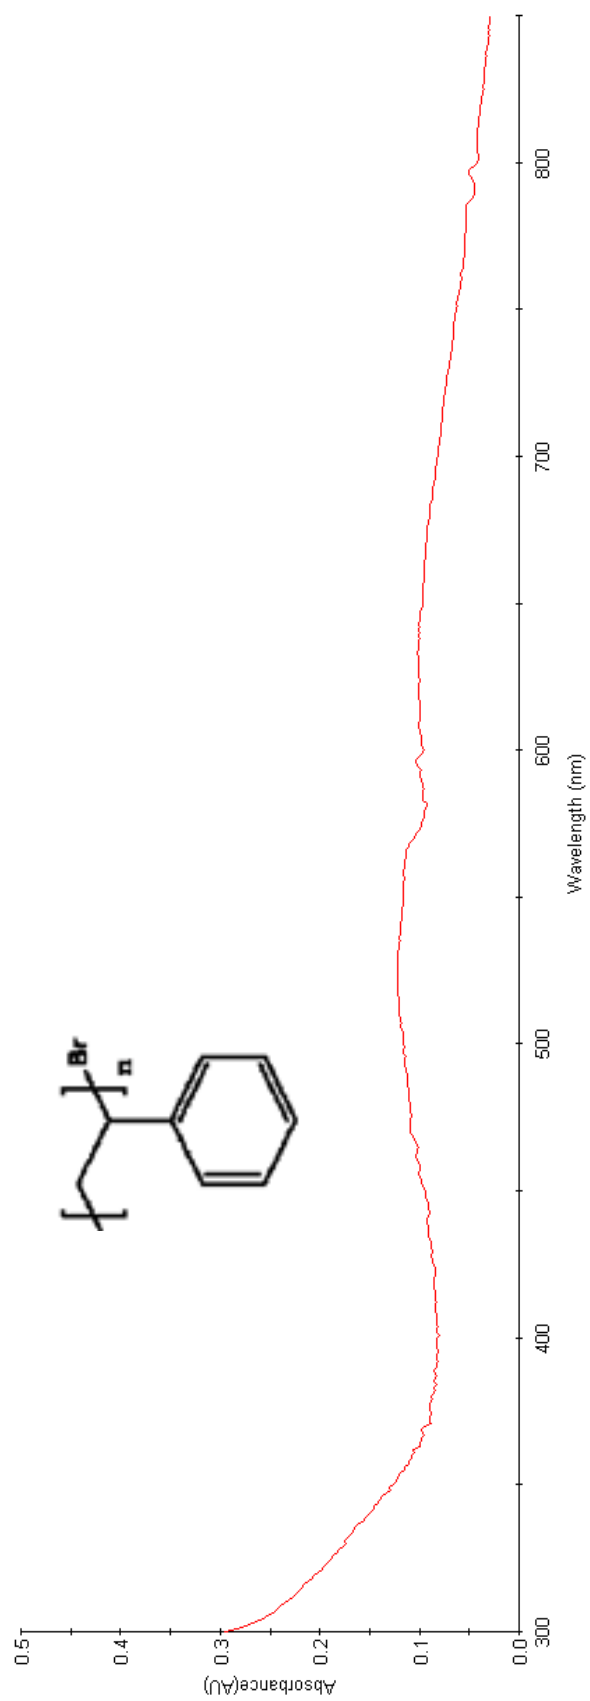


Figure A. 7: UV-Vis spectrum of PS-Br.

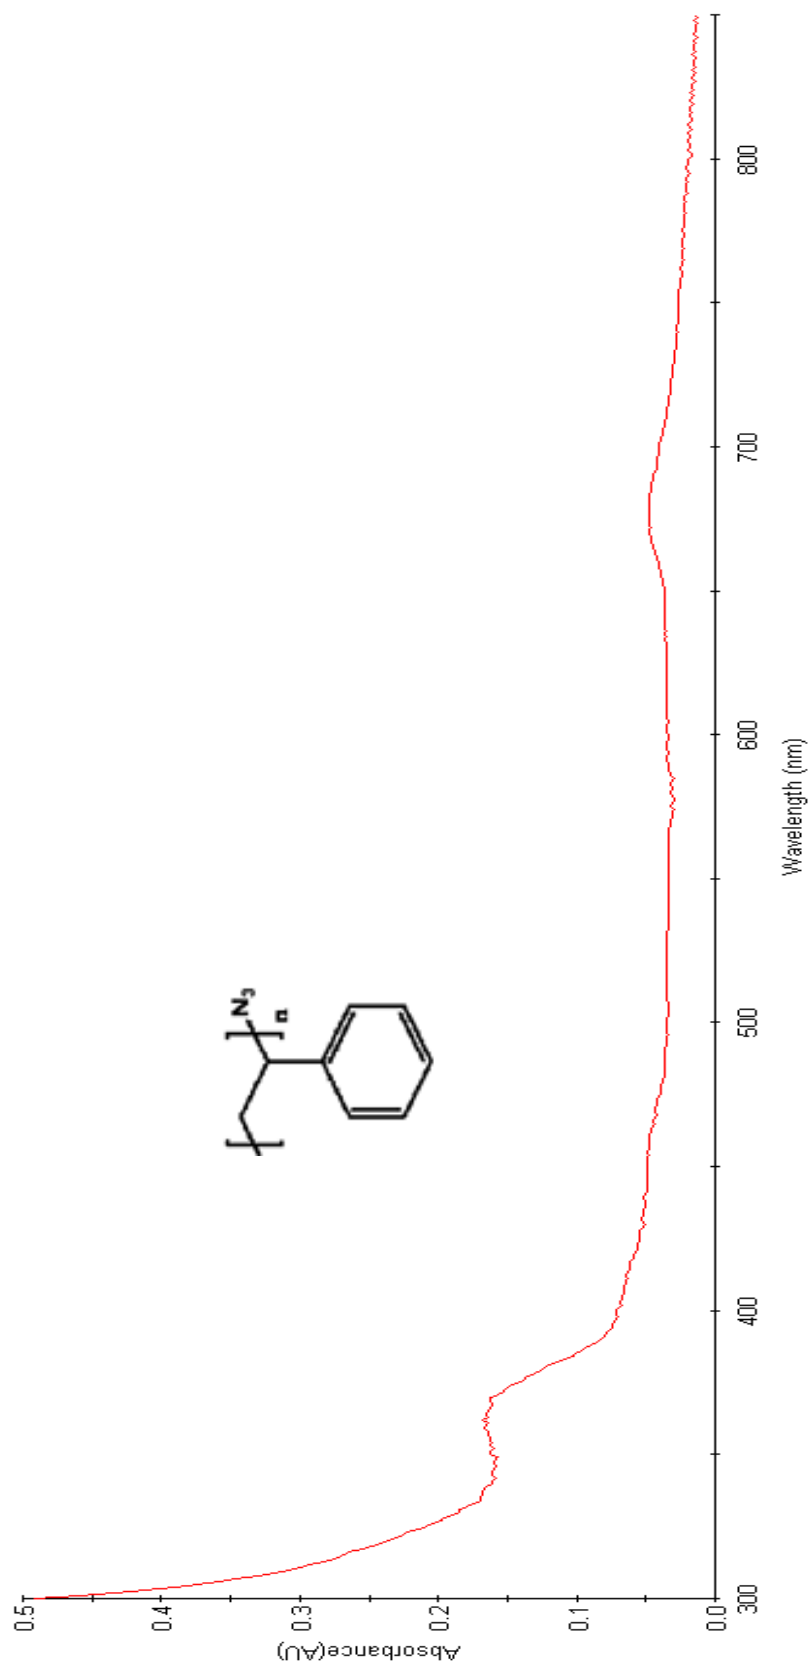


Figure A. 8: UV-Vis spectrum of PS-N₃.

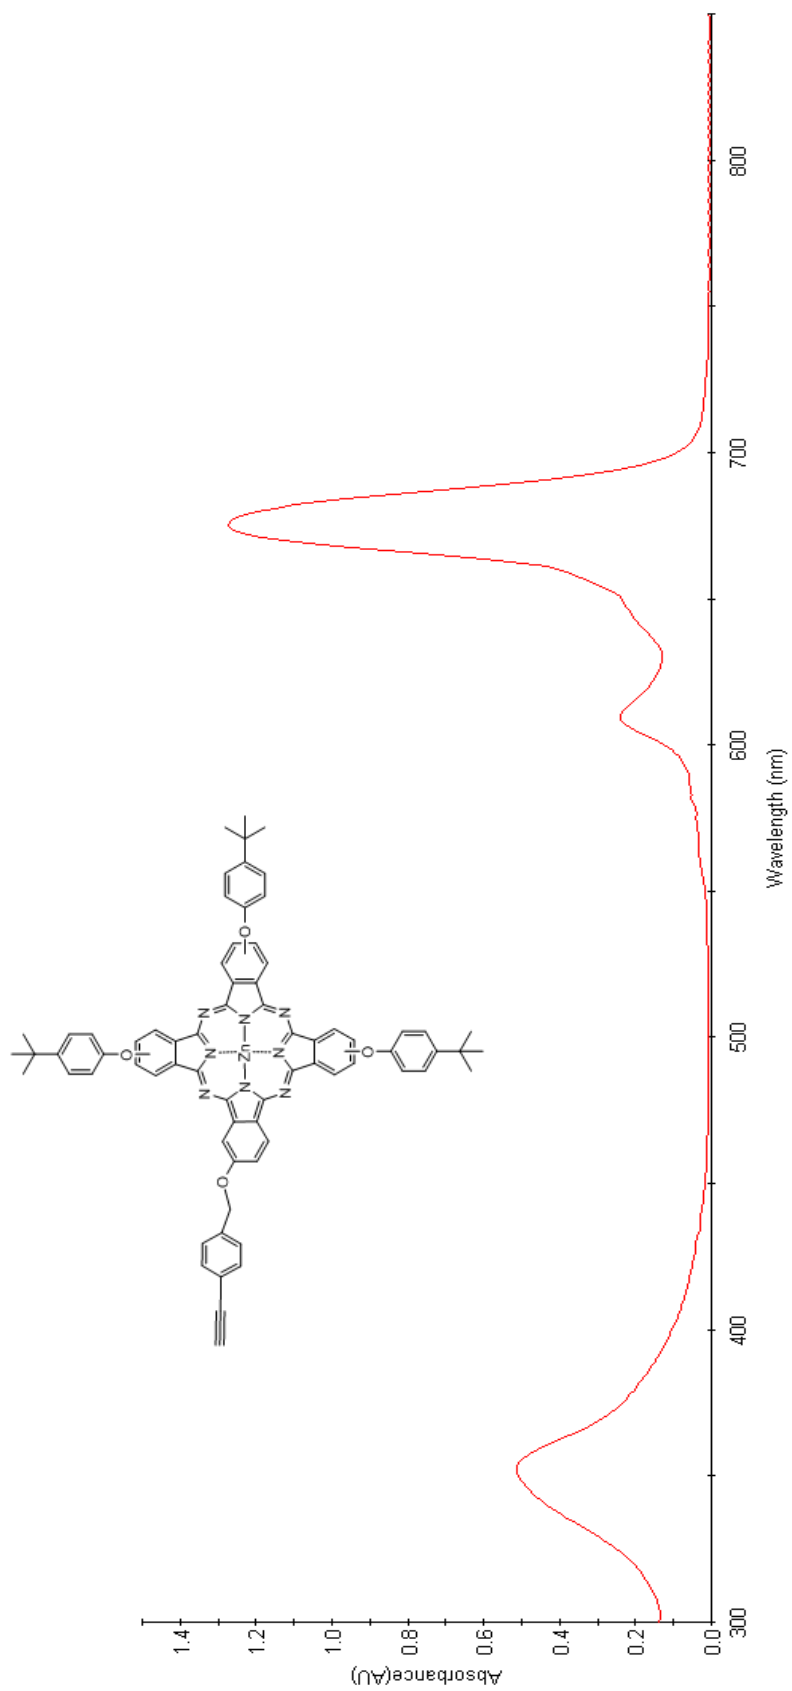


Figure A. 9: UV-Vis spectrum of ZnPc.

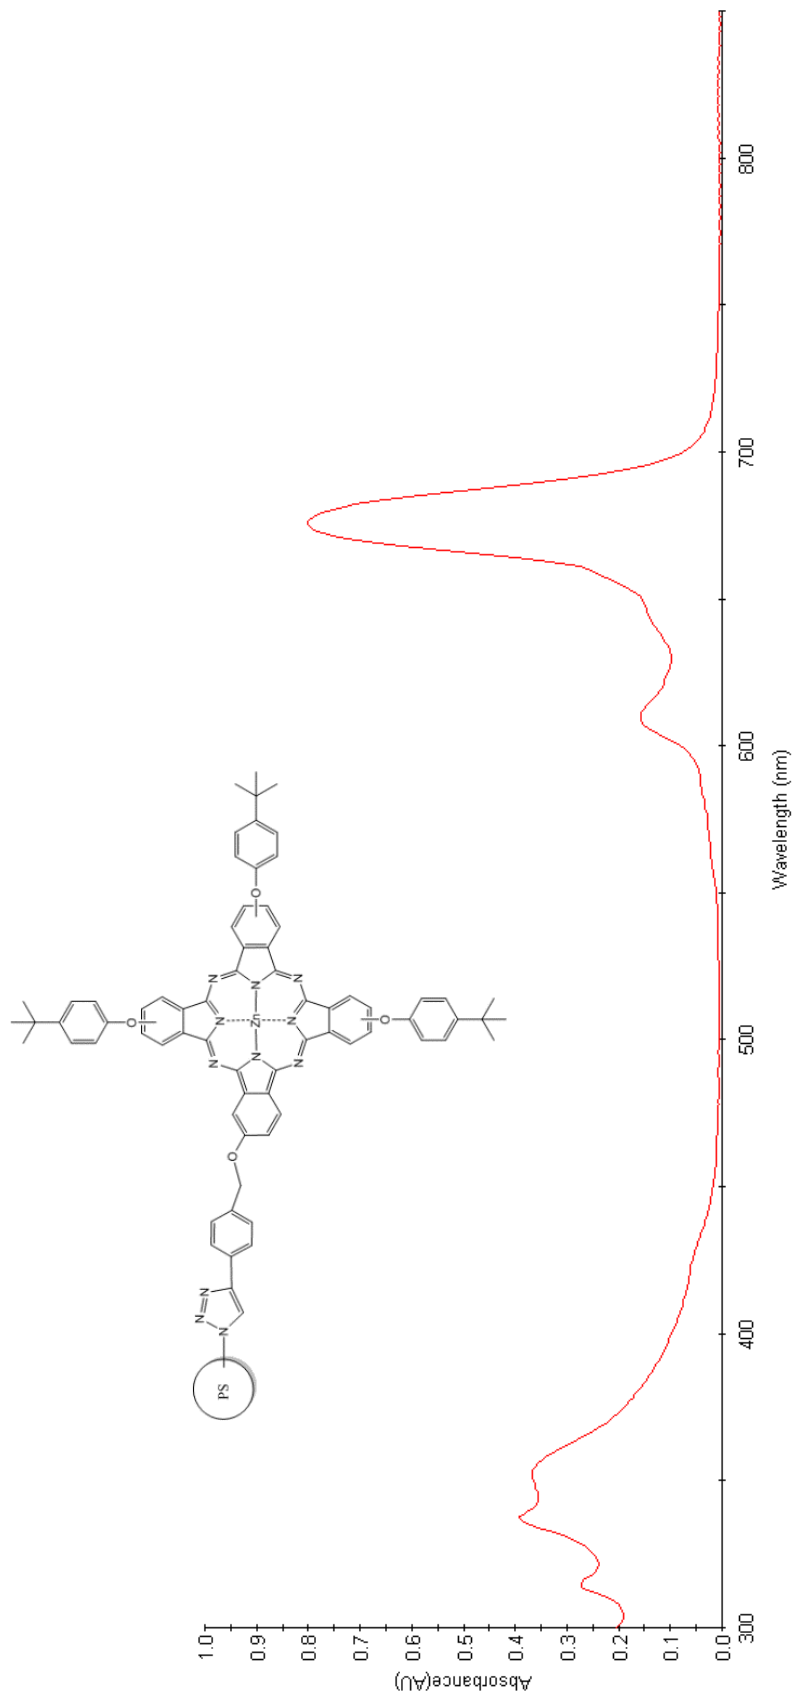


Figure A. 10: UV-Vis spectrum of PS-ZnPc.

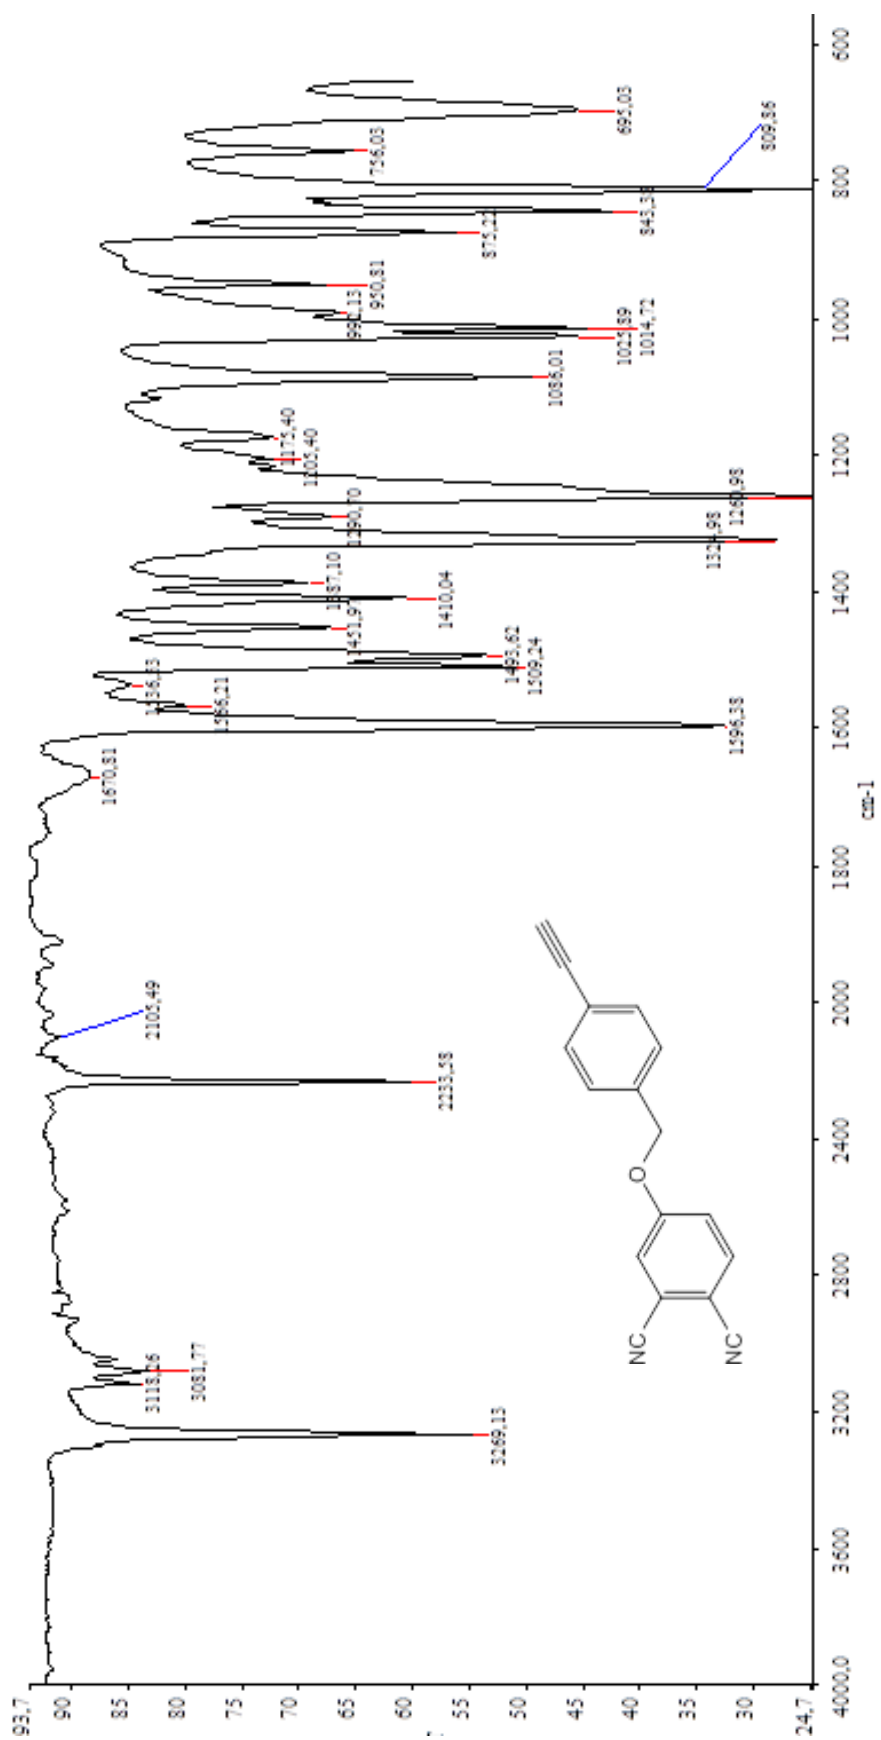


Figure A. 11: FT-IR spectrum of (4).

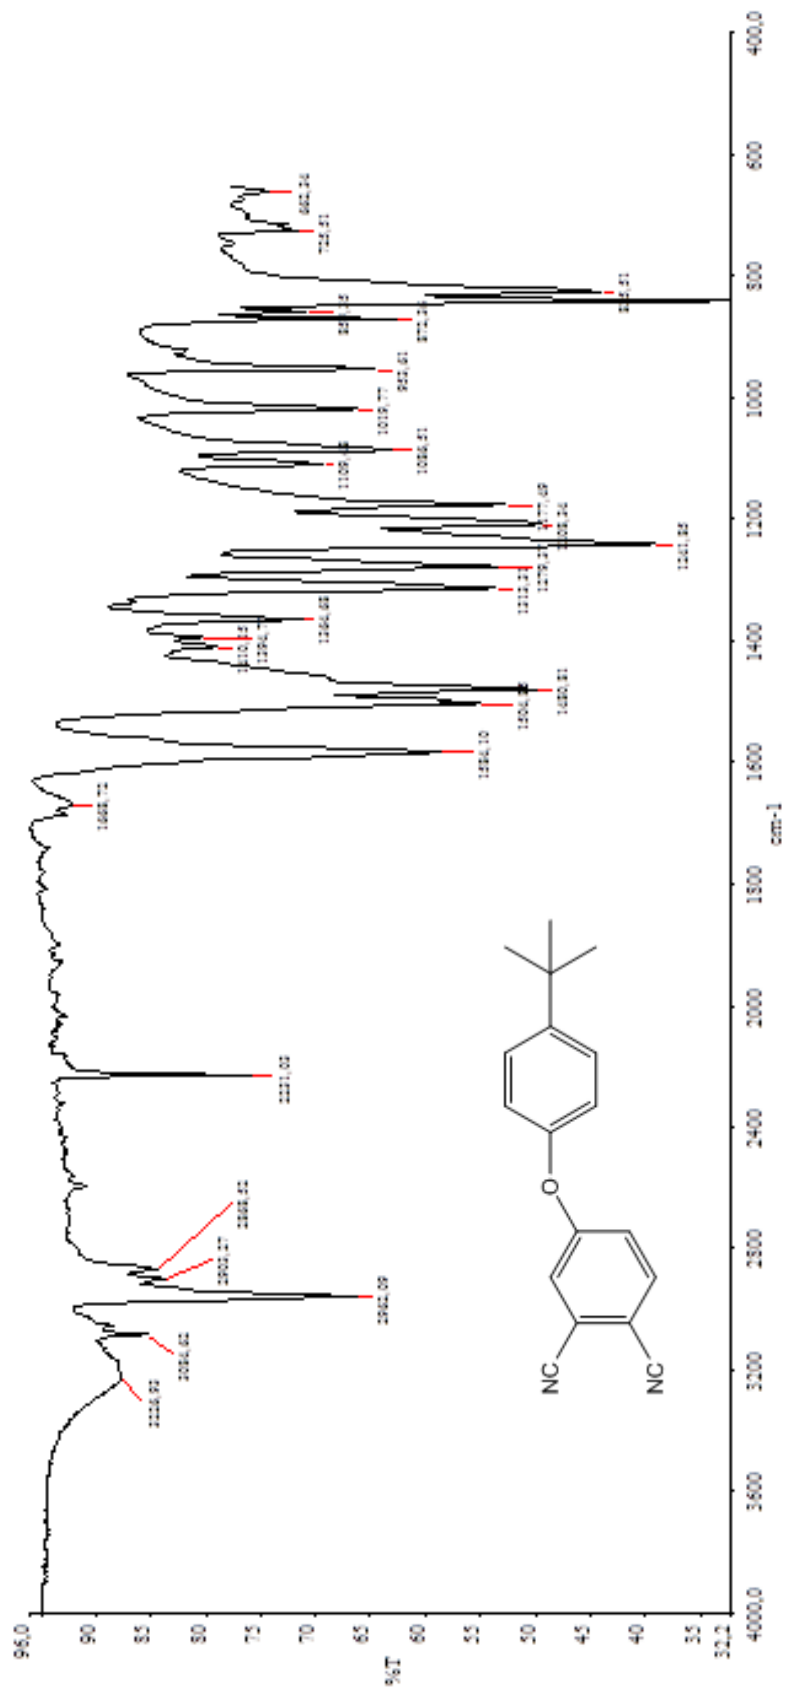


Figure A. 12: FT-IR spectrum of (3).

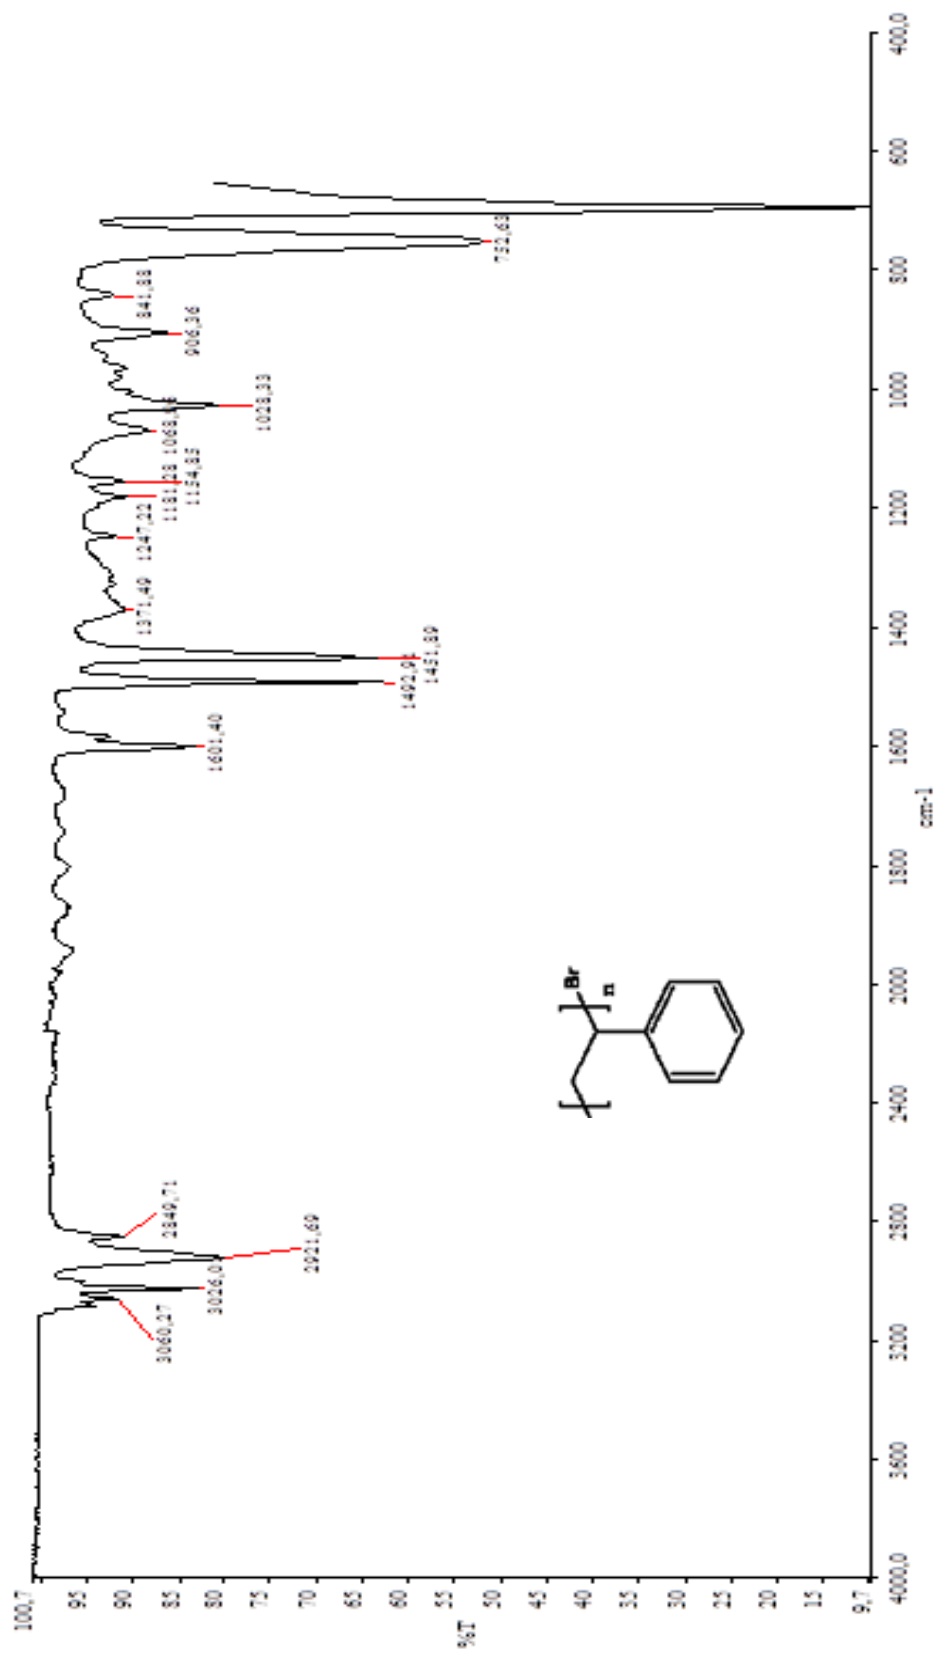


Figure A. 13: FT-IR spectrum of PS-Br.

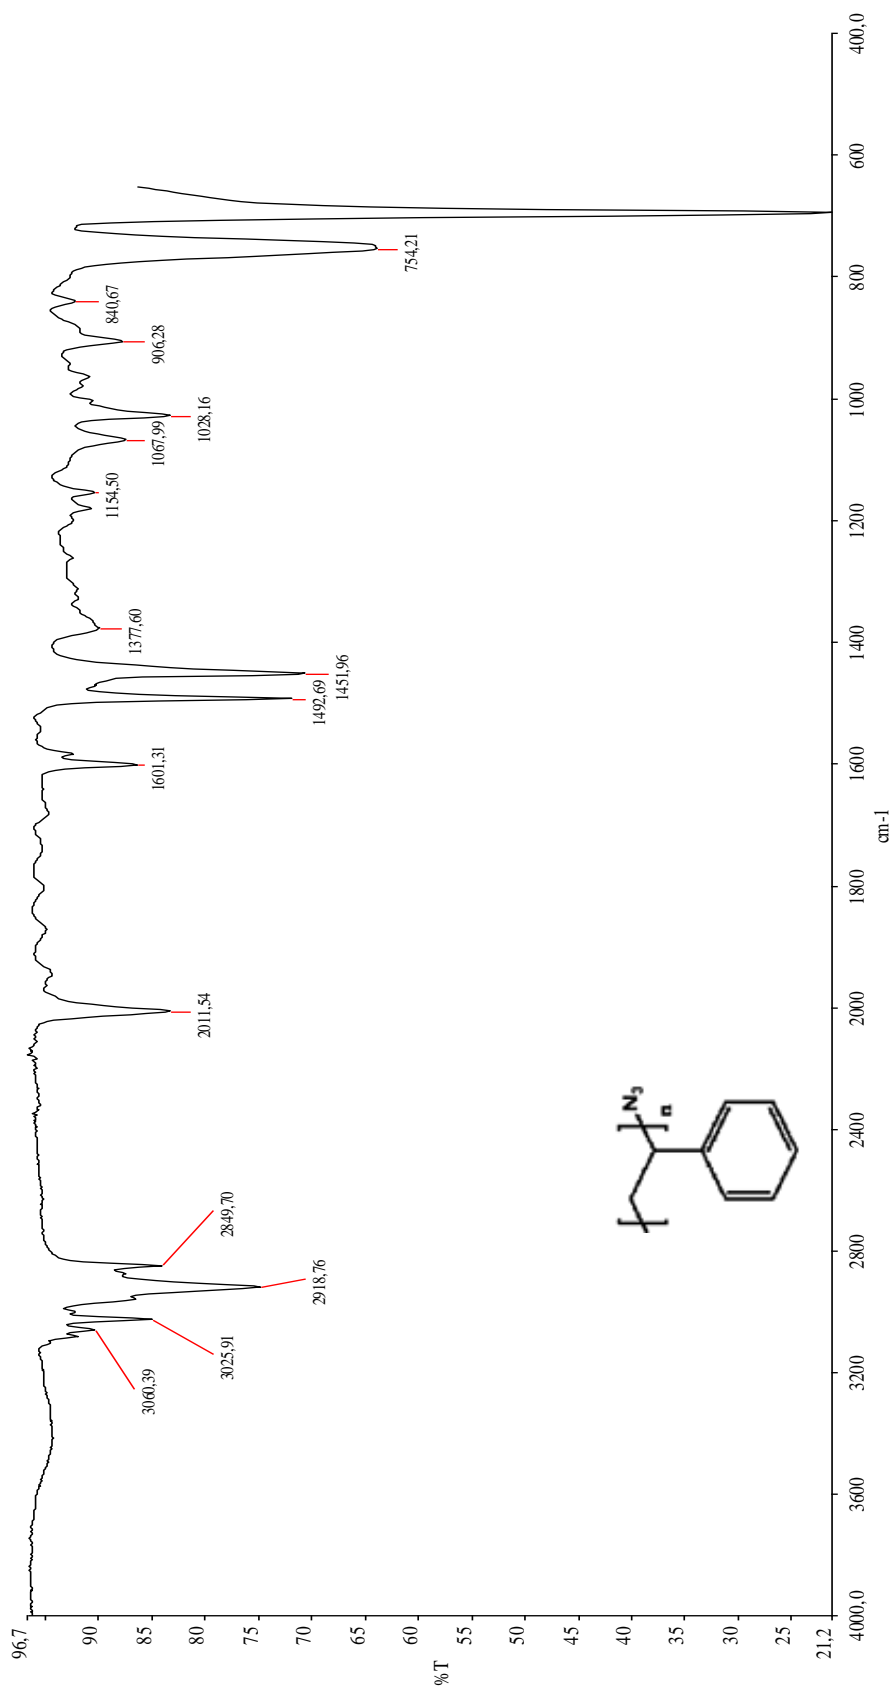


Figure A. 14: FT-IR spectrum of PS-N₃.

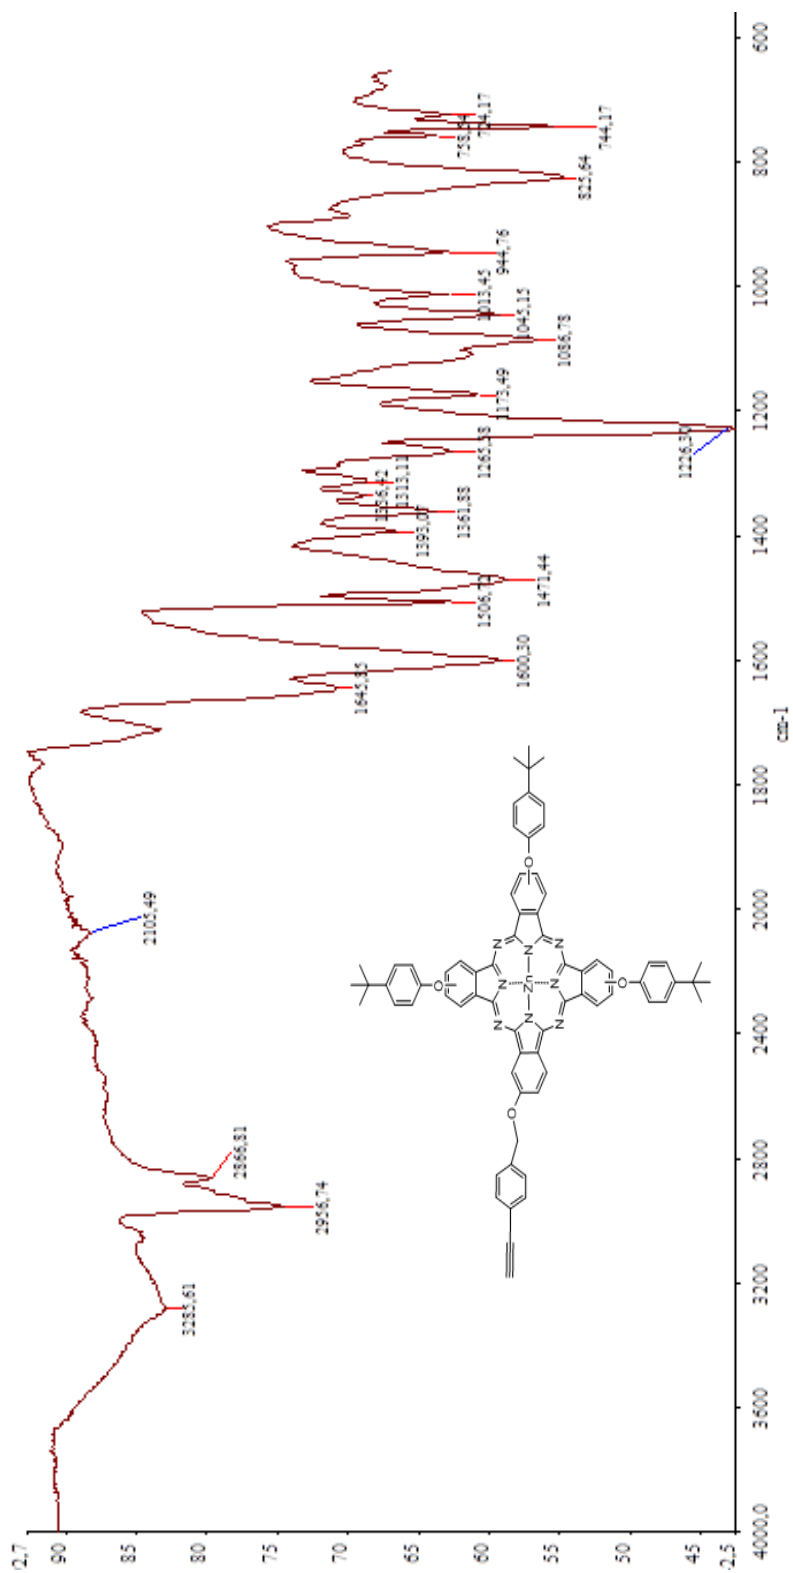


Figure A. 15: FT-IR spectrum of ZnPc.

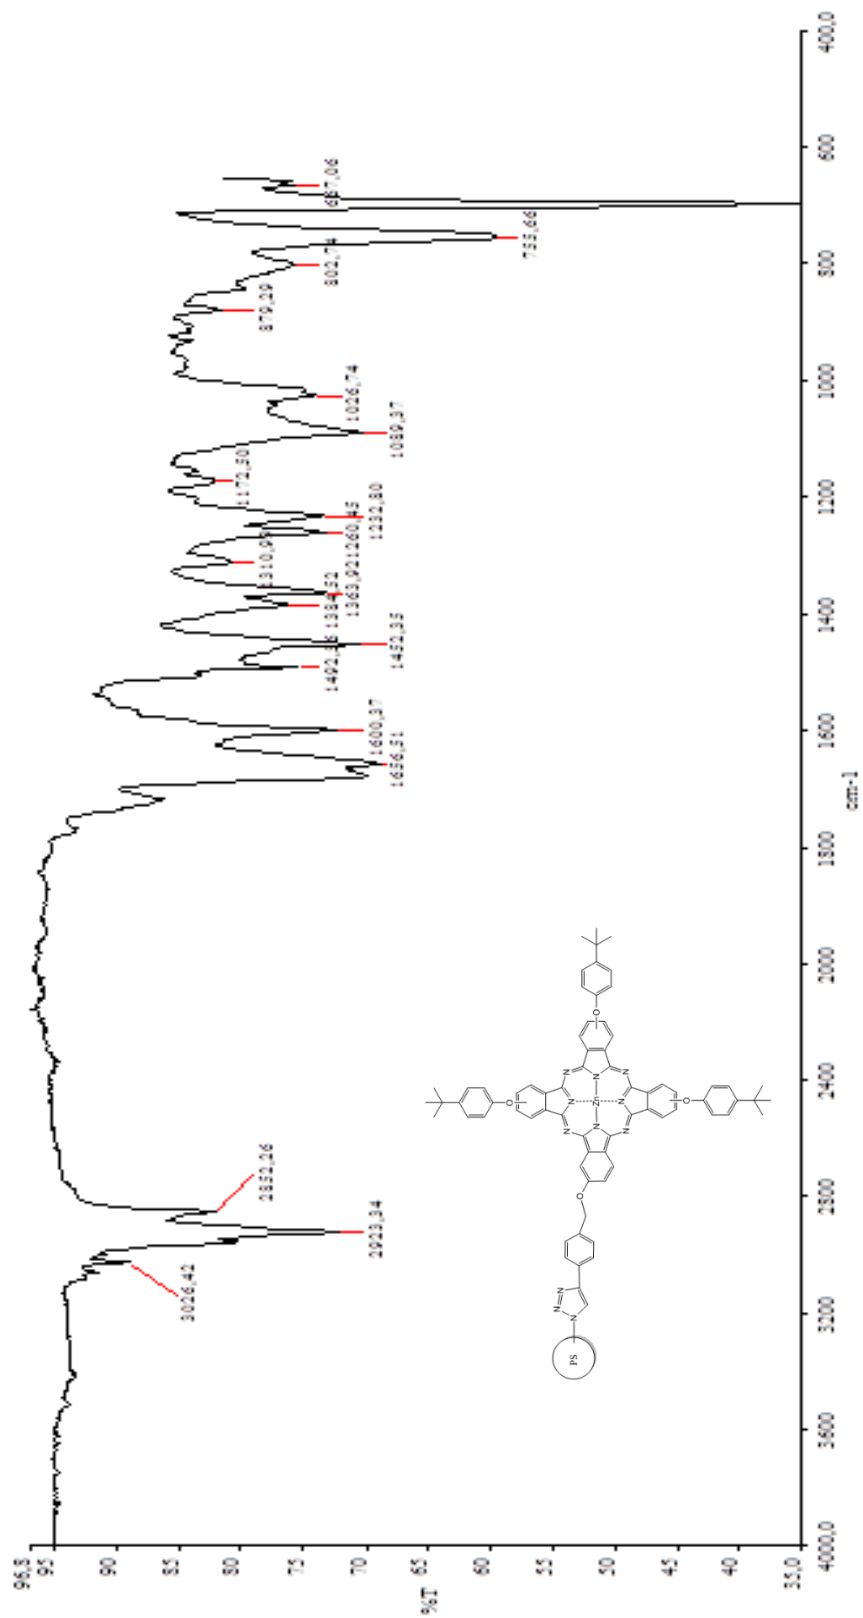


Figure A. 16: FT-IR spectrum of PS-ZnPc.

CURRICULUM VITAE



Name Surname : Yunus Alp SÜTCÜLER
Place and Date of Birth : Kocaeli, 25/ 01/ 1991
E-Mail : alpsutculer77@gmail.com

EDUCATION

M.Sc. : 2016, Istanbul Technical University, Graduate School of Science Engineering and Technology, Polymer Science and Technology

B.Sc. : 2014, Ankara University, Faculty of Science, Chemistry

PROJECTS

TÜBİTAK Project (114R117) : 2015, Istanbul Technical University-
“Photocatalytic Degradation of Persistent Organic Pollutants in Aqueous Medium with Visible Light by Using TiO₂ Impregnated with Non-symmetric Metallophthalocyanines”

TÜBİTAK Project (114M524) : 2014, Istanbul Technical University-
“Synthesis of graphene fiber and researching of the gas adsorption behaviour”